

Chemical Engineering

Mechanical Operations

Comprehensive Theory

with Solved Examples and Practice Questions



MADE EASY
Publications



MADE EASY Publications Pvt. Ltd.

Corporate Office: 44-A/4, Kalu Sarai (Near Hauz Khas Metro Station), New Delhi-110016

E-mail: infomep@madeeasy.in

Contact: 011-45124612, 0-9958995830, 8860378007

Visit us at: www.madeeasypublications.org

Mechanical Operations

© Copyright, by MADE EASY Publications Pvt. Ltd.

All rights are reserved. No part of this publication may be reproduced, stored in or introduced into a retrieval system, or transmitted in any form or by any means (electronic, mechanical, photo-copying, recording or otherwise), without the prior written permission of the above mentioned publisher of this book.

First Edition : 2021

Contents

Mechanical Operations

Chapter 1

Properties and Handling of

Particulate Solids 1

1.1 Introduction	1
1.2 Characterization of Solid Particles	2
1.3 Mixed and Average Size Analysis	3
1.4 Screening	7
<i>Student's Assignments</i>	13

Chapter 2

Size Reduction Laws & Equipments 17

2.1 Introduction	17
2.2 Crushing Efficiency	18
2.3 Mechanical Efficiency	18
2.4 Laws of Size Reduction	19
2.5 Size-Reduction Equipment	20
<i>Student's Assignments</i>	28

Chapter 3

Sedimentation and Fludization.....31

3.1 Separations based on the Motion of Particles through Fluids	31
3.2 Sorting Classifiers.....	32
3.3 Clarifiers and Thickeners.....	33
3.4 Centrifugal Settling Processes.....	35
3.5 Principles of Centrifugal Sedimentation.....	35
3.6 Fluidization.....	37
3.7 Terminal Velocity	39

3.8 Flow through a Packed Bed.....	40
<i>Student's Assignments</i>	45

Chapter 4

Filtration.....48

4.1 Introduction	48
4.2 Filtration Mechanism	48
4.3 Characteristics of a Good Filter	49
4.4 Filter Media and Filter Aids	49
4.5 Theory of Filtration	50
4.6 Modes of Filtration.....	51
4.7 Filtration Equipments.....	53
4.8 Centrifugal Filtration.....	57
<i>Student's Assignments</i>	62

Chapter 5

Mixing and Agitation67

5.1 Introduction	67
5.2 Purposes of Agitation	67
5.3 Impellers.....	67
5.4 Power Consumption.....	68
<i>Student's Assignments</i>	74

Chapter 6

Transportation & Storage of Solids.....76

6.1 Introduction	76
6.2 Storage of Solids.....	77
6.3 Bulk Solids Conveying	78
<i>Student's Assignments</i>	81



Properties and Handling of Particulate Solids

LEARNING OBJECTIVES

The reading of this chapter will enable the students

- To understand the characterization of solid particles.
- To understand the mixed and average size analysis.
- To understand the concept of screening and screening equipment.
- To understand the concept of screen effectiveness and capacity.

1.1 Introduction

Mechanical Unit Operations are the operations which are purely based on physical or mechanical forces such as

- Gravitational force
- Centrifugal force
- Mechanical and kinetic forces arising from flow

So, the unit operations of which are purely based on mechanical or physical forces such as gravitational force, centrifugal force, mechanical or kinetic forces arising from flow, etc. they are known as the kind of mechanical unit operations.

Mechanical Unit Operations can be classified based on phases interacting as

- Solid-Solid Operations : Crushing, grinding, sieving, compaction, cutting, storage and transport of bulk solids, etc.
- Solid-Fluid Operations : Filtration, sedimentation, centrifugation, floatation, cyclone separators, etc.

Unit Operations involving Particulate Solids :

- Separation of solids from a suspension by filtration.
- Fractionation of solids of wide size distribution based on size by gravity settling or differential settling methods.
- Separation of immiscible liquids by centrifugation (or decanting) and separation of solids from liquids by centrifugation.

1.2 Characterization of Solid Particles

Individual solid particles are characterized by their size, shape, and density. Particles of homogeneous solids have the same density as the bulk material. Particles obtained by breaking up a composite solid, such as a metal-bearing ore, have various densities, usually different from the density of the bulk material. Size and shape are easily specified for regular particles, such as spheres and cubes, but for irregular particles (such as sand grains or mica flakes) the terms size and shape are not so clear and must be arbitrarily defined.

1.2.1 Particle Shape

The shape of an individual particle is conveniently expressed in terms of the sphericity ϕ_s , which is independent of particle size. For a spherical particle of diameter D_p , $\phi_s = 1$; for a non-spherical particle, the sphericity is defined by the relation

$$\phi_s = \frac{6V_p}{D_p S_p} \quad \dots(1.1)$$

where,

D_p = equivalent diameter or nominal diameter of particle

S_p = surface area of one particle

V_p = volume of one particle

The equivalent diameter is sometimes defined as the diameter of a sphere of equal volume. For fine granular materials, however, it is difficult to determine the exact volume and surface area of a particle, and D_p is usually taken to be the nominal size based on screen analyses or microscopic examination. For many crushed materials ϕ_s is between 0.6 and 0.8, as shown in table given below, but for particles rounded by abrasion ϕ_s may be as high as 0.95.

For cubes and cylinders for which the length L equals the diameter, the equivalent diameter is greater than L and ϕ_s found from the equivalent diameter would be 0.81 for cubes and 0.87 for cylinders. It is more convenient to use the nominal diameter L for these shapes since the surface-to-volume ratio is $6/D_p$, the same as for a sphere, and this makes ϕ_s equal to 1.0. For column packings such as rings and saddles the nominal size is also used in defining ϕ_s .

1.2.2 Particle Size

In general, "diameters" may be specified for any equidimensional particle. Particles that are not equidimensional, i.e., that are longer in one direction than in others, are often characterized by the second longest major dimension. For needlelike particles, for example, D_p would refer to the thickness of the particles, not their length.

Table. Sphericity of miscellaneous materials

Material	Sphericity	Material	Sphericity
Spheres, cubes, short cylinders ($L = D_p$)	1.0	Ottawa sand	0.95
Raschig rings ($L = D_p$)		Rounded sand	0.83
$L = D_o, D_i = 0.5D_o$	0.58	Coal dust	0.73
$L = D_o, D_i = 0.75D_o$	0.33	Flint sand	0.65
Berl saddles	0.3	Crushed glass	0.65
		Mica flakes	0.28

By convention, particle sizes are expressed in different units depending on the size range involved. Coarse particles are measured in inches or millimeters; fine particles in terms of screens size; very fine particles in micrometers or nanometers. Ultrafine particles are sometimes described in terms of their surface area per unit mass, usually in square meters per gram.

Sphericity of Some Regular Particle :

Particle Shape	Sphericity
Cylinder (L = D)	0.87
Cylinder (L = 2D)	0.82
Cylinder (L = 3D)	0.78
Cube	0.80
Cuboid (1 : 2 : 3)	0.725

1.3 Mixed and Average Size Analysis

In a sample of uniform particles of diameter D_p , the total volume of the particles is $\frac{m}{\rho_p}$, where m and ρ_p are the total mass of the sample and the density of the particles, respectively. Since the volume of one particle is v_p , the number of particles in the sample N is

$$N = \frac{m}{\rho_p v_p} \quad \dots(1.2)$$

The total surface area of the particles is, from Eqs. (1.1) and (1.2),

$$A = N s_p = \frac{6m}{\phi_s \rho_p D_p} \quad \dots(1.3)$$

To apply Eqs. (1.2) and (1.3) to mixtures of particles having various sizes and densities, the mixture is sorted into fractions, each of constant density and approximately constant size. Each fraction can then be weighed, or the individual particles in it can be counted or measured by any one of a number of methods. Equations (1.2) and (1.3) can then be applied to each fraction and the results added.

Information from such a particle-size analysis is tabulated to show the mass or number fraction in each size increment as a function of the average particle size (or size range) in the increment. An analysis tabulated in this way is called a **differential analysis**. The results are often presented as a histogram, as shown in fig. (a), with a continuous curve like the dashed line used to approximate the distribution. A second way to present the information is through a cumulative analysis obtained by adding, consecutively, the individual increments, starting with that containing the smallest particles, and tabulating or plotting the cumulative sums against the maximum particle diameter in the increment. Fig. (b) is a cumulative-analysis plot of the distribution shown in fig. (a). In a cumulative analysis the data may appropriately be represented by a continuous curve.

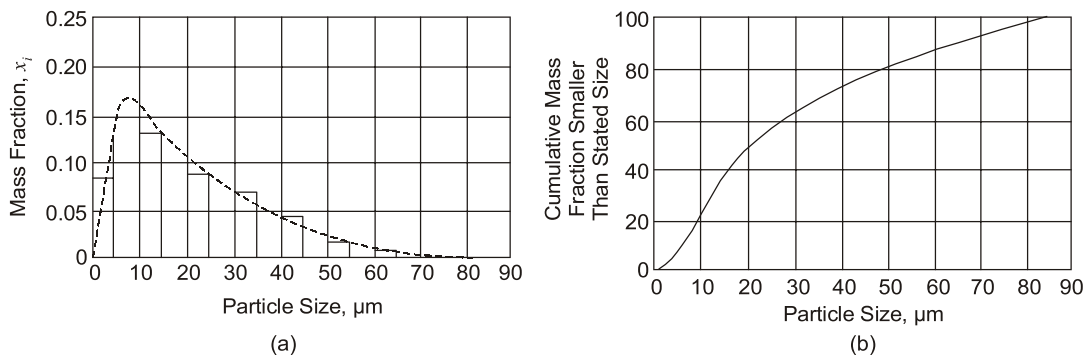


Fig. Particle-size distribution for powder: (a) differential analysis; (b) cumulative analysis

Calculations of average particle size, specific surface area, or particle population of a mixture may be based on either a differential or a cumulative analysis. In principle, methods based on the cumulative analysis are more precise than those based on the differential analysis, since when the cumulative analysis is used, the assumption that all particles in a single fraction are equal in size is not needed. The accuracy of particle-size measurements, however, is rarely great enough to warrant the use of the cumulative analysis, and calculations are nearly always based on the differential analysis.

Specific Surface of Mixture : If the particle density ρ_p and sphericity Φ_s are known, the surface area of the particles in each fraction may be calculated from Eq. (1.3) and the results for all fractions added to give A_w , the specific surface (the total surface area of a unit mass of particles). If ρ_p and Φ_s are constant, A_w is given by

$$\begin{aligned} A_w &= \frac{6x_1}{\Phi_s \rho_p \bar{D}_{p1}} + \frac{6x_2}{\Phi_s \rho_p \bar{D}_{p2}} + \dots + \frac{6x_n}{\Phi_s \rho_p \bar{D}_{pn}} \\ &= \frac{6}{\Phi_s \rho_p} \sum_{i=1}^n \frac{x_i}{\bar{D}_{pi}} \end{aligned} \quad \dots(1.4)$$

where

subscripts = individual increments

x_i = mass fraction in a given increment

n = number of increments

\bar{D}_{pi} = average particle diameter, taken as arithmetic average of smallest and largest particle diameter in increment

1.3.1 Average Particle Size

The average particle size for a mixture of particles is defined in several different ways. Probably the most used is the volume-surface mean diameter \bar{D}_s , which is related to the specific surface area A_w . It is defined by the equation

$$\bar{D}_s = \frac{6}{\Phi_s A_w \rho_p} \quad \dots(1.5)$$

Substitution from Eq. (1.4) in Eq. (1.5) gives

$$\bar{D}_s = \frac{1}{\sum_{i=1}^n \left(\frac{x_i}{\bar{D}_{pi}} \right)} \quad \dots(1.6)$$

Other averages are sometimes useful. The arithmetic mean diameter \bar{D}_N is

$$\bar{D}_N = \frac{\sum_{i=1}^n (N_i \bar{D}_{pi})}{\sum_{i=1}^n N_i} = \frac{\sum_{i=1}^n (N_i \bar{D}_{pi})}{N_T} \quad \dots(1.7)$$

where N_T is the number of particles in the entire sample.

The mass mean diameter \bar{D}_w is found from the equation

$$\bar{D}_w = \sum_{i=1}^n x_i \bar{D}_{pi} \quad \dots(1.8)$$

Dividing the total volume of the sample by the number of particles in the mixture (see below) gives the average volume of a particle. The diameter of such a particle is the volume mean diameter \bar{D}_v , which is found from the relation

$$\bar{D}_V = \left[\frac{1}{\sum_{i=1}^n \left(\frac{x_i}{\bar{D}_{pi}^3} \right)} \right]^{1/3}$$

For samples consisting of uniform particles these average diameters are, of course, all the same. For mixtures containing particles of various sizes, however, the several average diameters may differ widely from one another.

Number of Particles in Mixture. To calculate, from the differential analysis, the number of particles in a mixture, Eq. (1.2) is used to compute the number of particles in each fraction, and N_w , the total population in one mass unit of sample, is obtained by summation over all the fractions. For a given particle shape, the volume of any particle is proportional to its “diameter” cubed, or

$$v_p = aD_p^3 \quad \dots(1.9)$$

where a is the volume shape factor. From Eq. (1.2), then, assuming that a is independent of size,

$$N_w = \frac{1}{ap_p} \sum_{i=1}^n \frac{x_i}{\bar{D}_{pi}^3} = \frac{1}{ap_p \bar{D}_V^3} \quad \dots(1.10)$$

Screen Analysis; Standard Screen Series : Standard screens are used to measure the size (and size distribution) of particles in the size range between about 3 and 0.0015 in. (76 mm and 378 μ m). Testing sieves are made of woven wire screens, the mesh and dimensions of which are carefully standardized. The openings are square. Each screen is identified in meshes per inch. The actual openings are smaller than those corresponding to the mesh numbers, however, because of the thickness of the wires. This set of screens is based on the opening of the 200-mesh screen, which is established at 0.074 mm. The area of the openings in any one screen in the series is exactly twice that of the openings in the next smaller screen. The ratio of the actual mesh dimension of any screen to that of the next smaller screen is, then, $\sqrt{2} = 1.41$. For closer sizing, intermediate screens are available, each of which has a mesh dimension $\sqrt[4]{2}$ or 1.189, times that of the next smaller standard screen.

In making an analysis a set of standard screens is arranged serially in a stack, with the smallest mesh at the bottom and the largest at the top. The sample is placed on the top screen and the stack shaken mechanically for a definite time, perhaps 20 min. The particles retained on each screen are removed and weighed, and the masses of the individual screen increments are converted to mass fractions or mass percentages of the total sample. Any particles that pass the finest screen are caught in a pan at the bottom of the stack.

Since the particles on any one screen are passed by the screen immediately ahead of it, two numbers are needed to specify the size range of an increment, one for the screen through which the fraction passes and the other on which it is retained. Thus, the notation 14/20 means “through 14 mesh and on 20 mesh.”

Average particle size for a mixture of particles is defined in several different ways :

(i) **Volume Surface Mean Diameter (\bar{D}_s) :**

$$(\bar{D}_s) = \frac{6}{\phi_s \rho_p A_w} = \frac{1}{\sum_{i=1}^n \left(\frac{x_i}{\bar{D}_{pi}} \right)}$$

It is defined as the diameter of sphere that has same volume/surface area ratio as a particle of interest.

(ii) Mass Mean Diameter (\bar{D}_w) :

$$\bar{D}_w = \sum_{i=1}^n x_i \bar{D}_{P_i}$$

(iii) Average Volume of a Particle :

$$= \frac{\text{Total volume of the sample}}{\text{No. of particles in the mixture}}$$

(iv) Volume Mean Diameter :

$$\bar{D}_v = \left[\frac{1}{\sum_{i=1}^n \left(\frac{x_i}{\bar{D}_{P_i}^3} \right)} \right]^{1/3}$$

(v) Arithmetic Mean Diameter (\bar{D}_N) :

$$\bar{D}_N = \frac{\sum_{i=1}^n N_i D_{P_i}}{N_T}$$

where, N_T is the number of particles in entire sample.

(vi) Number of Particle in the Mixture :

$$N_w = \frac{1}{a\rho_p} \sum_{i=1}^n \frac{x_i}{D_{P_i}^3} = \frac{1}{a\rho_p \bar{D}_v^3}$$

where,

a = Volume shape factor.

N_w is the total population in one unit mass of sample, obtained by summation over all fractions.

Also,

$$V_p = aD_p^3$$

(vii) Sauter Mean Diameter (S.M.D.) :

- It is a common measure in fluid dynamic as a way to estimate the average particle size.
- It is defined as the diameter of a sphere that has the same volume/surface area ratio as the particle of interest.
- Sauter mean diameter is typically defined in terms of

Surface dia, $d_s = \sqrt{\frac{A_p}{\pi}}$, and

Volume diameter, $d_v = \left(\frac{6V_p}{\pi} \right)^{1/3}$

where, A_p and V_p are the surface area and volume of particle.

- S.M.D. for a given particle is

$$\text{S.D.} = D[3, 2] = d_{32} = \frac{d_v^3}{d_s^2}$$

If actual surface area A_p and volume V_p of the particle are known then equation simplifies as :

$$\frac{V_p}{A_p} = \frac{\frac{4}{3}\pi\left(\frac{d_{32}}{2}\right)^3}{4\pi\left(\frac{d_{32}}{2}\right)^2} = \frac{\left(\frac{d_{32}}{2}\right)^3}{3\left(\frac{d_{32}}{2}\right)^2} = \frac{d_{32}}{6}$$

$$d_{32} = 6\frac{V_p}{A_p}$$


- S.M.D. is especially important in calculation where the active surface area is important. Such area included catalysis and application in fuel combustion.

1.4 Screening

Screening is a method of separating particle according to size alone. Material passed through a series of screen of different size is separated into sized fraction. Fraction in which both maximum and minimum particle size are known. Material that remains on a given screening surface is the oversize material that passing through the screening surface is the undersize material. Industrial screens are made from woven wire, silk cloth, metal bars. Perforated or slatted metal plates etc. Separation in the size range between 4 mesh and 48 mesh is called fine screening and for sizes smaller than 48 mesh is called ultra fine.

Terms related to Screening

- **Limiting Screen** : The screen through which particles have passed.
- **Retaining Screen** : The screen which has retained the particles.

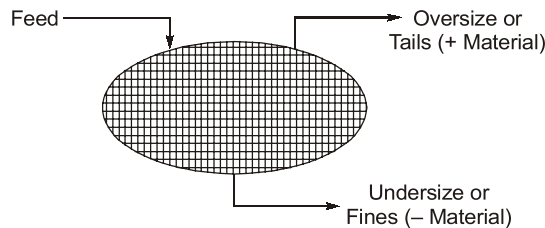

- **Starification** : Some kind of motion is given to the screen so that large particles rise to the top and smaller particles shift through the voids. This is done to prevent the blinding of screen openings.
- **Separation Probability** : Probability by which particles are rejected by screen or they pass through the screen. Smaller difference between the particle size and screen size cause problem. Let, w be the screen opening d_p be the diameter of particle.
- **Critical Class** : When $0.5w < d_p < 1.5w$



- When $d_p > 1.5w$ (oversize easily)
When $d_p < 0.5w$ (undersize easily)

- **Aperture size (w)** : The minimum clear space between the edges of opening in a screening surface. Aperture size is in inch, cm or mm.
- **Mesh number (m)** : It is the number of apertures (opening) in one linear inch. e.g. 30 mesh screen means 1 inch consist of 30 openings.
Note : As the mesh number increases, the size of opening decreases.
- Relation between aperture (w), mesh number (m) and diameter of wire (d) : $w = \frac{1}{m} - d$
- A particle passing through 'a' mesh screen and retained on 'b' mesh screen is expressed as a/b or $(-a + b)$ fraction.
- **Ideal screen** : An ideal screen separate the feed mixture in such a way that smallest particle in overflow would be just larger than largest particle in overflow.
- **Cut diameter (D_c)** : Size of screen opening.
- In actual screening, overflow is found to contain some particles smaller than cut diameter and underflow is found to contain some particles larger than cut diameter, giving rise to overlap of the two.
- Screening can be done dry as well as wet. Wet screening is done occasionally (by adding water) to remove undesirable materials e.g. extremely fine particles.

1.4.1 Major Screening Equipment

Grizzly Screens : A grizzly screen consists of a set of parallel bars held apart by spaces at some predetermined opening. Bars are frequently made of manganese steel to reduce wear. A grizzly is widely used before a primary crusher in rock or ore crushing plant to remove the fines before ore or rock enters the crusher.

The stationary grizzly is the simplest of all separating devices and the least expensive to install and maintain. It is normally limited to the rough screening of dry material at 2" and courses. The slope or angle with the horizontal will vary between 20-50°. Stationary grizzlies require no power and little maintenance. It is difficult to change the opening between the bars and the separation may not be sufficiently complete. Flat grizzlies in which the parallel bars are in a horizontal plane are used on tops of ore and coal bins and under unloading trestles. A flat grizzly is used to retain too large pieces which are then broken up or removed manually.

Gyratory Screen : Gyratory screens are box like machine which contain several decks of screens are above the other, held in box or casing. The coarsest screen is at the top and the finest at the bottom. The mixture of particle is dropped on the top screens and casing are gyrated to shift the particle through screen openings. Often the screening surface is doubled between the two screens are rubber balls held in separate compartment. As the screen operates, the balls strike the screen surface and free the opening of screen surface.

Screen size : 1^{1/2} × 4 to 5 × 14 ft²
Gyration rate : 600-1800 r/min
Motor size : 1-3 HP

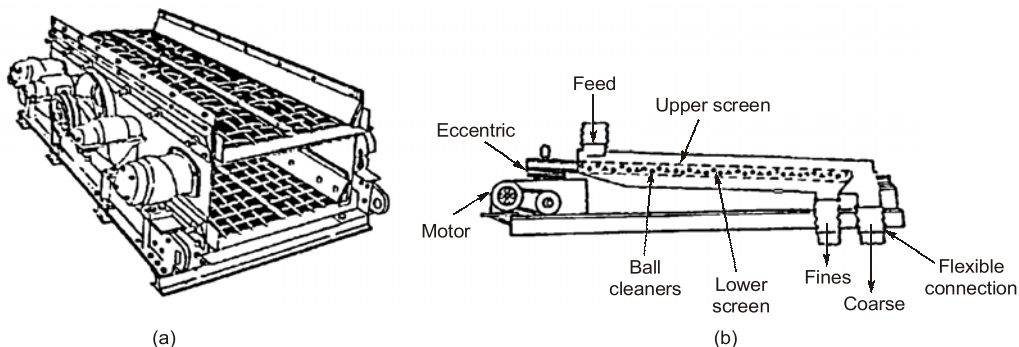


Fig. (a) Heavy-duty vertically gyrated screen; (b) Horizontally gyrated screen

Vibrating Screens : Vibrating screens are used for standard size particle whose large capacity and high efficiency are desired. The capacity in the finer size is so much greater than any of other screens that they have practical replaced all other types where the screen efficiency is important.

Advantage :

- (i) Accuracy of sizing
- (ii) Increased capacity per unit area
- (iii) Low maintenance cost
- (iv) Saving in installation space and weight

Table : Comparison of screening equipment

	Size of articles separated	Capacity	Efficiency
Grizzlies	20 mm and above	Very high	Low
Trommels	13 mm and above	Low	Low
Vibrating screens	Coarse, medium and fine particles	High	High
Gyratory screens	Finer particles	Low	Very high

1.4.2 Objective of Screening

1. To scalp out oversize material.
2. To remove fines or degradation from a finished product.
3. To produce a commercial or process grade product to meet specific particle size limits.
4. To remove fines from material before entering to reduction equipment such as a crushers, ball mills or rod mills.

1.4.3 Material Balance Over Screen

Let

F = Mass flow rate of feed

D = Mass flow rate of over flow

B = Mass flow rate of under flow

x_F = Mass fraction of material A in feed,

$1 - x_F$ = Mass fraction of material B in feed

x_D = Mass fraction of material A in over flow

$1 - x_D$ = Mass fraction of material B in over flow

x_B = Mass fraction of material A in under flow

$1 - x_B$ = Mass fraction of material B in under flow

Total material fed to screen will leave it either as under flow or as over flow.

$$F = B + D \quad \dots(i)$$

The material A in the feed will also leave in these two stream :

$$Fx_F = Dx_D + Bx_B \quad \dots(ii)$$

Eliminating B from equation (i) and (ii) gives

$$\frac{D}{F} = \frac{x_F - x_B}{x_D - x_B} \quad \dots(iii)$$

and eliminating of D gives

$$\frac{B}{F} = \frac{x_D - x_F}{x_D - x_B} \quad \dots(iv)$$

1.4.4 Screen Effectiveness

1. Screen efficiency is a measure of the success of a screen in closely separating two materials *A* and *B*. If the screen functioned perfectly, all of material *A* would be in the overflow and the all of material *B* would be in the under flow.
2. Screen efficiency based on over size + (Rejection)

$$E_A = \frac{\text{Oversize material in the overflow}}{\text{Amount of oversize material entering with feed}}$$

$$= \frac{Dx_D}{Fx_F}$$

3. Screen efficiency based on the undersize – (Recovery)

$$E_B = \frac{B(1-x_B)}{F(1-x_F)}$$

4. Combined overall efficiency

$$E = E_A E_B = \frac{D \cdot B \cdot x_D (1 - x_B)}{F^2 \cdot x_F (1 - x_F)}$$

$$E = \frac{(x_F - x_B) \cdot (x_D - x_F) \cdot x_D (1 - x_B)}{(x_D - x_B)^2 \cdot (1 - x_F) \cdot x_F}$$

1.4.5 Capacity of Screen

- It is the mass of material that can be fed per unit time, per unit area of the screen (tons/ft² h)
- Capacity $\propto D_C$ (cut diameter / Mesh opening of screen)
- For mm mesh size screen,
Capacity range = (0.2 – 0.8) tons/ft²h
- Capacity and effectiveness are 2 opposing factors, i.e., when capacity increase, effectiveness decreases. This is because as capacity increase, screen becomes overloaded, number of contacts and chance of passage of undersize particle is low, so effectiveness decrease.

Example 1.1

Consider a spherical particle and a short cubical, which particle will have more surface area if their volumes are same:

- | | |
|---------------------------------------|------------------------|
| (a) Short cubical particle | (b) Spherical particle |
| (c) Both will have equal surface area | (d) None of the above |

Solution: (a)

Example 1.2

Consider a spherical particle and a hemispherical particle, which particle will have more surface surface area if their volumes are same:

- | | |
|----------------------------------|------------------------|
| (a) Hemispherical particle | (b) Spherical particle |
| (c) Both will have equal surface | (d) None of the above |

Solution: (b)

Example 1.3

What are the units for sphericity in SI units?

- (a) m (b) m² (c) m³ (d) Dimensionless

Solution: (d)

Example 1.4

What is the sphericity of a rectangular prism of size $a \times 2a \times 3a$?

- (a) 0.791 (b) 0.767 (c) 0.761 (d) 0.725

Solution: (d)

Example 1.5

Calculate the mean diameter for material of the following size distribution:

Weight % Material	With diameter smaller than d_p (μm)
0	10
3	20
8	30
16	40
90	80
97	100
100	150

Solution:

Diameter range (μm)	\bar{d}_{P_i} (μm)	Weight fraction in interval, x_i	$\frac{x_i}{d_{P_i}}$
10 – 20	15	$\frac{(3 - 0)}{100} = 0.03$	$\frac{0.03}{15} = 0.002$
20 – 30	25	$\frac{(8 - 3)}{100} = 0.05$	$\frac{0.05}{25} = 0.002$
30 – 40	35	$\frac{(16 - 8)}{100} = 0.08$	$\frac{0.08}{25} = 0.0023$
40 – 80	60	$\frac{(90 - 16)}{100} = 0.74$	$\frac{0.74}{60} = 0.0123$
80 – 100	90	$\frac{(97 - 90)}{100} = 0.07$	$\frac{0.07}{90} = 0.00048$
100 – 150	125	$\frac{(100 - 97)}{100} = 0.03$	$\frac{0.03}{125} = 0.00024$
			$\sum \frac{x_i}{d_{P_i}} = 0.01962$

$$\text{Mean diameter, } \bar{D}_s = \frac{1}{\sum \frac{x_i}{d_{P_i}}} = \frac{1}{0.01962} = 50.9682 \mu\text{m (on } 0.00509 \text{ cm)}$$

Example 1.6

Calculate the surface volume mean diameter for the following particulate material:

Size Range, μm	Most of the particle in range (gm)
-704 + 352	25
-352 + 176	37.5
-176 + 88	62.5
-88 + 44	75
Pan	50

Solution:

Size range (μm)	Average diameter \bar{D}_{P_i} , μm	Mass (gm)	Mass Fraction x_i	$\frac{x_i}{\bar{D}_{P_i}}$
704 + 352	528	25	0.10	1.8939×10^{-4}
352 + 176	264	37.5	0.15	5.6818×10^{-4}
176 + 88	132	62.5	0.25	18.939×10^{-4}
88 + 44	66	75	0.30	45.4545×10^{-4}
44	44	50	0.20	45.4545×10^{-4}
			$\Sigma m = 250 \text{ gm}$	$\Sigma \frac{x_i}{\bar{D}_{P_i}} = 117.4237 \times 10^{-4}$

$$\text{Surface volume mean diameter, } D_s = \frac{1}{\sum \frac{x_i}{D_{P_i}}} = \frac{1}{117.4237 \times 10^{-4}} = 85.16 \mu m$$

Example 1.7

Which of the following shapes has highest shape factor?

- (a) Cylinder (b) Hemisphere (c) Cube (d) Sphere

Solution: (c)

Example 1.8

Arrange the following particle shapes in order of increasing sphericity: Cube, Sphere, Cylinder, and Hemisphere.

- (a) Cylinder, Cube, Hemisphere, Sphere (b) Hemisphere, Cube, Cylinder, Sphere
(c) Cube, Cylinder, Hemisphere, Sphere (d) Cube, Hemisphere, Cylinder, Sphere

Solution: (d)

Example 1.9

Which of the following shapes has the highest shape factor

- (a) Cylinder (b) Cube (c) Hemisphere (d) Sphere

Solution: (b)





Student's Assignments

- Q.1** What is the sphericity of a cuboid whose length, breadth and depth are in the ratio 5 : 4 : 1 ?
(a) 0.726 (b) 0.614
(c) 0.81 (d) 0.563
- Q.2** Find the shape factor of a cylindrical particle of 3 mm diameter and 3 mm length?
(a) 0.873 (b) 1.145
(c) 1 (d) 1.375
- Q.3** What is the sphericity of a cylindrical particle whose length is equal to its diameter?
(a) 0.873 (b) 0.673
(c) 0.573 (d) 0.81
- Q.4** For a cylindrical particle of height equal to twice the diameter, the sphericity value is
(a) 0.655 (b) 0.728
(c) 0.832 (d) 0.915
- Q.5** The shape factor for a hemisphere is
(a) equal to 1 (b) greater than 1
(c) less than 1 (d) None of the above
- Q.6** Find the sphericity of a cube of dimension $a \times a \times a$.
- Q.7** Finely divided clay is used as a catalyst in the petroleum industry. It has a density of 1.2 g/cc and a sphericity of 0.5. The size analysis is as follows :

Average diameter, $D_{pr,avg}(cm)$	0.0252	0.0178	0.0126	0.0089	0.0038
Mass fraction, $x_i (g/g)$	0.088	0.178	0.293	0.194	0.247

Find the specific surface area and the Sauter mean diameter of the clay material.

- Q.8** Calculate the volume-surface mean diameter for the following particulate material.

Size range, μm	Mass of particles in the range, g
-710 + 300	30
-300 + 180	35
-180 + 90	65
-90 + 38	70
Pan	55

- Q.9** Which of the following particle has the lowest value of sphericity?
(a) Rounded sand
(b) Pulverized coat
(c) Tungsten powder
(d) Mica flakes
- Q.10** The following table gives the size distribution of a dust measured by micro scope. Convert these figures to obtain distribution on mass basis and calculate the specific surface in μm . Assuming spherical particle of specific gravity 2.65.

Size range (mm)	Number of Particles
0 - 2	2000
2 - 4	600
4 - 8	140
8 - 12	40
12 - 16	15
16 - 20	5
20 - 24	2

- Q.11** The cumulative mass fraction of particles smaller than size d_j for a collection of N_i particles of diameter d_i and mass m_i ($i = 1, 2, 3, \dots, \infty$) is given by

$$(a) \frac{\sum_{i=1}^j N_i d_i^3}{\sum_{i=1}^{\infty} N_i d_i^3} \quad (b) \frac{\sum_{i=1}^j N_i m_i d_i^3}{\sum_{i=1}^{\infty} N_i m_i d_i^3}$$

$$(c) \frac{\sum_{i=1}^j N_i m_i d_i^2}{\sum_{i=1}^{\infty} N_i m_i d_i^2} \quad (d) \frac{\sum_{i=1}^j N_i m_i d_i}{\sum_{i=1}^{\infty} N_i m_i d_i}$$

Q.12 Weight mean diameter is given by :

$$(a) \frac{\sum n_i d_i^4}{\sum n_i d_i^3} \quad (b) \left(\frac{\sum n_i d_i^3}{\sum n_i} \right)^{1/3}$$

$$(c) \frac{\sum n_i d_i^3}{\sum n_i d_i^2} \quad (d) \frac{\sum n_i d_i^2}{\sum n_i d_i}$$

ANSWERS

1. (b) 2. (b) 3. (a) 4. (c)
5. (b) 6. (0.81) 7. (1235.43, 8.094 × 10⁻³)
8. (79.11) 9. (d) 10. (0.726 × 10⁶)
11. (b) 12. (c)

Explanation

1. (b)

The volume of cuboid is $5 \times 4 \times 1 = 20 \text{ m}^3$
and surface area of this cuboid
 $= 2[(5 \times 4) + (4 \times 1) + (5 \times 1)]$
 $= 2(20 + 4 + 5)$
 $= 2 \times 29 = 58 \text{ m}^2$

Let D_p = Diameter of the equivalent sphere

$$\text{Then, } \frac{\pi}{6} D_p^3 = 20$$

$$D_p = 3.36 \text{ m}$$

$$\text{Area of sphere} = \pi D_p^2 = 35.63 \text{ m}^2$$

$$\text{Thus, Sphericity} = \frac{35.63}{58} = 0.614$$

2. (b)

For a non-spherical particle, the sphericity (ϕ)

$$= \frac{6}{D_p} \left(\frac{V_p}{S_p} \right)_{\text{Particle}}$$

$$\text{Vol. of sphere} = \frac{\pi}{6} D_p^3$$

$$\text{Volume of cylindrical particle} = \frac{\pi}{4} D^2 \times l$$

where $l = D$

$$\frac{\pi}{4} D_p^3 = \frac{\pi}{4} D^3$$

$$D_p = \left(\frac{6}{4} \right)^{1/3} D$$

$$\left(\frac{V_p}{S_p} \right)_{\text{Particle}} = \frac{\frac{\pi}{4} D^3}{\frac{\pi}{2} D^2 + \pi D^2} = \frac{D}{6}$$

$$\phi = \frac{6}{D_p} \times \frac{D}{6} = \left(\frac{4}{6} \right)^{1/3}$$

$$\phi = 0.873$$

$$\text{Shape factor, } \phi' = \frac{1}{\phi} = \frac{1}{0.873} = 1.145$$

3. (a)

For a non-spherical particle, the sphericity (ϕ)

$$= \frac{6}{D_p} \left(\frac{V_p}{S_p} \right)_{\text{Particle}}$$

$$\text{Vol. of sphere} = \frac{\pi}{6} D_p^3$$

$$\text{Volume of cylindrical particle} = \frac{\pi}{4} D^2 \times l$$

where $l = D$

$$\frac{\pi}{6} D_p^3 = \frac{\pi}{4} D^3$$

$$D_p = \left(\frac{6}{4} \right)^{1/3} D$$

$$\left(\frac{V_p}{S_p} \right)_{\text{Particle}} = \frac{\frac{\pi}{4} D^3}{\frac{\pi}{2} D^2 + \pi D^2} = \frac{D}{6}$$

$$\phi = \frac{6}{D_p} \times \frac{D}{6} = \left(\frac{4}{6} \right)^{1/3}$$

$$\phi = 0.873$$

4. (c)

$$\text{Sphericity } \phi = \frac{6}{D_p} \left(\frac{V_p}{S_p} \right)_{\text{particle}}$$

Volume of sphere = Volume of cylindrical particle

$$\frac{\pi}{6} D_p^3 = \frac{\pi}{4} D^2 \times l$$

where $l = 2D$

$$\frac{\pi}{6} D_p^3 = \frac{\pi}{4} \times 2D^3$$

$$D_p = (3)^{1/3}D$$

$$\left(\frac{V_p}{S_p}\right)_{\text{particle}} = \frac{D}{5}$$

$$\phi = \frac{6}{D_p} \times \frac{D}{5} = 0.832$$

5. (b)

$$\text{Shape factor} \propto \frac{1}{\text{Sphericity}}$$

6. (0.81)

We have the sphericity of a cube as

$$\Phi_{\text{cube}} = \frac{6}{D_p} \left(\frac{V_p}{S_p}\right)_{\text{cube}}$$

Here, for this cube, $V_p = a^3$ and $S_p = 6a^2$.
To find D_p , we have to equate the sphere volume with the cube volume.

$$\text{Thus, } \frac{\pi}{6} D_p^3 = a^3 \Rightarrow D_p = a \times \sqrt[3]{\frac{6}{\pi}}$$

$$\text{Thus, } \Phi_{\text{cube}} = \frac{6}{a \times \sqrt[3]{\frac{6}{\pi}}} \left(\frac{a^3}{6a^2}\right) = \sqrt[3]{\frac{\pi}{6}} = 0.81$$

7. (1235.43, 8.094×10^{-3})

The specific surface area and the Sauter mean diameters are given by the relations

$$A_{ss} = \frac{6}{\Phi \rho_p} \sum_{i=1}^{i=n} \frac{x_i}{D_{pi,avg}}$$

$$\text{and } \bar{D}_{Vs} = \frac{1}{\sum_{i=1}^{i=n} \frac{x_i}{D_{pi,avg}}}$$

For finding these, we have to proceed as follows :

Average diameter $D_{pi,avg}$ (cm)	Mass fraction x_i (gg)	$\frac{x_i}{D_{pi,avg}}$
0.0252	0.088	3.492
0.0178	0.178	10.000
0.0126	0.293	23.254
0.0089	0.194	21.797
0.0038	0.247	65.000
	$\sum x_i = 1.000$	$\sum \frac{x_i}{D_{pi,avg}} = 123.543$

Thus, the specific surface area,

$$A_{ss} = \frac{6}{\Phi \rho_p} \sum_{i=1}^{i=n} \frac{x_i}{D_{pi,avg}}$$

$$= \frac{6(123.543)}{0.5 \times 1.2} = 1235.43 \text{ cm}^2/\text{g}$$

and the Sauter mean diameter,

$$\bar{D}_{Vs} = \frac{1}{\sum_{i=1}^{i=n} \frac{x_i}{D_{pi,avg}}} = \frac{1}{123.543}$$

$$= 0.008094 \text{ cm} = 8.094 \times 10^{-3} \text{ cm}$$

8. (79.11)

The volume-surface mean diameter is given by the relation

$$\bar{D}_{Vs} = \frac{1}{\sum_{i=1}^{i=n} \frac{x_i}{D_{pi,avg}}}$$

For finding this, we have to proceed as follows :

Size Range (μm)	$D_{pi,avg}$	Mass (g)	Mass Fraction, x_i	$\frac{x_i}{D_{pi,avg}}$
-710+300	505	30	0.117	0.00023
-300+180	240	35	0.137	0.00057
-180+90	135	65	0.255	0.00189
-90+38	64	70	0.275	0.00429
Pan	38	55	0.215	0.00566
				$\sum \frac{x_i}{D_{pi,avg}} = 0.01264$

$$\text{Thus, } \bar{D}_{Vs} = \frac{1}{0.01264} = 79.11 \mu\text{m}$$

The negative (-) sign indicates that the material passes through the screen and the positive (+) sign indicates that the material is retained on the screen.

10. (0.726×10^6)

Size Range (μm)	Average \bar{D}_p (μm) (Calculated)	No. of Particle	Mass $m(g) = \rho_p V n$ $= \rho_p \frac{\pi}{6} \bar{D}_p^3 n_i$	Mass Fraction x_i	$\frac{x_i}{\bar{D}_p} \times 10^6$
0-2	1	2000	2.7×10^{-12}	0.011	0.011
2-4	3	600	22.5×10^{-12}	0.090	0.030
4-8	6	140	41.93×10^{-12}	0.168	0.028
8-12	10	40	55.47×10^{-12}	0.222	0.022
12-16	14	15	55.08×10^{-12}	0.229	0.016
16-20	18	5	40.44×10^{-12}	0.162	0.009
20-24	22	2	29.53×10^{-12}	0.118	0.005
			$\Sigma m = 249.72 \times 10^{-12}$	$\Sigma x_i = 1$	$\Sigma \frac{x_i}{\bar{D}_p} = 0.121 \times 10^6$

Volume surface mean diameter,

$$\bar{D}_s = \frac{1}{\sum \frac{x_i}{D_i}}$$

$$= \frac{1}{0.121 \times 10^6} = 8.264 \times 10^{-6}$$

Surface Area \Rightarrow

$$S_p = \pi \bar{D}_s^2 = \pi (8.264 \times 10^{-6})^2$$

$$= 214.44 \times 10^{-12}$$

Volume, $V_p = \frac{\pi}{6} \bar{D}_s^3 = 295.36 \times 10^{-18} \text{ m}^3$

Specific surface,

$$\frac{S_p}{V_p} = \frac{214.44 \times 10^{-12}}{295.36 \times 10^{-18}}$$

$$= 0.726 \times 10^6 \text{ m}$$

11. (b)

Cumulative mass fraction of particle = Fraction of total weight of particle having a size smaller than a given screen opening.

Hence, required cumulative mass fraction is given

$$\text{by } \Rightarrow \frac{\sum_{i=1}^j N_i m_i d_i^3}{\sum_{i=1}^{\infty} N_i m_i d_i^3}$$

12. (c)

Weight mean diameter

$$\bar{D}_w = \frac{\sum x_i \bar{D}_p^3}{\sum x_i}$$

where $x_i \propto n_i \bar{D}_p^3$

$$\bar{D}_w = \frac{\sum n_i \bar{D}_p^3}{\sum n_i \bar{D}_p^2} = \frac{\sum n_i d_i^3}{\sum n_i d_i^2}$$

■■■■