

Computational modeling of the mechanics of hierarchical materials

Stefano Signetti, Federico Bosia, and Nicola M. Pugno

Structural hierarchy coupled with material heterogeneity is often identified in natural materials, from the nano- to the macroscale. It combines disparate mechanical properties, such as strength and toughness, and multifunctionality, such as smart adhesion, water repellence, self-cleaning, and self-healing. Hierarchical architectures can be employed in synthetic bioinspired structured materials, also adopting constituents with superior mechanical properties, such as carbon nanotubes or graphene. Advanced computational modeling is essential to understand the complex mechanisms that couple material, structural, and topological hierarchy, merging phenomena of different nature, size, and time scales. Numerical modeling also allows extensive parametric studies for the optimization of material properties and arrangement, avoiding time-consuming and complex experimental trials, and providing guidance in the fabrication of novel advanced materials. Here, we review some of the most promising approaches, with a focus on the methods developed by our group.

Introduction

For centuries, nature has provided inspiration for man in the design and manufacture of structural materials. Many natural materials display fascinating physical and mechanical properties that, until recently, have been hard to replicate in artificial materials and structures. These include high stiffness and low density,¹ strong adhesion and easy detachment,² self-sharpening,³ self-healing, growth, and adaptive tissue organization, water-repellence, self-cleaning, and superhydrophobic or superhydrophilic behaviors.^{4,5} All of these properties are usually related to complex multiscale structural arrangements of different constituents, from the nano- to the macroscale, involving material mixing and grading, interaction between constituents, and, most importantly, hierarchy, intended as the property whereby a material exhibits structure on more than one length scale.^{6–8}

In the study of bioinspired materials, the focus is on the link between material properties and the emergence of specific functions across all relevant scales. The main lesson from nature is that complex behavior and functionality derives from structure, hierarchy, and optimal organization of simple basic components. This is in stark contrast to many engineered materials that exploit the properties of exotic metals or polymers, with associated high production and environmental costs. Nature has successfully done more with less, in terms

of material design and production. This paradigm could, in principle, also apply to synthetic materials, and can be transposed to many fields in engineering, with the potential to do even better than nature, in the absence of limiting biological constraints.

Experimental tests and measurements on hierarchical materials can be difficult to rationalize due to high uncertainties and statistical dispersion at the nanoscale, difficulties in sample manipulation and characterization, problematic reproducibility of boundary conditions and, in some cases, the impossibility of direct experimental verification at all the different size scales. Thus, due to the complexity and cross-scale interaction of the physical phenomena involved, further progress requires comprehensive numerical modeling. The challenge is to integrate multiple length scales and physical phenomena within the same simulation framework, since in hierarchical structures, a piecewise understanding of individual parts cannot simply be assembled or superimposed: the whole is greater than the sum of the individual parts.^{9,10}

Numerical modeling of biological and bioinspired material properties

Computational methods to model the mechanics of hierarchical materials need to span the various size and time scales of the problems involved. These can be divided schematically

Stefano Signetti, Laboratory of Bio-Inspired & Graphene Nanomechanics, Department of Civil, Environmental and Mechanical Engineering, University of Trento, Italy; stefano.signetti@unitn.it
 Federico Bosia, Department of Physics and Nanostructured Interfaces and Surfaces Interdepartmental Centre, University of Turin, Italy; fbosia@unito.it
 Nicola M. Pugno, Laboratory of Bio-Inspired & Graphene Nanomechanics, Department of Civil, Environmental and Mechanical Engineering, University of Trento, and Center for Materials and Microsystems, Fondazione Bruno Kessler, Italy; and School of Engineering and Materials Science, Queen Mary University of London, UK; nicola.pugno@unitn.it
 doi:10.1557/mrs.2016.185

into three broad categories: (1) nanoscale—methods like density functional theory or molecular dynamics (MD) to achieve characterization of the basic constituents of hierarchical composites; (2) micro-/mesoscale—fiber bundle model (FBM), lattice spring model (LSM), discrete and meshless methods to reconstruct the role of hierarchy and material mixing in characteristic mechanical properties of composites; and (3) macroscale—finite element methods (FEMs) and discrete or boundary element methods to model complex mechanical problems at the continuum level for solids, and particle methods for fluid mechanics, based on Navier-Stokes or Boltzmann equations. **Figure 1** depicts the overall scenario of these multiscale analysis techniques.

Computational methods can provide new insights for understanding fracture mechanisms in heterogeneous/hierarchical/multiscale structures, starting from the nanoscale. Various multiscale models have been developed to capture the mechanisms involved in the optimization of global material mechanical properties.^{11–13} One example is represented by the FBMs,¹⁴ which are particularly appropriate for the simulation of fibrous materials, often occurring in biomaterials. Here, material structure at a certain size scale is modeled as a network of fibers arranged in parallel and in series subjected to uniaxial tension, with statistically Weibull-distributed yield and fracture strengths or strains. Usually, an equal-load-sharing hypothesis is adopted,¹⁴ whereby when fibers fracture, stresses are redistributed uniformly among the remaining fibers in the bundle. Multiphase media are modeled by assigning different mechanical properties to the fibers of each bundle.

We introduced a hierarchical extension of this approach (i.e., the hierarchical fiber bundle model [HFBM]), whereby

the input mechanical behavior of a subvolume or “fiber” at a given hierarchical level is statistically inferred from the average output deriving from repeated simulations at the lower level, down to the lowest hierarchical level¹⁵ (**Figure 2a**). Results from this and other implementations of HFBM show that specific hierarchical organizations can lead to increased damage resistance (e.g., self-similar fiber-reinforced matrix materials)¹⁶ or that the interaction between hierarchy and material heterogeneity is critical, since homogeneous hierarchical bundles do not display improved properties.¹⁷ The effect of defects at the nanoscale can also be accounted for, and the HFBM has been used to estimate the strength and stiffness of macrostructures such as the futuristic nanotube-based space elevator cable, highlighting the defect-related decrease in performance with respect to estimations based on ideal defect-free materials.¹⁸

Similar approaches, appropriate for two-dimensional (2D) or three-dimensional (3D) simulations, are based on LSMs¹⁹ or random fuse models,²⁰ which provide a discrete description of continuous media through a network of discrete elements (springs or “resistors”). These have been used to simulate plasticity, damage propagation, and statistical distributions of “avalanches” of fracture events in heterogeneous materials.²⁰ Similar to the procedure adopted for HFBM, we recently introduced the hierarchical lattice spring model (HLSM), extending the classical LSM²¹ (**Figure 2b**). Other analytical theories such as our quantized fracture mechanics²² (QFM) or atomistic methods such as MD can be integrated in these multiscale approaches, for instance, to determine constitutive laws at the lower scale as a function of atomic structure, defect content, or molecular organization.

Other computational approaches that can also be used to model fracture propagation in a multilevel scheme include 3D mesh-free models, useful for simulating complex 3D heterogeneous media with nonlocal effects.^{23,24} These methods have also been implemented in a multiscale scheme.²⁵ Standard FEM approaches based on erosion algorithms are pushed to their limits when dealing with fracture nucleation and propagation. Therefore, various alternative strategies have been adopted, such as adaptive refinement of the mesh along the model solving the use of cohesive zone model (CZM)-based elements, or extended FEM (X-FEM).²⁶ Peridynamics is a meshless method whose nonlocal response represents an ideal bridge between atomistic (MD) and continuum methods.²⁷ This novel approach is based on a nonlocal and integral reformulation of the standard continuum theory of solid mechanics, which is applicable even when cracks and other singularities appear in the deformation field. Since peridynamics models


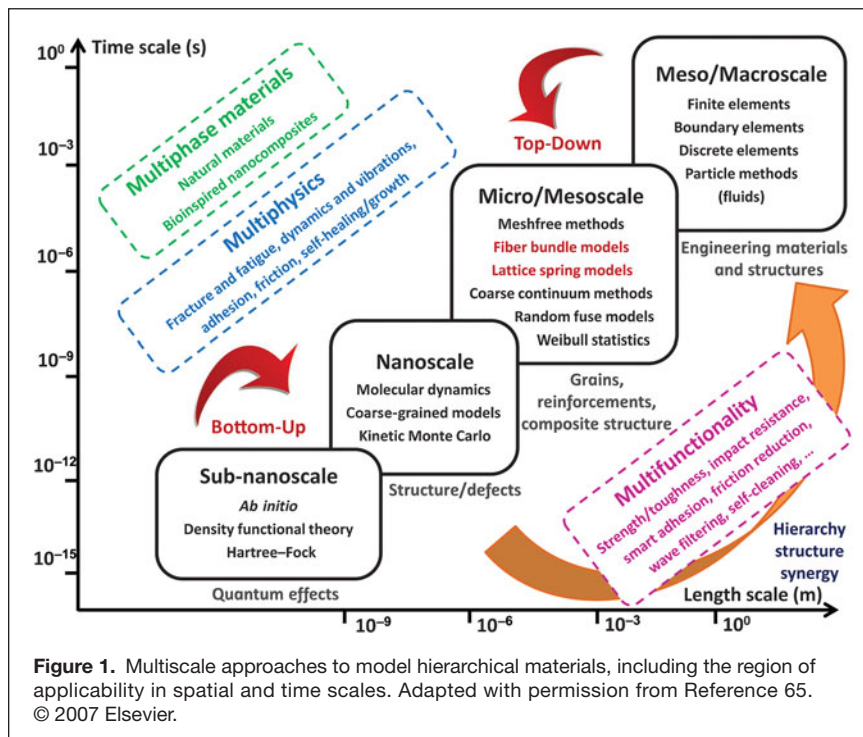


Figure 1. Multiscale approaches to model hierarchical materials, including the region of applicability in spatial and time scales. Adapted with permission from Reference 65. © 2007 Elsevier.

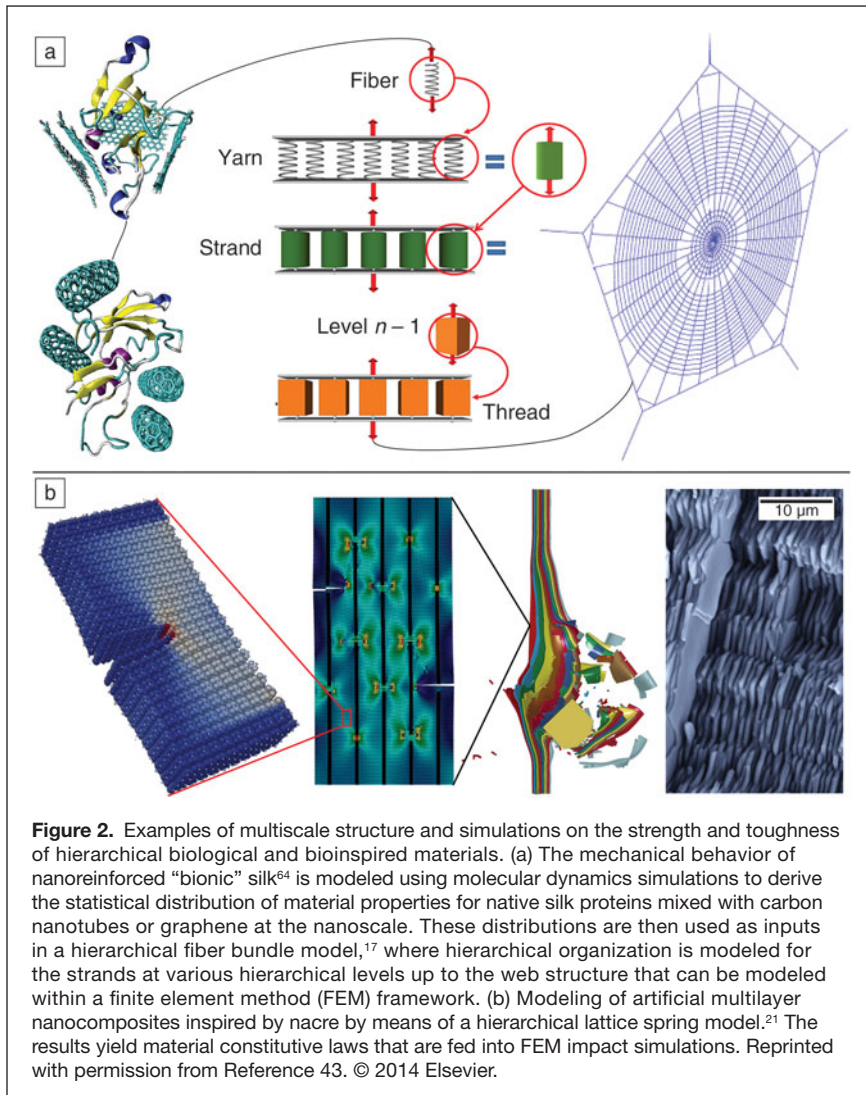

continuous media, discrete particles, and defects using the same set of equations, it provides a means to couple different length scales.²⁷

Applications of modeling biomaterials

Both theoretical models and numerical methods such as those previously described have shown that reinforcement organization in biological or bioinspired composite materials can increase damage tolerance, avoiding direct crack path propagation and drastically improving the global response.²⁸ Studies have focused on the influence of the structure, reinforcement shape, aspect ratio, dispersion, organization, and of mechanical properties of the constituents at various scale levels, iteratively deriving higher scale mechanical properties from lower ones, until a global material response is obtained.²⁹

As an example, the macroscopic nonlinear (stiffening) constitutive behavior of spider silk derived from atomistic simulations (Figure 2a) have been shown to play an essential role in the macroscopic robustness of spiderwebs,⁷ since

simulations demonstrate that the same type of impact would cause more widespread damage for linear elastic and elastic-perfectly plastic counterparts. Another example of how an integrated framework can synergistically combine scalable modeling using coarse-graining with mesoscopic dissipative particle dynamics simulations for bioinspired design can be found in studies on silk spinning.³⁰ The combined multiscale use of different computational techniques such as HFBM and HLSM has also proved to be successful in reproducing the macroscopic behavior of artificial nanocomposites such as gelatin-graphene oxide fibers.³¹ Mesoscale models allow the design of composite materials exhibiting tailored fracture properties, drawing inspiration from mineralized biological composites.³²

Another biomaterial property that has been studied and simulated in recent years is self-healing, and its effects on the elastic, fracture, and fatigue properties of materials.³³ Self-healing is incorporated in HFBM/HLSM models by replacing fractured fibers or springs with intact ones (the process of healing) having appropriate mechanical properties, volume fractions, replacement rates, and locations as damage evolves during simulations. The main control parameter is the “healing rate,” defined as the ratio of the number of healed and fractured fibers in a given fixed time interval. Both “distributed” and “local” healing processes can be simulated, whereby fractured fibers are replaced either over the whole structure or at concentrated locations where damage is accumulated, respectively.³⁴ It has been

found that a hierarchical structure increases the efficiency of self-healing, leading to increased toughness with respect to the corresponding nonhierarchical case and fatigue resistance, for example, in tendons.³⁵

The problem of simultaneous optimization of strength and toughness in materials also appears in the field of high-energy shock loadings (e.g., impacts and blasts). Indeed, energy dissipation must occur in a limited volume of material in these cases, since heavy structures are generally undesirable, such as in body armors, helmets, and crashworthy components for automotive or aerospace applications.

Extreme specific impact toughness may be pursued, for example, through the adoption of graphene-based nanocomposites^{36,37} or through smart bioinspired structural solutions. Dermal armors of various animals, such as the *Arapaima gigas* fish scales and many species of beetles, have several common characteristics, such as hard and patterned front layers^{38,39} and a backing sequence of softer layers,^{38,40} with overall flexibility of the armor (when required for locomotion) guaranteed via

discrete systems of interconnected scales.^{38,40,41} All of these features are generally synergistically coupled with hierarchical assembly, which optimizes layer thickness strength and stiffness.^{38,42}

The large variety of parameters to be considered in the study of these biological systems due to heterogeneity, the numerous levels of hierarchy, and the complexity of the constitutive laws (often strain-rate dependent) make experimental tests scarcely viable, and computational techniques are needed for the study of toughening mechanisms and for the design and optimization of bioinspired armors. Today, commercial software offers robust nonlinear FEM tools for the analysis of these types of large-scale problems at an acceptable computational cost. HFBM and HLSM are useful in providing an advanced constitutive response to be used as input in FEM simulations, which can be limited to details at the upper scale (Figure 2b). Thus, a series of parametric studies, each replicating thousands of experiments, can be performed. For example, the relationship between specific energy absorption in multilayer armors and the interface strength between layers, which could be tuned via different adhesive materials or with bioinspired hierarchical structuring of surfaces,⁴³ has been rationalized and explained through a FEM study on composite multilayer structures.⁴⁴

Modeling of impacts naturally involves friction. One of the main challenges is multiscale modeling of hierarchical rough surfaces that emerge at the microscale or from biological optimized solutions.^{45,46} Explicit numerical modeling of rough surfaces features a wide range of significant length scales and would be prohibitively expensive. Because of this, a central ingredient of a multiscale approach becomes homogenization, so that macroscale friction coefficients are derived from the solution of a microscale boundary-value problem based on the smallest representative volume element of the rough profile.⁴⁷ Alternatively, isogeometric analysis,⁴⁸ which exploits computer aided design of interpolating functions (splines) both as geometry descriptors and element basis functions, is especially attractive for the analysis of complex contact geometries. This can be exploited in the analysis of armors, for instance, such as those inspired by the bombardier beetle, whose reaction chamber for the production of a defensive fluid is enclosed in undulated walls for greater energy dissipation and structural resistance.⁴⁶

Another field in which multiscale FEM simulations are required is the modeling of dry adhesion in biological organisms, such as geckos, which is optimized using various strategies at different scale levels. Studies have shown how contact splitting (i.e., when a single contact is split into many smaller ones) is used effectively by animals such as geckos and insects to increase the total peeling line (i.e., the sum of the width of the contacts) and adhesion force.^{49,50} This is combined at the microscale with tapering of contact units or gradation in mechanical properties to increase adhesion efficiency.^{49,51}

Structures such as the anchorages of spiderwebs to external structures (Figure 3) exploit hierarchical structure together

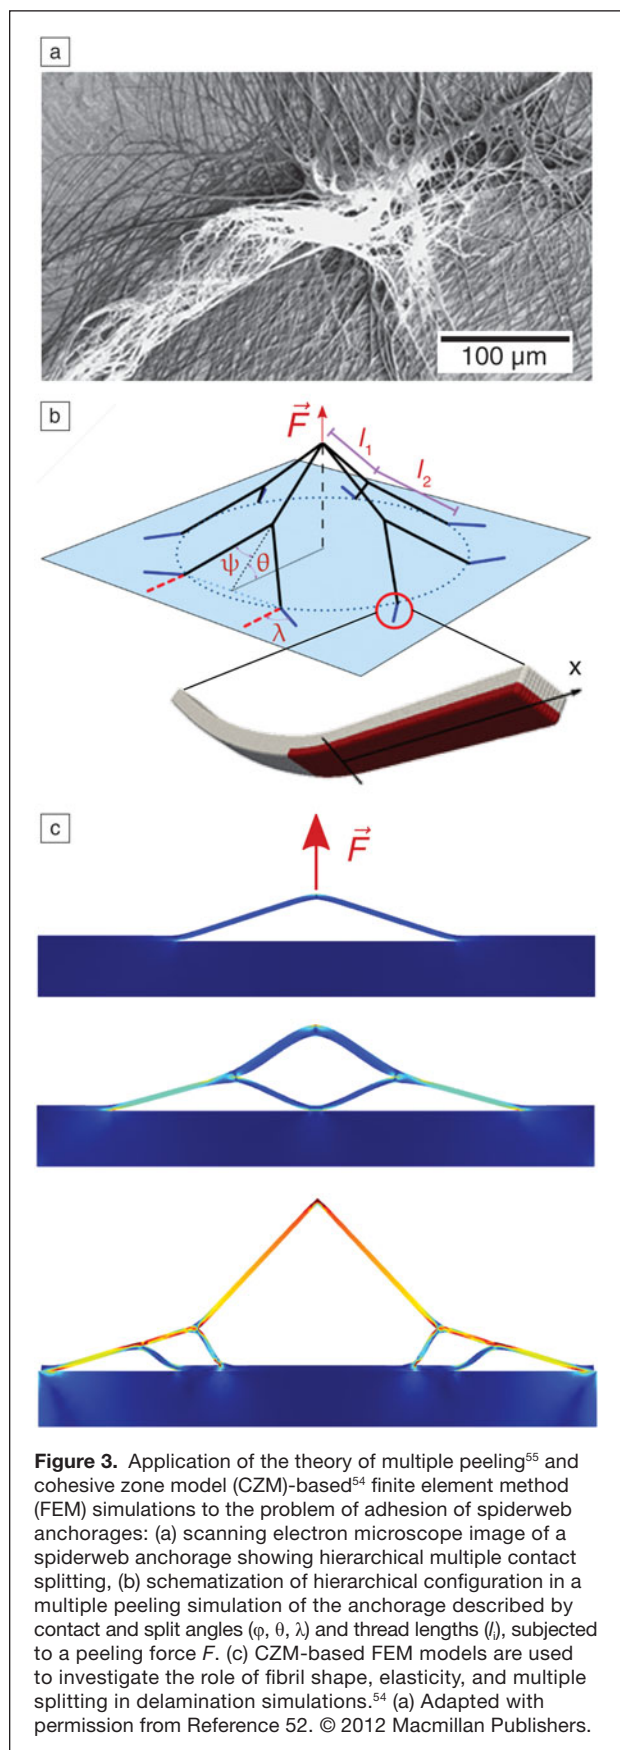


Figure 3. Application of the theory of multiple peeling⁵⁵ and cohesive zone model (CZM)-based⁵⁴ finite element method (FEM) simulations to the problem of adhesion of spiderweb anchorages: (a) scanning electron microscope image of a spiderweb anchorage showing hierarchical multiple contact splitting, (b) schematization of hierarchical configuration in a multiple peeling simulation of the anchorage described by contact and split angles (ψ , θ , λ) and thread lengths (l), subjected to a peeling force F . (c) CZM-based FEM models are used to investigate the role of fibril shape, elasticity, and multiple splitting in delamination simulations.⁵⁴ (a) Adapted with permission from Reference 52. © 2012 Macmillan Publishers.

with nonlinear constitutive material properties to improve resilience and to achieve tunability in adhesion/detachment characteristics.⁵² These mechanisms can be modeled using numerical implementations of our multiple peeling theory⁵³ or CZM formulations within a FEM-based framework. Such computational studies have revealed how, through hierarchical structure, contact splitting and adhesion can be maximized,⁵⁴ tunability achieved,⁵⁵ and microcontacts optimized for improved performance.⁵⁶ These results can be of great value in the design of bioinspired micropatterned adhesive surfaces.⁵⁷

Another topic of interest is the study of the vibrations and wave propagation in biological or bioinspired structures, such as in the bombardier beetle's undulated reaction chamber. The role of hierarchy in the dynamic behavior of these structures remains largely unexplored to date. Studies have highlighted the possibility of enhanced vibration damping through branching, including in bioinspired slender structures.⁵⁸ In the fields of phononic crystals and acoustic metamaterials (i.e., periodic structures exhibiting frequency bandgaps in which wave propagation is inhibited, or other exotic effects like focusing and cloaking), some theoretical investigations of 2D lattices with nonself-similar⁵⁹ or self-similar^{60,61} hierarchical topologies have been performed. Preliminary numerical studies have shown that hierarchy can help create wider bandgaps at multiple frequency scales compared to simple periodic structures,⁶² and to tune the bandgaps and directionality of phononic crystals.⁶³

Outlook

As discussed in this article, hierarchical design down to the nanoscale, where increased surface forces and material toughening mechanisms can be exploited, could be the breakthrough solution for a new generation of high-performance, multifunctional, and environmentally friendly materials. For this purpose, novel multiscale and multiphysics computational tools, such as HFBM and HLSM discussed here, need to be further developed, bridging traditional methods that deal with distinct scale ranges and enabling engineers and scientists to tailor and optimize structural mechanisms in multiphase, multiscale, and multifunctional materials. To make this possible, the aim of computational scientists is to broaden the overlap regions in scale and time between different simulation techniques, relying on the availability of ever more powerful computational resources and, whenever possible, to enable their integration within the same computational multiscale framework.

Acknowledgments

N.M.P. is supported by the European Research Council (ERC StG Ideas 2011 BIHSNAM No. 279985 and ERC PoC 2015 SILKENE No. 693670) and by the European Commission under the Graphene FET Flagship (WP14 "Polymer Composites" No. 696656). S.S. and F.B. acknowledge support from BIHSNAM.

References

1. Z.Q. Liu, D. Jiao, M.A. Meyers, Z.F. Zhang, *Acta Biomater.* **17**, 137 (2015).
2. H. Yao, H. Gao, *J. Mech. Phys. Solids* **54**, 1120 (2006).
3. C.E. Killian, R.A. Metzler, Y. Gong, T.H. Churchill, I.C. Olson, V. Trubetskov, M.B. Christensen, J.H. Fournelle, F. De Carlo, S. Cohen, J. Mahamid, A. Scholl, A. Young, A. Doran, F.H. Wilt, S.N. Coppersmith, P.U.P.A. Gilbert, *Adv. Funct. Mater.* **21**, 682 (2011).
4. Y. Tian, L. Jiang, *MRS Bull.* **40**, 155 (2015).
5. M.A. Meyers, P.Y. Chen, A.Y.M. Lin, Y. Seki, *Prog. Mater. Sci.* **53**, 1 (2008).
6. B.H. Ji, H.J. Gao, *J. Mech. Phys. Solids* **52**, 1963 (2004).
7. S.W. Cranford, A. Tarakanova, N.M. Pugno, M.J. Buehler, *Nature* **482**, 72 (2012).
8. H.S. Gupta, J. Seto, W. Wagermaier, P. Zaslansky, P. Boesecke, P. Fratzl, *Proc. Natl. Acad. Sci. U.S.A.* **103**, 17741 (2006).
9. S.W. Cranford, *Biomateriomics*, 1st ed. (Springer, New York, 2012).
10. S.W. Cranford, J. de Boer, C. van Blitterswijk, M.J. Buehler, *Adv. Mater.* **25**, 802 (2013).
11. G.B. Olson, *Science* **277**, 1237 (1997).
12. L. Mishnaevsky, *Rev. Adv. Mater. Sci.* **30**, 60 (2012).
13. L. Mishnaevsky, G. Dai, *Compos. Struct.* **117**, 156 (2014).
14. S. Pradhan, A. Hansen, B.K. Chakrabarti, *Rev. Mod. Phys.* **82**, 499 (2010).
15. N.M. Pugno, F. Bosia, T. Abdalrahman, *Phys. Rev. E* **85**, 011903 (2012).
16. L. Mishnaevsky, *Compos. Sci. Technol.* **71**, 450 (2011).
17. F. Bosia, T. Abdalrahman, N.M. Pugno, *Nanoscale* **4**, 1200 (2012).
18. N.M. Pugno, F. Bosia, A. Carpinteri, *Small* **4**, 1044 (2008).
19. A.B. Gavin, M.C. Christopher, J.C. Douglas, *Model. Simul. Mater. Sci. Eng.* **9**, 485 (2001).
20. S. Zapperi, A. Vespignani, H.E. Stanley, *Nature* **388**, 658 (1997).
21. L. Brely, F. Bosia, N.M. Pugno, *Front. Mater.* **2**, 00051 (2015).
22. N.M. Pugno, R.S. Ruoff, *Philos. Mag.* **84**, 2829 (2004).
23. S.W. Yang, P.R. Budarapu, D.R. Mahapatra, S.P.A. Bordas, G. Zi, T. Rabczuk, *Comput. Mater. Sci.* **96**, 382 (2015).
24. E. Barbieri, M. Meo, *Compos. Sci. Technol.* **69**, 2169 (2009).
25. L.T. Zhang, W.K. Liu, S.F. Li, D. Qian, S. Hao, "Survey of Multi-scale Meshfree Particle Methods," in *Meshfree Methods for Partial Differential Equations*, M. Griebel, M.A. Schweitzer, Eds. (Springer Berlin Heidelberg, Berlin, 2003).
26. J.H. Song, H.W. Wang, T. Belytschko, *Comput. Mech.* **42**, 239 (2008).
27. S.A. Silling, *J. Mech. Phys. Solids* **48**, 175 (2000).
28. D. Sen, M.J. Buehler, *Sci Rep.* **1**, 35 (2011).
29. Z.Q. Zhang, Y.W. Zhang, H.J. Gao, *Proc. R. Soc. Lond. B* **278**, 519 (2011).
30. S.C. Lin, S. Ryu, O. Tokareva, G. Gronau, M.M. Jacobsen, W.W. Huang, D.J. Rizzo, D. Li, C. Staii, N.M. Pugno, J.Y. Wong, D.L. Kaplan, M.J. Buehler, *Nat. Commun.* **6**, 6892 (2015).
31. S. Panzavolta, B. Bracci, C. Gualandi, M.L. Focarete, E. Treossi, K. Kouroupis-Agalou, K. Rubini, F. Bosia, L. Brely, N.M. Pugno, V. Palermo, A. Bigi, *Carbon* **78**, 566 (2014).
32. L.S. Dimas, G.H. Bratzel, I. Eylon, M.J. Buehler, *Adv. Funct. Mater.* **23**, 4629 (2013).
33. A.C. Balazs, *Mater. Today* **10**, 18 (2007).
34. F. Bosia, T. Abdalrahman, N.M. Pugno, *Langmuir* **30**, 1123 (2014).
35. F. Bosia, M. Merlino, N.M. Pugno, *J. Mater. Res.* **30**, 2 (2015).
36. J.-H. Lee, P.E. Loya, J. Lou, E.L. Thomas, *Science* **346**, 1092 (2014).
37. K. Yoon, A. Ostadhosseini, A.C.T. van Duin, *Carbon* **99**, 58 (2016).
38. S.N. Patek, R.L. Caldwell, *J. Exp. Biol.* **208**, 3655 (2005).
39. L. Kundanati, N. Gundiah, *J. Exp. Biol.* **217**, 1946 (2014).
40. W. Yang, I.H. Chen, B. Gludovatz, E.A. Zimmermann, R.O. Ritchie, M.A. Meyers, *Adv. Mater.* **25**, 31 (2013).
41. H.M. Yao, M. Dao, T. Imholt, J.M. Huang, K. Wheeler, A. Bonilla, S. Suresh, C. Ortiz, *Proc. Natl. Acad. Sci. U.S.A.* **107**, 987 (2010).
42. R.O. Ritchie, *Nat. Mater.* **13**, 435 (2014).
43. E. Lin, Y. Li, C. Ortiz, M.C. Boyce, *J. Mech. Phys. Solids* **73**, 166 (2014).
44. S. Signetti, N.M. Pugno, *J. Eur. Ceram. Soc.* **34**, 2823 (2014).
45. M.J. Baum, A.E. Kovalev, J. Michels, S.N. Gorb, *Tribol. Lett.* **54**, 139 (2014).
46. E.M. Arndt, W. Moore, W.-K. Lee, C. Ortiz, *Science* **348**, 563 (2015).
47. P. Wriggers, *Computational Contact Mechanics*, 2nd ed. (Springer-Verlag Berlin Heidelberg, New York, 2006).
48. T.J.R. Hughes, J.A. Cottrell, Y. Bazilevs, *Comput. Methods Appl. Mech. Eng.* **194**, 4135 (2005).
49. M. Varenberg, N.M. Pugno, S.N. Gorb, *Soft Matter* **6**, 3269 (2010).
50. M. Kamperman, E. Kroner, A. del Campo, R.M. McMeeking, E. Arzt, *Adv. Eng. Mater.* **12**, 335 (2010).
51. H. Peisker, J. Michels, S.N. Gorb, *Nat. Commun.* **4**, 1661 (2013).
52. V. Sahni, J. Harris, T.A. Blackledge, A. Dhinojwala, *Nat. Commun.* **3**, 1106 (2012).
53. N.M. Pugno, *Int. J. Fract.* **171**, 185 (2011).
54. F. Bosia, S. Colella, V. Mattoli, B. Mazzolai, N.M. Pugno, *RSC Adv.* **4**, 25447 (2014).
55. L. Brely, F. Bosia, N.M. Pugno, *Interface Focus* **5**, 20140051 (2015).
56. R.A. Sauer, M. Holl, *Comput. Methods Biomech. Biomed. Eng.* **16**, 577 (2013).

57. G. Carbone, E. Pierro, S.N. Gorb, *Soft Matter* **7**, 5545 (2011).
 58. B. Theckes, E.D. Langre, X. Boutillon, *Bioinspir. Biomim.* **6**, 046010 (2011).
 59. Y.L. Xu, X.G. Tian, C.Q. Chen, *Physica B* **407**, 1995 (2012).
 60. Q.J. Lim, P. Wang, S.J.A. Koh, E.H. Khoo, K. Bertoldi, *Appl. Phys. Lett.* **107**, 221911 (2015).
 61. D. Mousanezhad, S. Babae, H. Ebrahimi, R. Ghosh, A.S. Hamouda, K. Bertoldi, A. Vaziri, *Sci. Rep.* **5**, 18306 (2015).
 62. M. Miniaci, A. Krushynska, F. Bosia, N.M. Pugno, *submitted to J. Mech. Phys. Solids* (forthcoming).
 63. D. Mousanezhad, S. Babae, R. Ghosh, E. Mahdi, K. Bertoldi, A. Vaziri, *Phys. Rev. B Condens. Matter* **92**, 104304 (2015).
 64. E. Lepore, F. Bonaccorso, M. Bruna, F. Bosia, S. Taioli, G. Garberoglio, A.C. Ferrari, N.M. Pugno, *Condens. Matter Mater. Sci.* (2015), available at <http://arxiv.org/abs/1504.06751>.
 65. M. Buehler, T. Ackbarow, *Mater. Today* **10**, 46 (2007). □



jmr Journal of
MATERIALS RESEARCH

FOCUS ISSUE • MAY 2017

Submission Deadline—October 1, 2016



Microstructural Characterization for Emerging Photovoltaic Materials

Emerging solar cell technologies, in particular those based on organic molecules and polymers, inorganic-organic perovskites, and kesterite-based semiconductors have begun demonstrating their potential for inexpensive solar energy on a terawatt scale. Increasing the power conversion efficiency and device lifetimes of these materials requires exercising nanoscale control over thin-film microstructure and device interfaces across large areas. Each of these systems has presented unique challenges to their full morphological and microstructural characterization, with issues ranging from poor scattering contrast between layers (organics) to overlapping diffraction features (kesterites). Advances in x-ray and neutron scattering methods have enabled breakthroughs in understanding the relationship between thin-film microstructure and device-level properties in these emerging energy materials, findings which have propelled photovoltaic performance over the last decade. Increased access to synchrotron and neutron sources, coupled with the development of new tools and techniques that merge scattering and spectroscopic information, are providing exciting opportunities to probe the microstructural evolution of these materials from fabrication through to fully operational devices subject to real-world environments.

Research papers are solicited in the use of x-ray and neutron characterization methods to monitor microstructure of these emerging energy materials, in particular methods that enable thin-film monitoring under fabrication and/or operational conditions. Approaches that demonstrate applications to the improved design and fabrication of materials and devices—affording insights into the underlying chemistry, materials science, and photophysics—are highly encouraged.

The issue will have a special emphasis on:

- ◆ Techniques that enable quantitative correlation between electronic performance and bulk microstructural evolution of emerging solar cell technologies, highlighting x-ray and neutron tools, but not excluding other approaches
- ◆ *In situ* and *in operando* techniques for monitoring physico-chemical interactions during photovoltaic device operation, including spectroscopic methods
- ◆ New experimental and computational approaches for classifying and quantifying structural properties in molecular and disordered electronic materials
- ◆ Integration of characterization tools in process monitoring for scalable module fabrication

GUEST EDITORS

Moritz Riede, University of Oxford, United Kingdom

Chris Nicklin, Diamond Light Source, United Kingdom

Dean M. DeLongchamp, National Institute of Standards and Technology, USA

Submission instructions may be found at www.mrs.org/jmr-instructions.

CALL FOR PAPERS

jmr@mrs.org



Leon Mishnaevsky Jr.
Guest Editor for this issue of *MRS Bulletin*

Department of Wind Energy, Technical University of Denmark, Denmark; tel. +45 46 77 57 29; and email lemi@dtu.dk. Mishnaevsky is a senior scientist at the Technical University of Denmark. He received his PhD degree from the Russian Academy of Sciences and a Dr. habil. degree from Technische Universität Darmstadt (TU Darmstadt), Germany. He is the author of more than 120 research papers. Prior to joining TU Darmstadt, he was a Heisenberg Fellow at the University of Stuttgart,

and was a visiting professor/scholar at Massachusetts Institute of Technology and Rutgers, The State University of New Jersey; The University of Tokyo, Japan; and École Nationale Supérieure d'Arts et Métiers, France. Mishnaevsky has led several international projects (EU, Danish-Chinese, Danish-Japanese) and is a chairman of many international conferences in composites, nanomaterials, modeling, and energy.



Michael Tsapatsis
Guest Editor for this issue of *MRS Bulletin*

Department of Chemical Engineering and Materials Science, University of Minnesota, USA; email tsapatsis@umn.edu.

Tsapatsis is a professor and the Amundson Chair in the Department of Chemical Engineering and Materials Science at the University of Minnesota. He has co-authored approximately 220 publications. Recent accomplishments of his group include the development of hierarchical catalysts and molecular sieve films for membrane applications. His teaching interests

include chemical engineering and materials design, with an emphasis on energy efficiency and process intensification. Tsapatsis is a member of the National Academy of Engineering.



Federico Bosia
Department of Physics and Nanostructured Interfaces and Surfaces Interdepartmental Centre, University of Turin, Italy; tel. +390116707889; and email fbosia@unito.it.

Bosia has been at the University of Turin in the Solid State Physics Group since 2007. He received his BS degree in physics in 1996 and his PhD degree in mechanical engineering in 2002 at École Polytechnique Fédérale de Lausanne, Switzerland. He has also worked at the Leibniz Institute for Solid State and Materials Research (IFW Dresden), Germany, and at Politecnico

di Torino, Italy. Bosia has published approximately 60 papers on topics related to the mechanics of composite and bioinspired materials, nonlinear elasticity, and acoustics.



Peter Fratzl
Department of Biomaterials, Campus Gölml, Max Planck Institute of Colloids and Interfaces, Germany; tel. +49-331-567-9400; and email fratzl@mpikg.mpg.de.

Fratzl is director at the Max Planck Institute of Colloids and Interfaces in the Department of Biomaterials. He received his engineering degree from École Polytechnique in France and his PhD degree from the University of Vienna, Austria. His research interests include structure and properties of biological and bioinspired materials. He co-authored over 500 publica-

tions and is a recipient of the Leibniz Award. Fratzl is also a member in several Academies of Science in Germany and Austria, and has been an MRS Fellow since 2012.


doi:10.1557/mrs.2016.169



Larissa Gorbatikh

Department of Materials Engineering, KU Leuven, Belgium; tel. +32-16-32 1235; and email larissa.gorbatikh@mtm.kuleuven.be. Gorbatikh is a research expert in the Composite Materials Group in the Department of Materials Engineering at KU Leuven, where she coordinates research activities in the field of nano-engineered and hybrid polymer composites. She received her master's degree in mechanics from St. Petersburg State University, Russia, in 1997, and her PhD degree in mechanical engineering from Tufts University in 2001. She

has co-authored over 120 publications and participated in many European and national projects in the United States, Belgium, and Russia. Gorbatikh currently serves on the council of the European Society for Composite Materials.

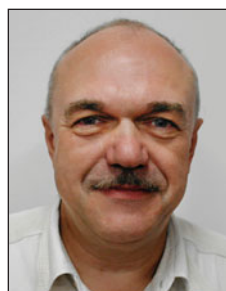

Evgeny Levashov

Department of Powder Metallurgy and Functional Coatings, Scientific-Educational Center of Self-Propagating High-Temperature Synthesis Center, National University of Science and Technology "MISIS," Russian Federation; tel. +7 495 6384500; and email levashov@shs.misis.ru.

Levashov is the head of the Department of Powder Metallurgy and Functional Coatings, director of the Self-Propagating High-Temperature Synthesis Center at the National University of Science and Technology, MISIS, and is also a professor.

He received an Honorary Doctorate of Engineering from the Colorado School of Mines in 2007. He is the author of four textbooks, 96 patents, and more than 580 articles. He serves as an editor-in-chief of the *Russian Journal of Non-Ferrous Metals*. Levashov's research is focused on materials science of functional materials and coatings.



Pavel Loginov

National University of Science and Technology, Moscow Institute of Steel and Alloys "MISIS," Russian Federation; tel. +74952369936; and email pavel.loginov.misis@list.ru.

Loginov is a junior research scientist at the National University of Science and Technology, MISIS. He received his MS degree in 2011 and his PhD degree in 2014, both from the National University of Science and Technology, MISIS. He is the author of 10 research papers. Loginov's scientific interests include powder metallurgy, dia-

mond tools, metal-matrix composites, mechanical alloying, and cutting diamond tools.



Stepan V. Lomov

Department of Materials Engineering, KU Leuven, Belgium; tel. +32-16-321210; and email Stepan.Lomov@mtm.kuleuven.be.

Lomov is a coordinator of the Composite Materials Group in the Department of Materials Engineering at KU Leuven and holds the Toray Chair. His research interests span experimental and theoretical studies of composites and textiles. He has co-authored more than 500 papers, edited two books, and is an editorial board member of *Composite Science and Technology*, *Textile Research Journal*, *Mechanics & Industry*,

and scientific committees of various conferences. Lomov's WiseTex software is licensed to more than 50 industrial and academia users worldwide.



Svetlana Mintova
Laboratoire Catalyse et Spectrochimie–
ENSICAEN, Université de Caen, CNRS,
France; tel. +33231452737; and
email svetlana.mintova@ensicaen.fr.

Mintova is a research director at the Laboratoire Catalyse et Spectrochimie–ENSICAEN Université de Caen, CNRS. She received her PhD degree in physical chemistry from the Technological University of Sofia, Bulgaria, in 1993. She worked as a docent at the University of Munich, Germany, as a visiting scholar at Purdue University, and as a postdoc at the Luleå University of Technology,

Sweden. Mintova's research interests include synthesis of nano-sized porous materials (zeolites) and preparation of films and assemblies related to new applications and processes.



Nicola M. Pugno
Laboratory of Bio-Inspired & Graphene
Nanomechanics, Department of Civil,
Environmental and Mechanical Engineering,
University of Trento, and Center for Materials
and Microsystems, Fondazione Bruno
Kessler, Italy; and School of Engineering
and Materials Science, Queen Mary
University of London, UK; tel. +39 0461
282525; and email nicola.pugno@unitn.it.

Pugno is a full professor of solid and structural mechanics at the University of Trento, and founder and head of the Laboratory of Bio-

Inspired & Graphene Nanomechanics. He leads the Graphene Nanocomposites grant within the EU Graphene Flagship at the Fondazione Bruno Kessler, Italy, and is a full professor of materials science at the Queen Mary University of London. He received master's degrees in mechanical engineering and theoretical physics, and two PhD degrees in fracture mechanics and biology. Pugno has published approximately 300 journal papers, and has received four grants from the European Research Council.



Daria Sidorenko
National University of Science and Technology,
Moscow Institute of Steel and Alloys "MISIS",
Russian Federation; tel. +74956384442;
and email dsidorenko@inbox.ru.

Sidorenko is a research scientist at the National University of Science and Technology, MISIS. She received her MS degree in 2009 and her PhD degree in 2012, both from the National University of Science and Technology, MISIS. She is the author of 15 research papers. Sidorenko's scientific interests include metal-matrix composites, nanomaterials, diamond, powder met-

allurgy, and cutting diamond tools.



Stefano Signetti
Laboratory of Bio-Inspired & Graphene
Nanomechanics, Department of Civil,
Environmental and Mechanical Engineering,
University of Trento, Italy; tel. +39 0461
282597; and email stefano.signetti@unitn.it.

Signetti is currently a doctoral candidate in solid and structural mechanics at the University of Trento. He received his MS degree in civil engineering from the Politecnico di Torino, Italy, in 2013. His research interests include the mechanics of biological and bioinspired structures involving fracture and fragmentation

under high-energy impacts, anticatastrophe civil structures, graphene-based nanocomposites, and tribology of graphene and of bioinspired nanosurfaces.



Mark A. Snyder
Department of Chemical and Biomolecular
Engineering, Lehigh University, USA; tel. 610-
758-6834; and email snyder@lehigh.edu.

Snyder is an associate professor of chemical and biomolecular engineering at Lehigh University. He received his BS degree from Lehigh University in 2000 and his PhD degree in 2006 from the University of Delaware, both in chemical engineering. Before joining the faculty at Lehigh in 2008, he was a postdoctoral associate in the Department of Chemical Engineering and Materials Science at the University of Minnesota.

His research interests include engineering of inorganic nanoparticles, nanoparticle assembly, and template-mediated synthesis of porous inorganic materials for applications spanning catalysis, separations, and electrodes. Snyder is the recipient of an NSF CAREER Award in 2014.



Valentin Valtchev
Laboratoire Catalyse et Spectrochimie–
ENSICAEN, Université de Caen, CNRS,
France; tel. +33679201146; and
email valentin.valtchev@ensicaen.fr.

Valtchev is a research director at the Laboratoire Catalyse et Spectrochimie–ENSICAEN Université de Caen, CNRS. He studied geochemistry at the University of Sofia, Bulgaria, and received his PhD degree from the Bulgarian Academy of Sciences. He worked as a postdoctoral research fellow from 1992 to 1993 and 1995 to 1996. In 1996, he was promoted to senior researcher at

the Bulgarian Academy of Sciences. Valtchev's research interests include synthesis and modification of zeolites and other porous solids that can be used for catalysis, separation, and molecular recognition.



Brian L. Wardle
Department of Aeronautics and Astronautics,
Massachusetts Institute of Technology, USA;
tel. 617-252-1539; and email wardle@mit.edu.

Wardle studies materials and structures in Massachusetts Institute of Technology's (MIT) Department of Aeronautics and Astronautics, with a focus on bulk nanostructured materials and devices. He is the founder and director of the Necstlab Research Group and MIT's NECST aerospace industry consortium. He received his BS degree in aerospace engineering from The Pennsylvania State University in 1992, and his

SM and PhD degrees at MIT in the Department of Aeronautics and Astronautics in 1995 and 1998, respectively. He has authored over 90 journal articles and holds five patents with more than 10 other applications pending in the area of nanoengineered materials. Wardle is an Associate Fellow of the American Institute of Aeronautics and Astronautics.



Richard Weinkamer
Department of Biomaterials, Campus Golm,
Max Planck Institute of Colloids and Interfaces,
Germany; tel. +49 (0) 331 567 9410; and
email Richard.Weinkamer@mpikg.mpg.de.

Weinkamer is a group leader in the Department of Biomaterials at the Max Planck Institute of Colloids and Interfaces. He earned his PhD degree in physics and his MS degree in mathematics from the University of Vienna, Austria, and, in 2012, habilitated in theoretical physics at Humboldt University of Berlin, Germany. Weinkamer's research interests include the adap-

tive and healing properties of biological materials, particularly bone.