

Ionic Conductivity and Solid Electrolytes I: The Basics

Chemistry 754
Solid State Chemistry
Lecture #26
June 2, 2003

Chem 754 - Solid State Chemistry

References

- A.R. West** - "*Solid State Chemistry and its Applications*", Chapter 13, Wiley (1984)
- C.N.R Rao and J. Gopalakrishnan** - "New Directions in Solid State Chemistry", pp. 409-416, Cambridge (1997)
- A. Manthiram & J. Kim** - "Low Temperature Synthesis of Insertion Oxides for Lithium Batteries", *Chem. Mater.* **10**, 2895-2909 (1998).
- J.C. Boivin & G. Mairesse** - "Recent Material Developments in Fast Oxide Ion Conductors", *Chem. Mater.* **10**, 2870-2888 (1998).
- Craig Fisher** (Japan Fine Ceramic Institute)
<http://www.spice.or.jp/~fisher/sofc.html>

Chem 754 - Solid State Chemistry

Solid Electrolytes

Electrolyte - A substance that conducts electricity through the movement of ions.

Most electrolytes are solutions or molten salts, but some electrolytes are solids and some of those are crystalline solids. Different names are given to such materials:

- Solid Electrolyte
- Fast Ion Conductor
- Superionic Conductor

Over the next two lectures we will be looking at materials which behave as solid electrolytes, their properties and applications.

Chem 754 - Solid State Chemistry

Ionic vs. Electronic Conductivity

Let's begin by comparing the properties of ionic conductors with the conventional electronic conductivity of metals.

Metals

- Conductivity Range = $10 \text{ S/cm} < \sigma < 10^5 \text{ S/cm}$
- Electrons carry the current
- Conductivity Increases linearly as temperature decreases (phonon scattering decreases as $T \downarrow$)


Solid Electrolytes

- Conductivity Range = $10^{-3} \text{ S/cm} < \sigma < 10 \text{ S/cm}$
- Ions carry the current
- Conductivity decreases exponentially as temperature decreases (activated transport)


Chem 754 - Solid State Chemistry

Defects

In order for an ion to move through a crystal it must hop from an occupied site to a vacant site. Thus ionic conductivity can only occur if defects are present. The two simplest types of point defects are Schottky and Frenkel defects.

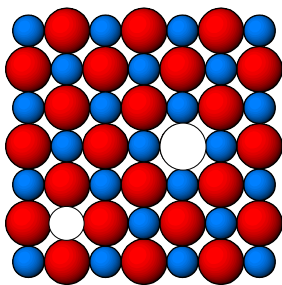

Schottky Defect
(i.e. NaCl)
 $\text{Na}^+ + \text{Cl}^- \rightarrow V_{\text{Na}} + V_{\text{Cl}}$



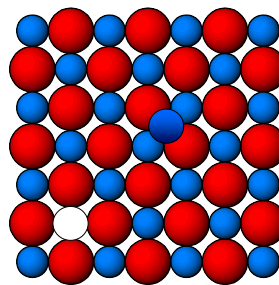


Frenkel Defect
(i.e. AgCl)
 $\text{Ag}^+ \rightarrow V_{\text{Ag}^+} + \text{Ag}^+_{\text{interstitial}}$

Chem 754 - Solid State Chemistry

Ion Migration (Schottky Defects)


Consider the movement of Na^+ ions in NaCl via vacancies originating from Schottky defects. Note that the Na^+ ion must squeeze through the lattice, inducing significant local distortion/relaxation. This is one factor that limits the mobility of ions. A second factor that contributes is the relatively high probability that the ion will jump back to its original position, leading to no net ionic migration.

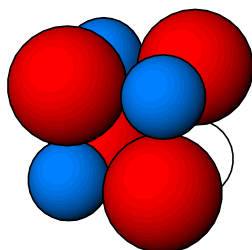


To get across the unit cell into the vacancy the Na^+ ion must hop through the center of the cube where it squeezes by 4 Cl^- and 2 Na^+ . The energy of this "transition state" will determine the ease of migration.

Ion Migration (Frenkel Defects)

The Frenkel defects in AgCl can migrate via two mechanisms.

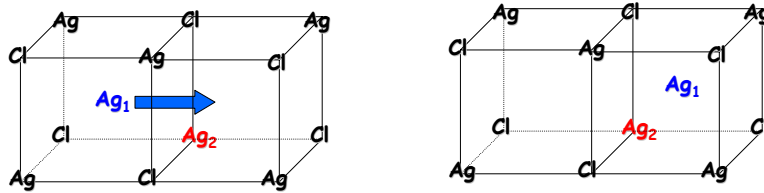

Direct Interstitial Jump

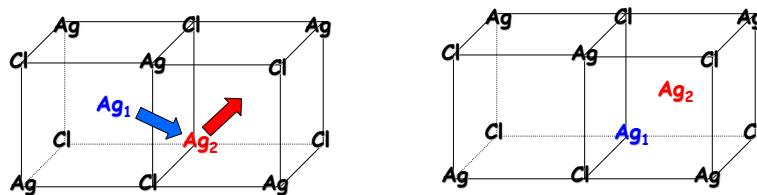


Interstitialcy Mechanism

Chem 754 - Solid State Chemistry

Applications of Ionic Conductors

There are numerous practical applications, all based on electrochemical cells, where ionic conductivity is needed and it is advantageous/necessary to use solids for all components.

- Batteries
- Fuel Cells
- Gas Sensors

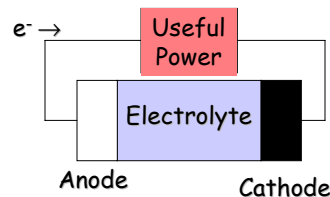


In such cells ionic conductors are needed for either the electrodes, the electrolyte or both.

- Electrolyte** (Material needs to be an electrical insulator to prevent short circuit)
- Electrode** (Mixed ionic and electronic conductivity is needed to avoid open circuit)

Chem 754 - Solid State Chemistry

Schematic of a Solid Oxide Fuel Cell

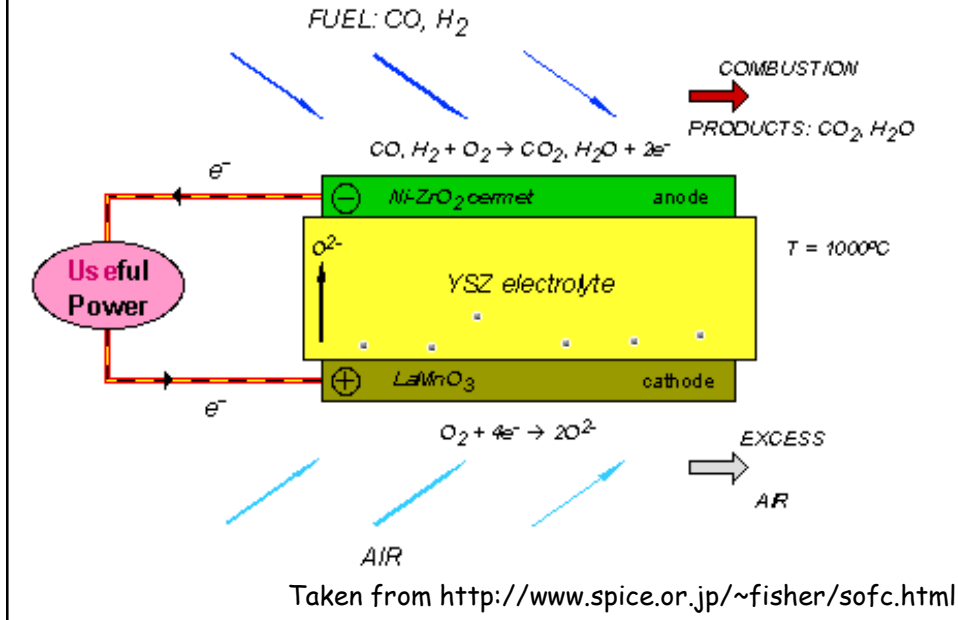

Schematic of Rechargeable Li Battery

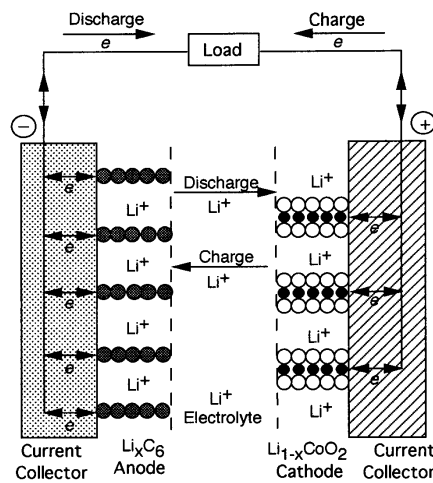


Figure 6. Schematic illustration of the discharge and charge processes in a rechargeable lithium ion battery. In the Li_xCoO_2 cathode, the solid and open circles refer, respectively, to Co and O atoms (adapted from ref 14).

Taken from A. Manthiram & J. Kim - "Low Temperature Synthesis of Insertion Oxides for Lithium Batteries", Chem. Mater. 10, 2895-2909 (1998).

Chem 754 - Solid State Chemistry

Solid Electrolyte Materials

- **Ag⁺ Ion Conductors**

- AgI & RbAg₄I₅

- **Na⁺ Ion Conductors**

- Sodium β-Alumina (i.e. NaAl₁₁O₁₇, Na₂Al₁₆O₂₅)

- NASICON (Na₃Zr₂PSi₂O₁₂)

- **Li⁺ Ion Conductors**

- LiCoO₂, LiNiO₂

- LiMnO₂

- **O²⁻ Ion Conductors**

- Cubic stabilized ZrO₂ (Y_xZr_{1-x}O_{2-x/2}, Ca_xZr_{1-x}O_{2-x})

- δ-Bi₂O₃


- Defect Perovskites (Ba₂In₂O₅, La_{1-x}Ca_xMnO_{3-y}, ...)

- **F⁻ Ion Conductors**

- PbF₂ & AF₂ (A = Ba, Sr, Ca)

Chem 754 - Solid State Chemistry

Stabilized ZrO₂ is not a good ionic conductor at low temperature.

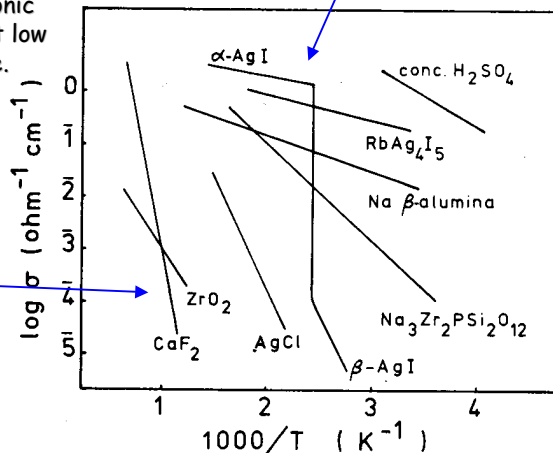

α-AgI & RbAg₄I₅ have ionic conductivities comparable to conc. H₂SO₄

Fig. 13.10 Ionic conductivity of some solid electrolytes with concentrated H₂SO₄ for comparison. In searching for new materials, one aims for the top right-hand corner of the diagram (high σ , low T)

Taken from "Solid State Chemistry and its Applications" by Anthony West

General Characteristics: Solid Electrolytes

1. A large number of the ions of one species should be mobile. This requires a large number of empty sites, either vacancies or accessible interstitial sites.
 - Empty sites are needed for ions to move through the lattice.
2. The empty and occupied sites should have similar potential energies with a low activation energy barrier for jumping between neighboring sites.
 - High activation energy decreases carrier mobility, very stable sites (deep potential energy wells) lead to carrier localization.
3. The structure should have solid framework, preferable 3D, permeated by open channels.
 - The migrating ion lattice should be "molten", so that a solid framework of the other ions is needed in order to prevent the entire material from melting.
4. The framework ions (usually anions) should be highly polarizable.
 - Such ions can deform to stabilize transition state geometries of the migrating ion through covalent interactions.

Molten Sublattice (1/2 Melting)

In the best ionic conductors one ion becomes so mobile that for all intensive purposes those ions are in a "molten" state. This behavior can be seen in part from the entropies of the observed phase transitions, where the Ag (and F respectively) sublattice melts prematurely.

(poor ionic conductor) $\beta\text{-AgI} \rightarrow \alpha\text{-AgI}$ (excellent ionic conductor)

$$T = 146\text{ }^\circ\text{C}, \Delta S = 14.5\text{ J/mol-K}$$

$\alpha\text{-AgI} \rightarrow \text{molten AgI}$

$$\Delta S = 11.3\text{ J/mol-K}$$

Compare with the an entropy of melting of 24 J/mol-K for NaCl.

$\text{solid PbF}_2 \rightarrow \text{molten PbF}_2$

$$\Delta S = 16.4\text{ J/mol-K}$$

Compare with the an entropy of melting of 35 J/mol-K for MgF₂

Ag⁺ Ion Conductors

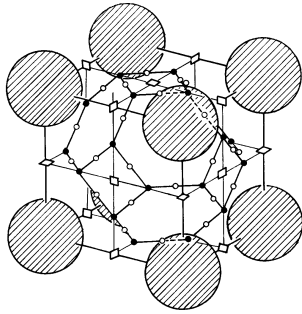


Figure 7.2 Structure of α -AgI, showing interstitial cation sites: large hatched circles, iodide ions; squares, octahedral 6b sites; solid circles, tetrahedral 12d sites; open circles, 24h sites.




Fig. 13.16 Conductivity of Ag⁺ in AgI and RbAg₄I₅

β -AgI

- Stable below 146 °C
- Wurtzite Structure (tetrahedral coordination)
- $\sigma = 0.001 \text{ S/cm} - 0.0001 \text{ S/cm}$

α -AgI

- Stable above 146 °C
- BCC Arrangement of I⁻, molten/disordered Ag⁺
- $\sigma \sim 1 \text{ S/cm}$, $E_A = 0.05 \text{ eV}$
- Conductivity decreases on melting

RbAg₄I₅

- Highest known conductivity at room temperature
- BCC Arrangement of I⁻, molten/disordered Ag⁺
- $\sigma \sim 0.25 \text{ S/cm}$ (25 °C), $E_A = 0.07 \text{ eV}$

Chem 754 - Solid State Chemistry

Na⁺ Ion Conductors

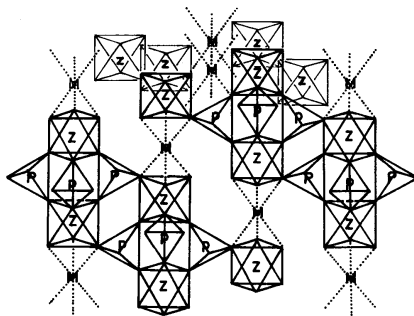


Figure 7.3 Structure of NaZr₂(PO₄)₃. (After Goodenough, 1984)

Na₃Zr₂PSi₂O₁₂ (NASICON)

- Framework of corner sharing ZrO₆ octahedra and PO₄/SiO₄ tetrahedra
- Na⁺ ions occupy trigonal prismatic and octahedral sites, $\frac{1}{4}$ of the Na⁺ sites are empty
- $E_A \sim 0.3 \text{ eV}$

NaAl₇O₁₁ (Na₂O·nAl₂O₃)

- FCC like packing of oxygen
- Every fifth layer $\frac{1}{4}$ of the O²⁻ ions are missing, Na⁺ ions present. These layers are sandwiched between spinel blocks.
- 2D ionic conductor

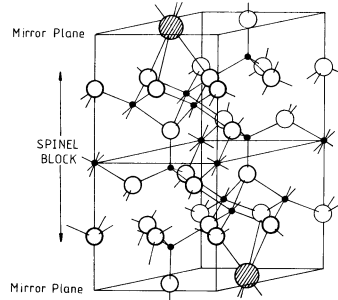


Figure 7.4 Structure of sodium β -alumina. Only half the unit cell is shown. Large hatched circles represent sodium, open circles oxygen, and small filled circles aluminium.