

AD-A105 498

NAVAL SEA SYSTEMS COMMAND WASHINGTON DC  
LASER TRANSFORMATION HARDENING OF FIRING ZONE CUTOUT CAMS.(U)  
JUN 81 R W LOWRY


F/G 20/5

UNCLASSIFIED

NAVSEA-5555-79

NL

1 of 1  
AD-A  
105-498

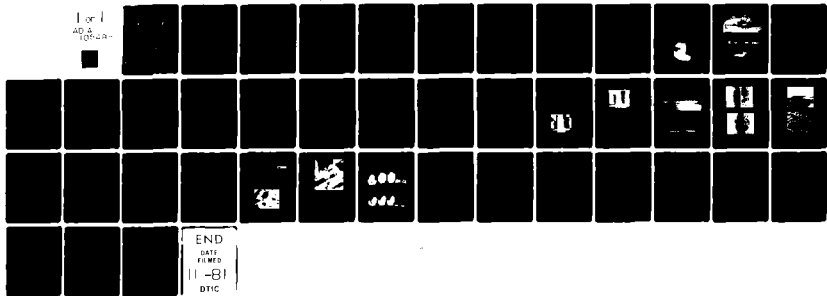

AD A105498

LEI

NAVSEA REPORT NO. S555-79  
JUNE 1981

12



# LASER TRANSFORMATION HARDENING OF FIRING ZONE CUTOUT CAMS

FINAL REPORT

A PROJECT OF THE  
MANUFACTURING TECHNOLOGY PROGRAM  
NAVAL SEA SYSTEMS COMMAND

by  
ROBERT W. LOWRY

DTIC  
ELECTE  
OCT 15 1981

A

Approved for public release; distribution unlimited.

WING FILE COPY

NAVAL SURFACE WEAPONS CENTER

DAHLGREN, VIRGINIA 22448

SILVER SPRING, MARYLAND 20910

81 10 14

NAVSEA Report No. S555-79  
June 1981

LASER TRANSFORMATION HARDENING  
OF FIRING ZONE CUTOUT CAMS

FINAL REPORT

A Project of The  
Manufacturing Technology Program  
Naval Sea Systems Command

by

Robert W. Lowry

NAVAL SURFACE WEAPONS CENTER  
Dahlgren, Virginia 22448      Silver Spring, Maryland 20910

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

14 REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER NAVSEA -S555-79	2. GOVT ACCESSION NO. AD-A305498	3. RECIPIENT'S CATALOG NUMBER 9
4. TITLE (and Subtitle) LASER TRANSFORMATION HARDENING OF FIRING ZONE CUTOUT CAMS	5. TYPE OF REPORT & PERIOD COVERED Final	
7. AUTHOR(s) Robert W. Lowry	6. PERFORMING ORG. REPORT NUMBER	
9. PERFORMING ORGANIZATION NAME AND ADDRESS Naval Surface Weapons Center (G53) Dahlgren, VA 22448	8. CONTRACT OR GRANT NUMBER(s)	
11. CONTROLLING OFFICE NAME AND ADDRESS Naval Sea Systems Command (05R) Washington, DC 20362	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS DNS 0055	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) 12 41	12. REPORT DATE Jun 1981	
	13. NUMBER OF PAGES 43	
	15. SECURITY CLASS. (of this report) UNCLASSIFIED	
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Laser Transformation Hardening Cams		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) This manufacturing technology (MT) project developed techniques to use laser transformation hardening to replace cyanide salt bath nitriding to case harden firing zone cutout cams for the Mk 10 Guided Missile Launcher System (GMLS). These cams, machined of 4340 steel, satisfactorily meet the manufacturing requirements of a case depth of 0.010-0.020 in. and a hardness of Rc 55-67, with minimal distortion, after undergoing laser hardening. The laser transformation, utilizing a beam oscillator and numerical control		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE  
S/N 0102-LF-014-6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

391340

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. ABSTRACT (Continued)

stepping procedures to minimize heat buildup, produces a very fine martensitic structure that is hard, typically  $R_C$  62. This hardness is reduced somewhat in the beam overlap regions, but this factor is compensated for by cam pre-heat treatment and sufficient overlap of laser beam passes. The cost of laser hardening is estimated at less than 10 percent of the cost of cyanide nitriding.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)


FOREWORD

The project reported herein was sponsored by Naval Sea Systems Command, Manufacturing Technology Office (NAVSEA 05R2). The work was funded under Project 4038-79, DNS 555. The purpose of the undertaking was to reduce the cost of surface hardening by developing laser transformation hardening as a replacement for the nitriding process. This project was demonstrated on the firing zone cutout cam of the Mk 10 Guided Missile Launching System (GMLS), but opens the door for laser treating a host of other naval surface weapons and components with the potential for additional cost savings and technological advantages.

The author wishes to acknowledge the following persons for their technical assistance: Robert Retter and Emmett Staples for metallographic analysis and Earl Baird for background information and hardware assistance.

This report has been reviewed and approved by Jerry Hall, Head, Materials Science Branch; Dr. John Thompson, Manufacturing Technology Program Manager; and David Malyevac, Head, Survivability and Applied Sciences Division.

Released by:



CAPT R. P. FUSCALDO

Assistant Head for Weapons Systems  
Weapons Systems Department

SEARCHED  
SERIALIZED  
INDEXED  
FILED  
MAY 1979  
AL

## EXECUTIVE SUMMARY

This manufacturing technology (MT) project developed techniques to use laser transformation hardening to replace cyanide salt bath nitriding to case harden firing zone cutout cams for the Mk 10 Guided Missile Launcher System (GMLS). These cams, machined of 4340 steel, satisfactorily meet the manufacturing requirements of a case depth of 0.010-0.020 in. and a hardness of  $R_C$  55-67, with minimal distortion, after undergoing laser hardening. The laser transformation, utilizing a beam oscillator and numerical control stepping procedures to minimize heat buildup, produces a very fine martensitic structure that is hard, typically  $R_C$  62. This hardness is reduced somewhat in the beam overlap regions, but this factor is compensated for by cam preheat treatment and sufficient overlap of laser beam passes. The cost of laser hardening is estimated at less than 10 percent of the cost of cyanide nitriding.

CONTENTS

	<u>Page</u>
FOREWORD . . . . .	v
EXECUTIVE SUMMARY . . . . .	vii
INTRODUCTION . . . . .	1
OBJECTIVE . . . . .	1
BACKGROUND . . . . .	1
APPROACH . . . . .	4
MATERIALS . . . . .	5
BASICS OF LASER HEAT TREATMENT . . . . .	6
EQUIPMENT AND PROCEDURE DEVELOPMENT . . . . .	9
RESULTS . . . . .	11
SUMMARY . . . . .	11
METALLURGICAL ANALYSIS . . . . .	12
Hardness . . . . .	12
Metallography. . . . .	14
TOLERANCE CONTROL . . . . .	18
WEAR TEST . . . . .	22
CORROSION TEST . . . . .	24
ADVANTAGES OF LASER PROCESSING . . . . .	25
Cost Analysis. . . . .	25
Applicability of Laser Processing to Other Navy Programs . . . .	27
CONCLUSIONS . . . . .	28
RECOMMENDATIONS . . . . .	28
REFERENCES . . . . .	29
DISTRIBUTION	



LIST OF FIGURES

<u>Figure</u>		<u>Page</u>
1	Photograph of Mk 10 Firing Zone Cutout Cam . . . . .	1
2	Photograph of USS BELKNAP (CG 26) Showing Mk 10 Terrier Launcher (Encircled) . . . . .	2
3	Illustration of Missile Being Fired to Clear Ship Superstructure (DDG 37 Class) . . . . .	2
4	Illustration of Cam Contour . . . . .	3
5	Typical Firing Cutout Zone . . . . .	3
6	Schematic Illustration of Regions of Laser Power Density and Interaction Time . . . . .	7
7	General Concept of Laser Heat Treating by the Use of Oscillating Laser Beam . . . . .	7
8	Laser Heat-Treating Patterns . . . . .	8
9	Laser Beam Step Pattern . . . . .	10
10	Hardness Profile, 4340 Steel . . . . .	12
11	Laser-Treated Cam (Defocused Beam, 0.100-in. Passes) . . . .	13
12	Laser-Treated Cam (Oscillated Beam, 0.300-in. Passes) . . .	14
13	Laser-Treated Cam Cross Section (Multiple Oscillated Passes, 4340 Steel) . . . . .	15
14	Laser-Treated Cam Cross Section (Multiple Passes, Defocused Beam, No Oscillation, 4340 Steel) . . . . .	15
15	Laser-Transformation-Hardened Cam (Approximately 0.017-in. Penetration, 4340 Steel) . . . . .	16
16	Laser-Treated Cam Bevel (Approximately 0.020-in. Penetration) . . . . .	16
17	Overlap of Two Laser Passes Using Beam Oscillator . . . . .	17
18	Laser-Transformed 4340 Steel Cam (Microstructure is Fine Martensite) . . . . .	17
19	Cam Follower Used on the Mk 10 Type Firing Cutout Cam . . .	22
20	Photograph of Wear Test Setup Showing Laser-Treated Cam (Right) and Nitrided Cam (Left) . . . . .	22
21	Photograph of Wear Test Setup Showing Follower for the Laser-Treated Cam . . . . .	23
22	Cam Sections After 48-Hour Salt-Spray Test . . . . .	24
23	Cam Sections After 48-Hour Salt-Spray Test (Reverse of Figure 22) . . . . .	24

LIST OF TABLES

<u>Table</u>		<u>Page</u>
1	Typical Chemical Compositions (Percent Weight) of Cam Steels . . . . .	5
2	Nitride Versus Laser Treatment (Batch of Four Cams) . . . . .	10
3	Cam Tolerance Chart . . . . .	19
4	Cam Tolerance Summary . . . . .	21
5	Economic Analysis . . . . .	27

## INTRODUCTION

### OBJECTIVE

The technical objective of this project was to develop production methods for laser processing as an alternative to nitriding as a means of surface hardening firing zone cutout cams for the Mk 10 Guided Missile Launcher System (GMLS). A coincident objective was to reduce the cost of the hardening process, while meeting cam surface requirements. The surface requirements are a case depth of 0.010-0.020 in. and a hardness of  $R_c$  55-67 with minimal distortion.

### BACKGROUND

The Naval Surface Weapons Center (NSWC) is currently the design agent for the Mk 10 GMLS firing zone cutout cam (see Figure 1). These items are used aboard ship to confine launcher azimuth and elevation angles in order to prevent firing the missile toward ship structures. Figures 2-5 help illustrate the cam function. Figure 2 is a photograph of the USS BELKNAP (CG 26), which has a Terrier missile launcher (encircled) that uses the Mk 10 firing zone cutout cam. Figure 3, a schematic of a DDG 37 class ship, shows a missile being launched to avoid the ship's superstructure. Figure 4 provides an example of cam contour, while Figure 5 provides a schematic of a typical firing cutout zone. The contour of the cam corresponds to the nonfiring zone profile that is configured to the layout of the ship superstructure. A cam follower (contact pin), when in contact with the cam, tells the launcher not to fire.

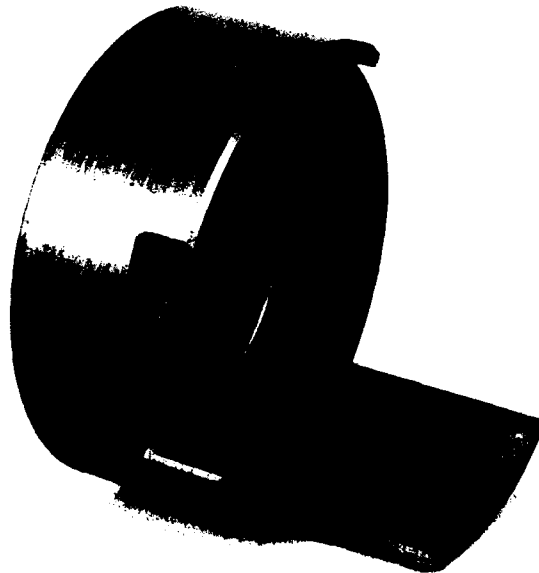


Figure 1. Photograph of Mk 10 Firing Zone Cutout Cam



Figure 2. Photograph of USS BELKNAP (CG 26)  
Showing Mk 10 Terrier Launcher (Encircled)

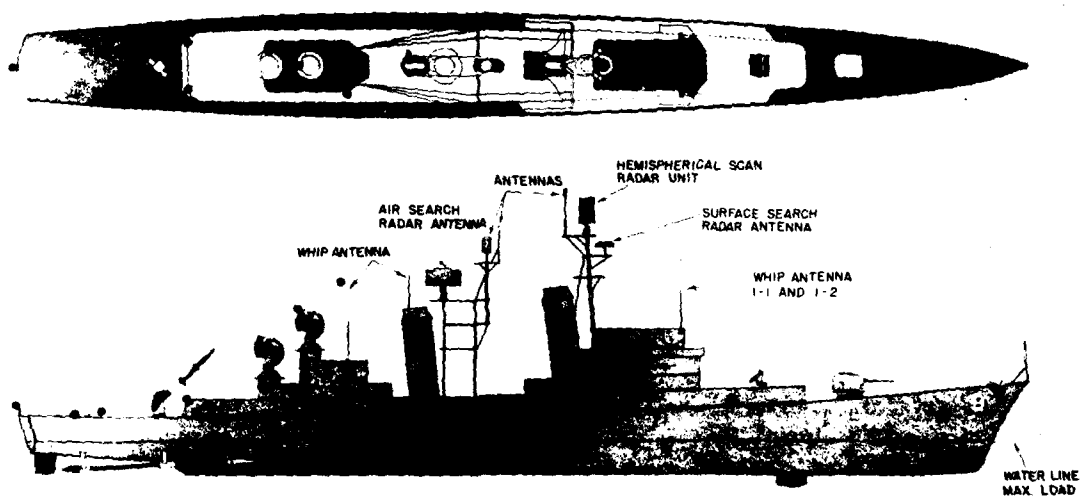


Figure 3. Illustration of Missile Being Fired to Clear  
Ship Superstructure (DDG 37 Class)

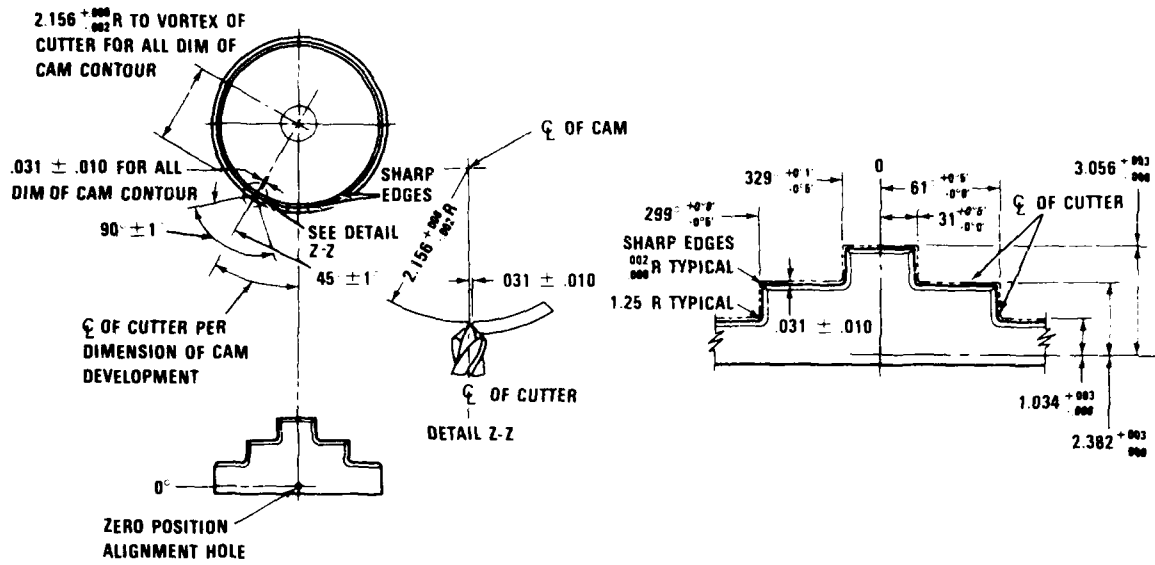


Figure 4. Illustration of Cam Contour

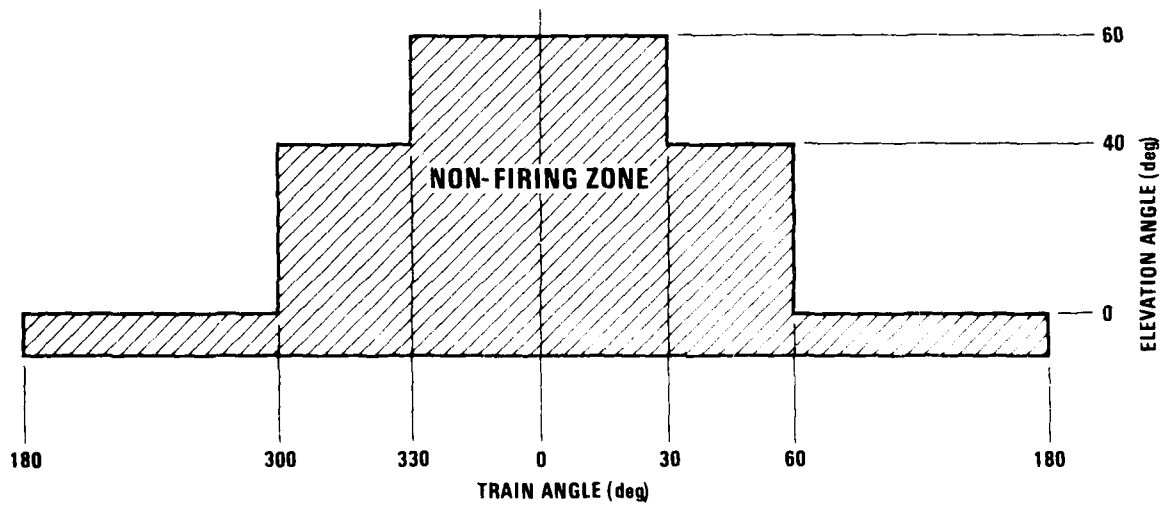


Figure 5. Schematic Illustration of Typical Firing Cutout Zone

The final step in cam manufacture is case hardening. The required quick turnaround (to meet fleet/ship requirements and schedules) is presently being performed by a cyanide salt bath nitriding processing of nitralloy steel cams. This process produces a 55-60  $R_c$  hardness and a case depth of 0.010 in. The requirements are a 55-67  $R_c$  hardness and a case depth of 0.010-0.020 in. One set of two cams has been hardened approximately every 60 days. This method (based on 12 cams/year) costs over \$18K per year, which includes the high cost of disposing of toxic cyanide salt waste (\$6K/yr) and the total energy consumption of the 60-kW salt bath (\$3K/yr) for this energy-intensive operation. These costs are based upon historical data from the 1970s. On a 12 cam/year basis, today's costs would be even higher.

A more cost-effective and less energy-consuming method for surface hardening these parts is laser hardening, which has recently been proven as a practical industrial tool in the manufacture of automobile engine camshafts, gears, and bearing surfaces.<sup>1,2,3</sup> The laser provides very low operating and maintenance costs compared to salt bath nitriding. Specifically, the laser in this application uses approximately 0.29 percent of the electrical energy of the cyanide salt bath. Furthermore, thicker case depths than those being obtained by nitriding are possible by laser hardening.

#### APPROACH

Originally, it was planned to use the 20-kW laser at the Naval Research Laboratory (NRL) to conduct the surface transformation hardening studies. However, after conducting a preliminary study on nitralloy steel using the NRL laser, it was learned that, because of commitment to other studies, turnaround time and scheduling would be a significant problem. Therefore, it was decided to use a laser from a private contractor. One advantage of this decision will be an early involvement of industry in the manufacturing process. It was also decided, after discussion with Laser Applications Inc., Baltimore, Maryland, that a smaller laser would be sufficient to do the job and that they could satisfy the Navy's cost and turnaround time requirements.

Studies were then initiated using Laser Application's 1.25-kW laser to perform the surface transformation hardening of cams. These studies were directed at determining the effects of laser power (beam intensity), dwell time, cam rotation speed, beam width, and beam oscillation on cam surface hardness and case depth. Hardness measurements were made and samples metallographically examined to assure that the cam cross sections are metallurgically sound and wear resistant. Wear tests, corrosion tests, and tolerance studies were conducted to obtain backup data to assure cam performance, reliability, and laser process repeatability.

It is anticipated that the laser transformation hardening production method will be implemented following completion of this manufacturing technology program. Laser equipment at Laser Applications, Inc., may be used. It is anticipated that 12 cams per year will be manufactured for approximately eight more years.

## MATERIALS

Four steels were considered suitable for laser transformation hardening to the desired hardness: nitralloy 135 modified, 4340, 1045, and 11L41 steels. The chemical compositions of these steels are shown in Table 1. The nitralloy 135 modified steel was examined early in the program because of its immediate availability as the current nitriding steel on stock. This material was found to be unsuitable because of surface eruptions and roughness upon laser impingement. AISI 4340 steel was selected because of hardenability, contractor experience, and surface smoothness after laser transformation hardening. The 1045 steel was selected as a low-cost alternative to 4340, and 11L41 was considered as a relatively low-cost material with good machinability.

Table 1. Typical Chemical Compositions (Percent Weight) of Cam Steels

Element	Nitralloy	AISI		
	135 Mod	4340	1045	11L41
Carbon	0.41	0.40	0.45	0.41
Manganese	0.55	0.70	0.75	1.50
Silicon	0.30	0.30	0.22	
Chromium	1.60	0.80		
Aluminum	1.00			
Molybdenum	0.35	0.25		
Nickel		1.85		
Phosphorus	0.04 max.	0.04 max.	0.04 max.	0.04 max.
Sulphur	0.05 max.	0.05 max.	0.05 max.	0.08-0.13
Lead				0.25

The two primary steels (4340 and 1045) were laser treated in both the as-received (hot rolled) and the heat-treated (called "preheat treatment" throughout the text) conditions. Preheat treatment is required to obtain proper hardness for the cam hobs. In addition, preheat treatment helps reduce the effect of tempering, which occurs at overlapping laser beam passes, and helps reduce warpage during laser heat treatment.

Important material properties for laser surface hardening are density, specific heat, thermal conductivity, and thermal diffusivity. Approximate property values for the steels tested are as follows:

- Density = 7.87 g/cc
- Specific Heat = 0.11 cal/g·°c

- Thermal Conductivity =  $9.7 \times 10^{-2}$  cal/cm·s·°c
- Thermal Diffusivity\* =  $0.21$  cm<sup>2</sup>/sec

These values determine depth of penetration and will not be discussed in detail here but are covered in the literature.<sup>4</sup>

#### BASICS OF LASER HEAT TREATMENT

LASER is an acronym standing for Light Amplification by Stimulated Emission of Radiation. Important laser properties are listed below.

1. Monochromaticity. Light energy from a laser is produced at a much narrower bandwidth and at a considerably higher intensity than energy produced by other light sources.

2. Coherence. Waveforms are regular and predictable with the same frequency, phase, amplitude, and direction.

3. Divergence. Waveforms are very parallel and, thus, energy remains intense over long distances.

4. Intensity. Output from well-collimated laser light can be focused to a very small spot with high energy concentration.

Regions of laser operations with regard to power density and interaction time is illustrated in Figure 6. The power required for laser hardening (heat treating) is in the region of  $10^3 - 10^5$  W/cm<sup>2</sup>. An interaction time on the order of  $10^{-1} - 10^{-2}$  sec is necessary.

The general concept of laser heat treating by the use of oscillating laser beams is illustrated in Figure 7. In this procedure, the laser beam is oscillated back and forth as the material is rotated or translated to provide a wider area of heat treatment. The material is heated very quickly above the transformation temperature (of a hardenable steel or alloy) and self-quenches rapidly to produce a largely martensitic (hard) microstructure.

---

\* Thermal diffusivity is thermal conductivity x heating rate. The value shown is for a composition close to that of 4340 steel.



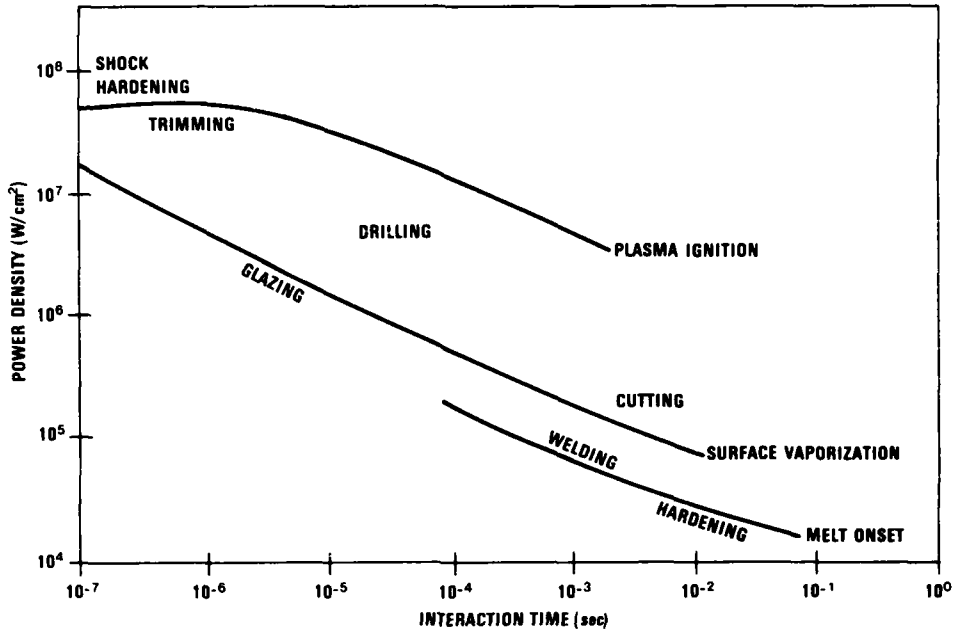


Figure 6. Regions of Laser Power Density and Interaction Time\*


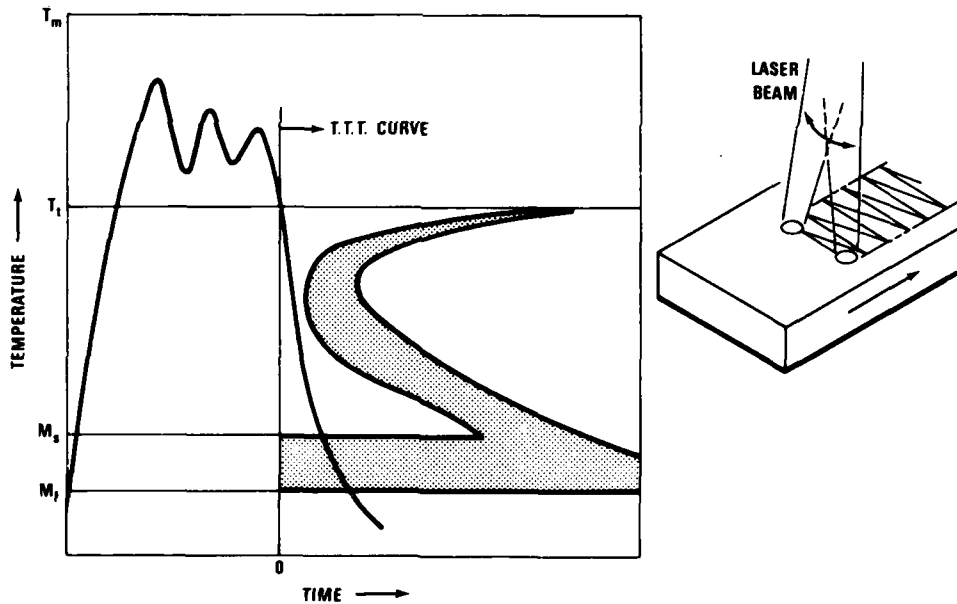



Figure 7. General Concept of Laser Heat Treating by the Use of Oscillating Laser Beam\*

\* Reprinted, with permission, from *Electro-Optical Systems Design* (Nov. 1976, pp. 25-28), Milton S. Kiver Publishers, Inc., Chicago, Il.


Laser heat-treating patterns are shown in Figure 8 for (a) defocused beam, single pass, (b) defocused beam, overlapping passes, and (c) oscillating beam, single pass. It should be noted that there is a small over-tempered zone of a few thousandths of an inch wide at the periphery of a pass and at the interface between two passes. These overlapping areas will be discussed in more detail with reference to the cams in a later section.

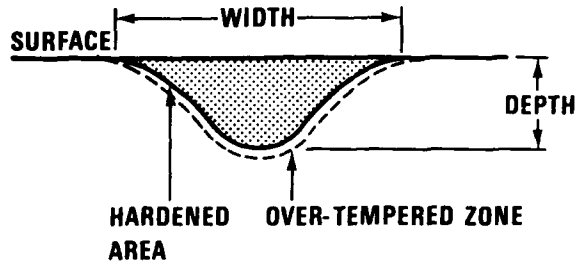

a. **DEFOCUSED BEAM, SINGLE PASS**

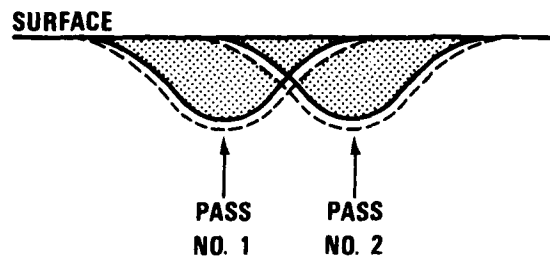

b. **DEFOCUSED BEAM, OVERLAPPING PASSES**

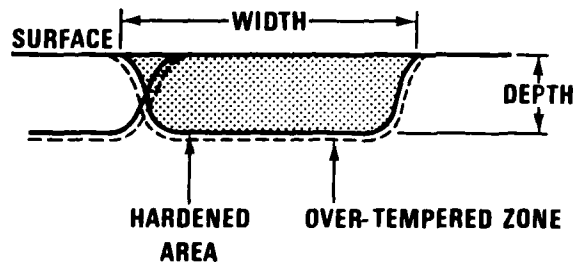

c. **OSCILLATING BEAM, SINGLE PASS**

Figure 8. Laser Heat-Treating Patterns\*

\* Reprinted, with permission, from *Electro-Optical Systems Design* (Nov. 1976, pp. 25-28), Milton S. Kiver Publishers, Inc., Chicago, Il.

## EQUIPMENT AND PROCEDURE DEVELOPMENT

Three basic pieces of equipment were used in conjunction with the tooling and fixtures required to manipulate the cam during heat treatment: (1) a 1.25-kW CO<sub>2</sub> laser (10.6- $\mu$ m wavelength) and (2) a laser beam oscillator (Model 447), both manufactured by Photon Sources, Inc.; and (3) a computerized numerical control (CNC) unit produced by Aerotech, Inc. The laser, of course, is the heat source, the oscillator provides rastering of the beam, while the CNC unit provides programmable automatic rotation and stepping of the cam.

Three different methods were tried in the development of the laser heat treatment of the cam:

1. Defocused beam with manual tilt (45°) for bevels
2. Focused beam with oscillation
3. Focused beam with oscillation; cam stepped with the CNC unit

The first method did not employ the laser beam oscillator and required a 45° manual tilt of the cam in order to harden the beveled surface of the cam. Although the heat treatment/hardening results were acceptable using this method, the manual tilt required time and precision in alignment of the laser beam on the beveled surface. Also, without oscillation, more laser passes were required to heat treat the cam outer surface than with the wider laser passes obtained with the oscillated beam (methods two and three). The width of the oscillated passes was approximately 0.25 in. compared to 0.10 in. for the non-oscillated beam. The use of oscillation in the second method eliminated the tilt and decreased the operation time. Use of an aluminum insert heat sink with thermal coat was required to reduce heat buildup and control distortion in the relatively thin-walled (approx. 0.33 in.) cam. The third and final method employed stepping the cam with the CNC unit to further control heat input distortion especially on the highest lip of the cam. This required programming of the CNC unit. Stepping of the cam is illustrated in Figure 9, a schematic of the cam showing the laser passes--lined off and numbered in order of the stepping sequence.

A comparison of the steps in nitride versus laser treatment for a batch of four cams is provided in Table 2. The time-consuming factors for the nitride process are the startup and shutdown of the salt bath, disposal of cyanide salt wastes, and the actual 24-hour nitride heat treatment itself. The most time-consuming task unique to the laser process is the preparation and checkout of the CNC computer program (2 hours). The total time for the nitride process is two weeks (including startup and shutdown) while that for the laser operation totals 10 hours (including transportation to laser). The laser surface treatment requires about 15 minutes to conduct per cam, which includes 5-7 minutes dwell time for the laser. Therefore, the actual run time for the laser is only 8-10 minutes per cam (32-40 minutes per batch of four cams). The salt bath operates at 60 kW while the laser operates at 1 kW. Therefore, the nitride process uses approximately 345 times the kilowatt-hours compared to the laser.

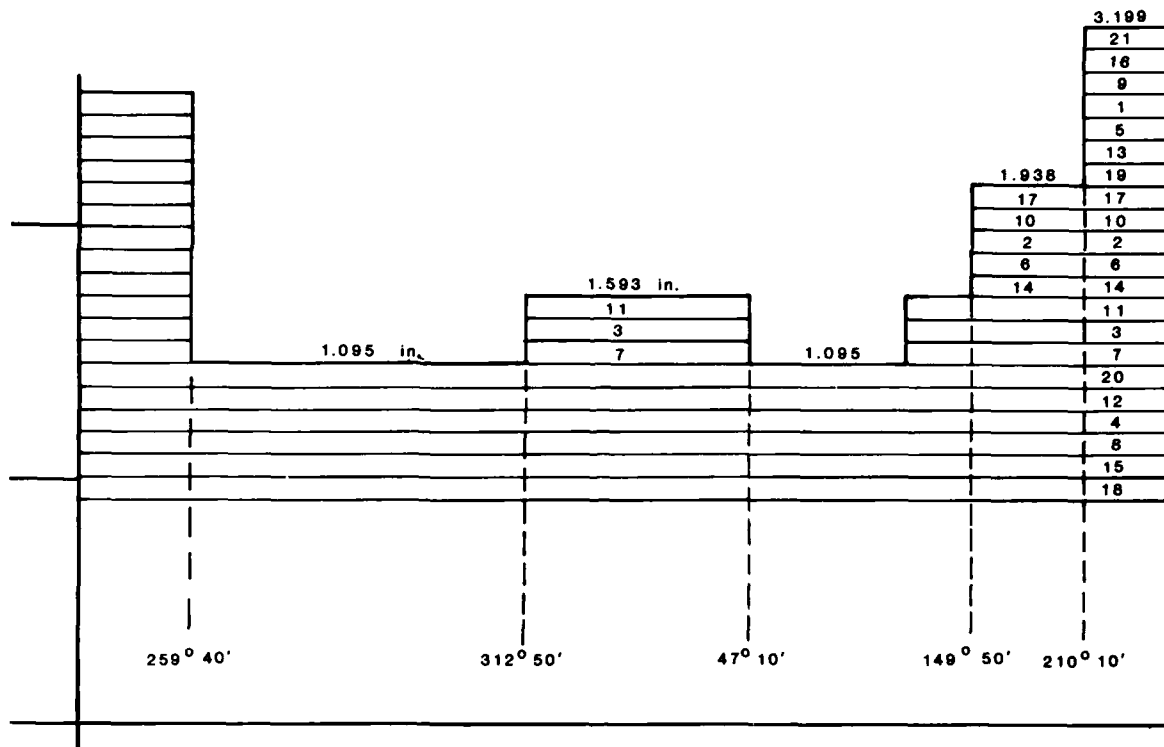


Figure 9. Laser Beam Step Pattern (Sequence)

Table 2. Nitride Versus Laser Treatment  
(Batch of Four Cams)

Nitride	Laser Treatment
<ul style="list-style-type: none"> <li>• Clean cams</li> <li>• Preheat treat cam</li> <li>• Mask off hobs</li> <li>• Prepare cyanide salt bath</li> <li>• Nitride (24 hr/batch of four cams)</li> <li>• Clean cams (shot peen)</li> <li>• Check case depth</li> <li>• Check case hardness</li> <li>• Shut down salt bath</li> <li>• Cyanide salt waste disposal</li> <li>• Gage cams</li> </ul>	<ul style="list-style-type: none"> <li>• Clean cams</li> <li>• Preheat treat cam</li> <li>• Check out parameters (power, mode, etc.)</li> <li>• Prepare and check computer program</li> <li>• Insert heat sink into cam</li> <li>• Spray graphite coating</li> <li>• Set beam oscillator parameters</li> <li>• Laser surface treatment (~15 min./cam)</li> <li>• Clean cam (wipe off)</li> <li>• Check hardness</li> <li>• Check case depth</li> <li>• Gage cams</li> </ul>
Total time 2 weeks	Total time 10 hours

It should be noted in Table 2 that a carbon spray coating was applied to the cam surface to provide heat coupling for the laser energy to the steel. Otherwise most of the light (approximately 90 percent) would be reflected and not absorbed.

Laser characteristics and parameters are listed below.

- Power: 1000 W
- Standoff: 8.75 in.
- Spot size: ~ 0.070 in.
- Focal length: 7.5 in.
- Rotation rate: 30 in./min.
- Oscillator rate: 100 Hz, 2 V, sine wave
- Scan length: 0.250 in.
- CNC program: 17-21 steps
- Run time: 15 min. (approx.)

Included in this list are the oscillator parameters. These parameters applied to the cams produce the results described in the next section. These are the final process parameters after process development. These parameters were varied over a considerable range during development.

## RESULTS

### SUMMARY

A summary of the results is provided below.

- Hardness: Profile = 62  $R_C$ ; Overlap = 51  $R_C$  (very narrow band)
- Depth: Profile = 0.015-0.017 in.; Overlap = 0.009-0.010 in.  
(Can get 0.025 to 0.030 in. with more heat but with warpage and melt)
- Tolerance: Within 4 min. train } Acceptable  
Within 0.001 in. elevation }
- Microstructure: Highly refined martensite
- Wear: ~0.0001 in.

The results show that the requirements of  $R_C$  55-67 and 0.010-0.020 in. depth of penetration with minimal distortion can be met. These values represent the best results obtained to date. A larger data base is required to determine the repeatability of tolerance control. This information will be collected on fleet cams as they are processed by laser heat treatment. The microstructure is basically a highly refined martensitic microstructure yielding a hard yet tough microstructure suitable for good wear resistance. The actual wear resistance compares favorably with that of nitrided cams.

Problems encountered in laser heat treatment of cams are (1) somewhat reduced hardness in the narrow overlap bands between laser passes, (2) potential for heat buildup causing tolerance distortion in outer members (lips), and (3) rounding of bevel edges/corners caused by incipient melt, which provides gaging difficulties. Each of these problems was addressed in this project. Tolerance distortion is the most significant problem and will be discussed in detail.

#### METALLURGICAL ANALYSIS

##### Hardness

Hardness results for cams made of 4340 and 1045 steels are compared in Figure 10. Both steels hardened to nearly the same peak hardness ( $R_C$  62) but the 4340 steel hardened more consistently to a greater depth. AISI 4340 steel is a deep-hardening steel and provides a smooth laser-hardened surface.

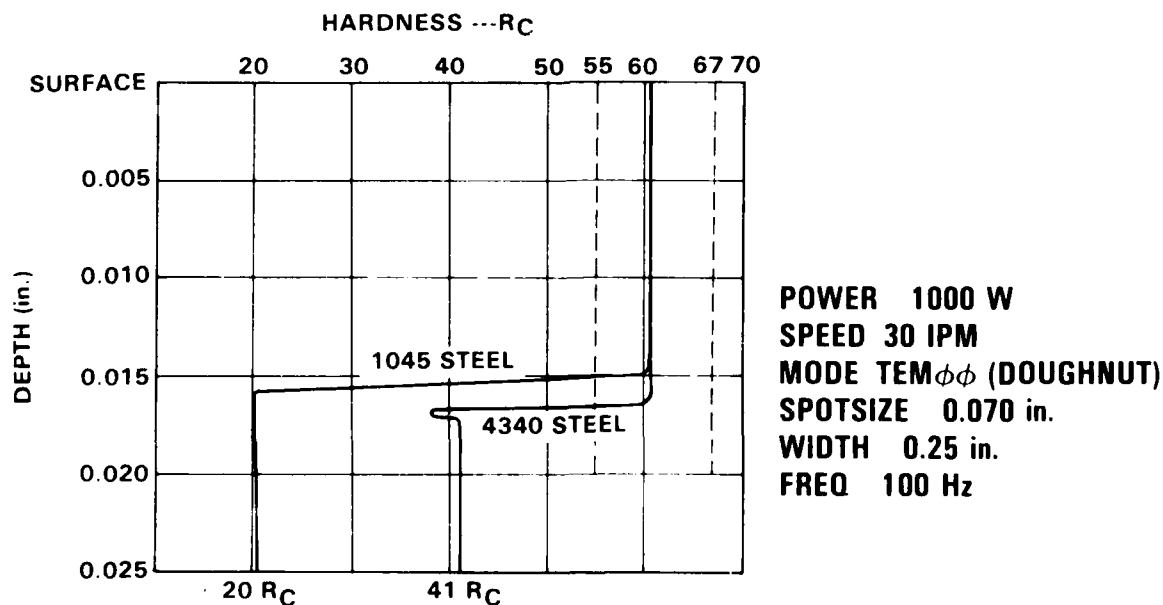


Figure 10. Hardness Profile, 4340 Steel

Initially, one problem encountered in obtaining uniform surface hardness was the overtempered zone or softening that occurs at laser beam interfaces of overlapping passes. These soft zones are very narrow in width (on the order of a few thousandths of an inch wide or a few hundredths of a millimeter). The hardness in these zones varies from 45-54  $R_C$  for the 4340 steel, which was prehardened to 41  $R_C$ . The 1045 steel was not prehardened in this particular case and the overlap hardness dropped off to the base hardness of  $R_C$  20. In another case, the 1045 steel was prehardened to about 35-38  $R_C$  which did improve the soft band hardness somewhat but not to the level of 4340 steel. Another problem with 1045 steel was poor machinability, both in the hot-rolled (as-received) condition and the hardened condition. The 4340 steel was both easier to machine and to laser harden from a penetration and surface-smoothness standpoint. As a result of prehardening and improvements in carbon spray coating, combined with proper laser pass overlapping, the soft bands have been nearly eliminated. They are very difficult to locate with a hardness tester.

Photographs of laser-hardened cams are shown in Figures 11 and 12. The thin lines (indicated by arrows) are the overlap zones between laser passes. Figure 11 shows 0.100-in.-wide (2.54 mm) laser passes without oscillation and Figure 12 shows the wider 0.300-in.-wide (6.4 mm) laser passes with beam oscillation.

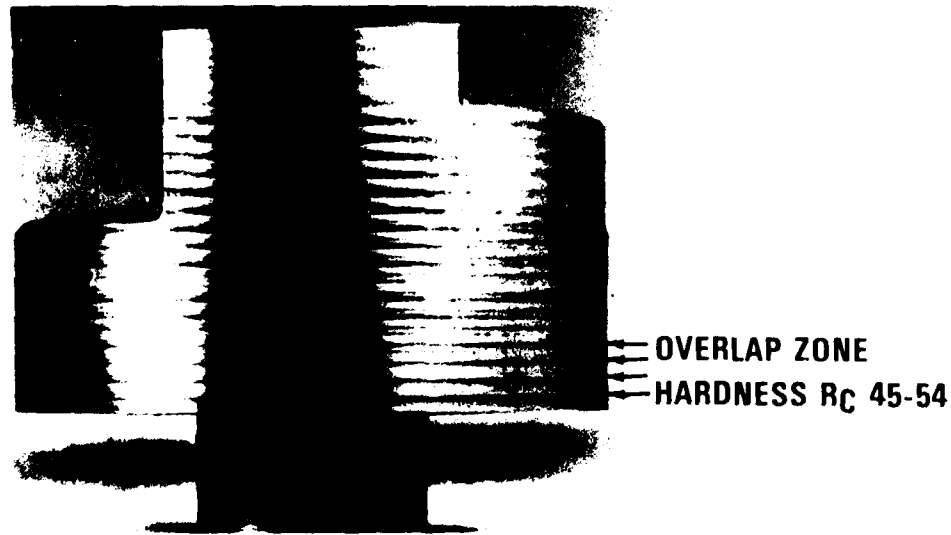


Figure 11. Laser-Treated Cam (Defocused Beam, 0.100-in. Passes)

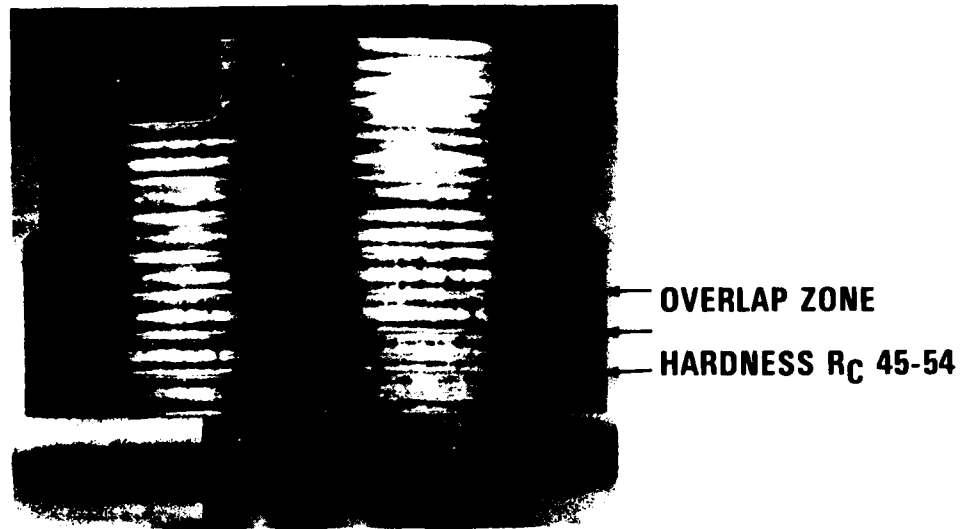


Figure 12. Laser-Treated Cam (Oscillated Beam, 0.300-in. Passes)

### Metallography

Macrographs of cam sections showing laser-hardened zones produced with and without laser beam oscillation are shown in Figures 13 and 14, respectively. Note the excellent coverage of the bevel (right side of macrograph) in Figure 13. The oscillated beams provide wider (plateau-like) and, therefore, fewer passes than the bell-shaped nonoscillated beam. Micrographs are provided in Figures 15-18 and show details of the laser-transformed microstructure. The white zones in Figures 15-17 are the laser-transformed microstructures while the dark zones are the parent metal microstructures. Figure 15 shows a 0.017-in. (0.43 mm) laser-hardened zone on a straight circumferential surface of a 4340 steel cam. Figure 16 shows laser penetration on the corner of a cam at the bevel. Laser penetration at cam corners is extremely good because of the cam geometry. It should be mentioned here that the cam bevels, edges, and corners are very important from a hardness standpoint because of cam follower impingement on them. Figure 17 shows overlap between two laser passes providing good laser coverage at the interface. This interface will possess adequate hardness because of the overlap and depth attained by the laser.



A closeup view of the laser-transformed microstructure is shown in Figure 18. This structure is a very fine tempered martensite with some bainite. This microstructure is very hard and should be durable because of its toughness.

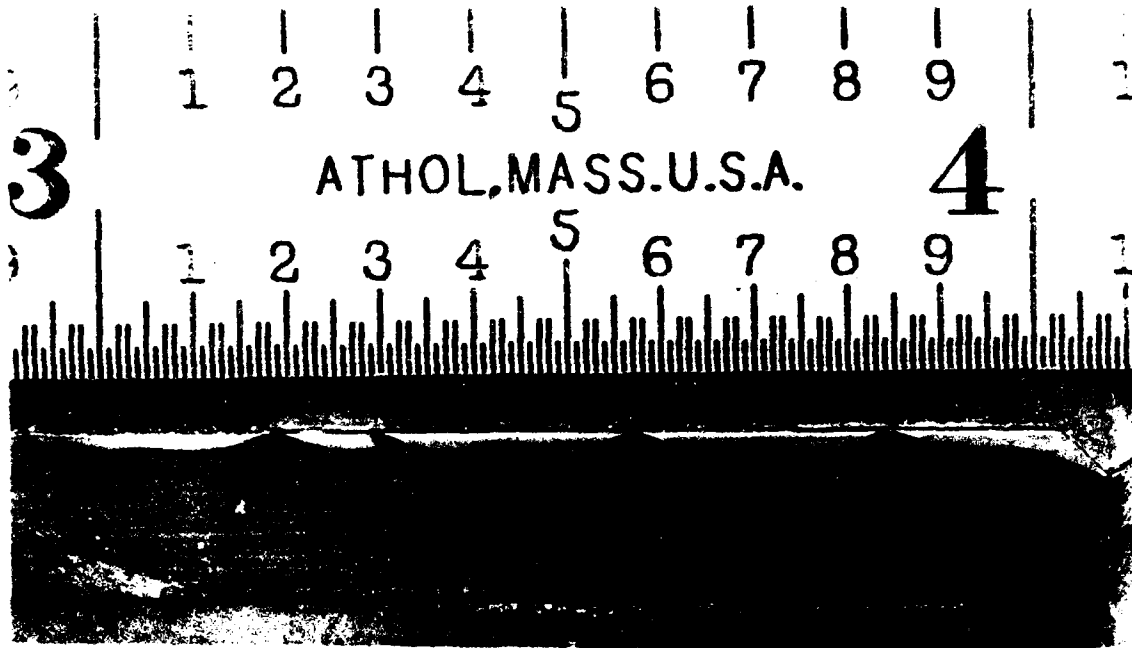


Figure 13. Laser-Treated Cam Cross Section (Multiple Oscillated Passes, 4340 Steel)



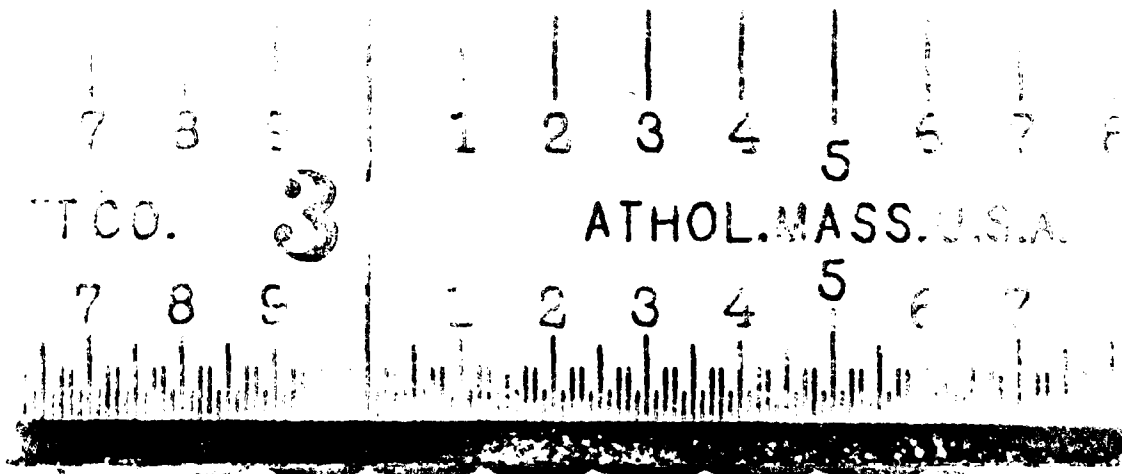


Figure 14. Laser-Treated Cam Cross Section (Multiple Passes, Defocused Beam, No Oscillation, 4340 Steel)

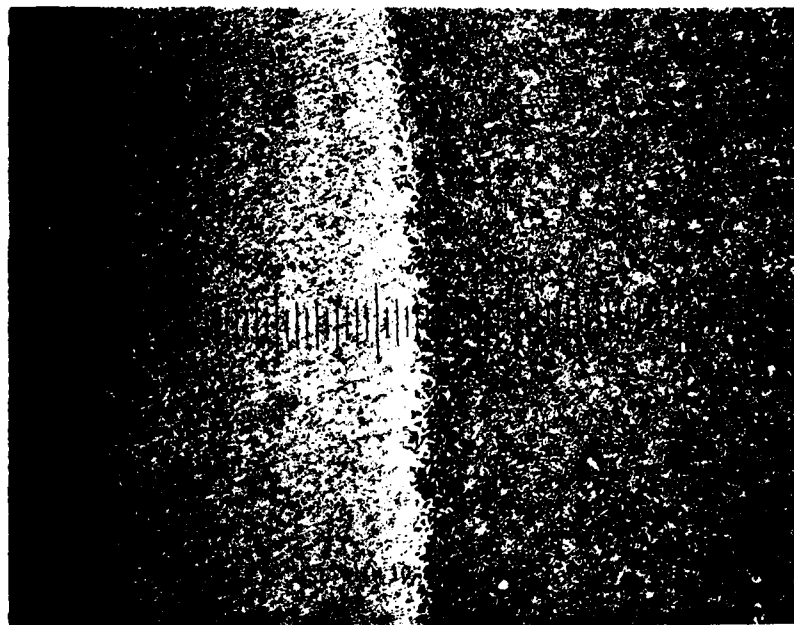


100X

Figure 15. Laser-Transformation-Hardened Cam (Approximately 0.017-in. Penetration, 4340 Steel)

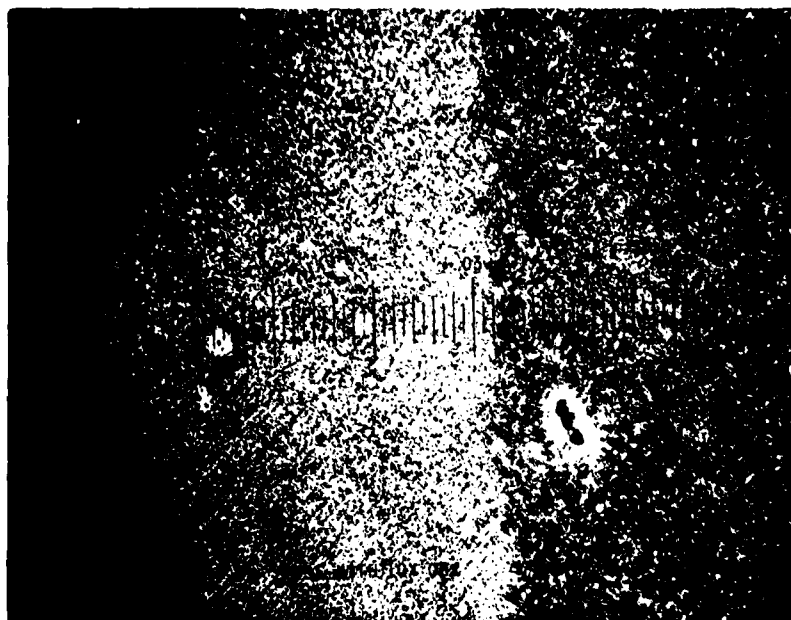


100X

Figure 16. Laser-Treated Cam Bevel (Approximately 0.020-in. Penetration)

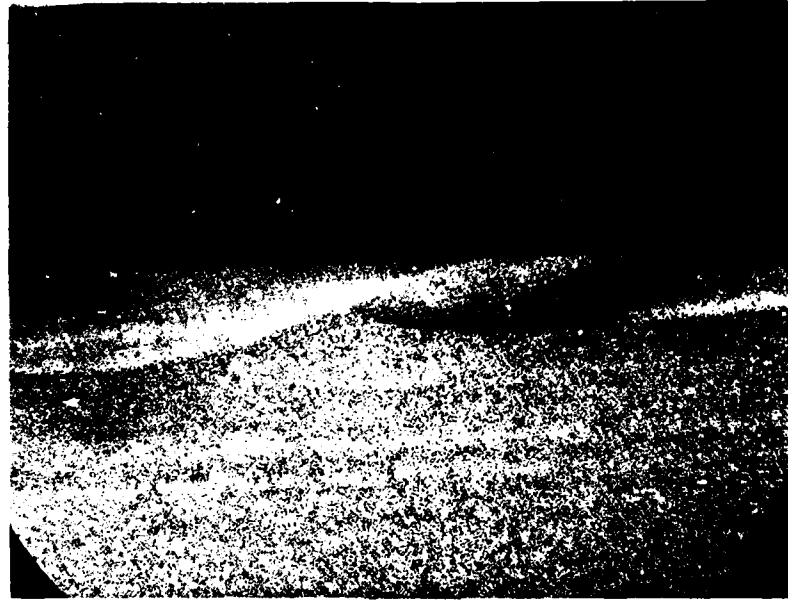

50X

Figure 17. Overlap of Two Laser Passes Using Beam Oscillator

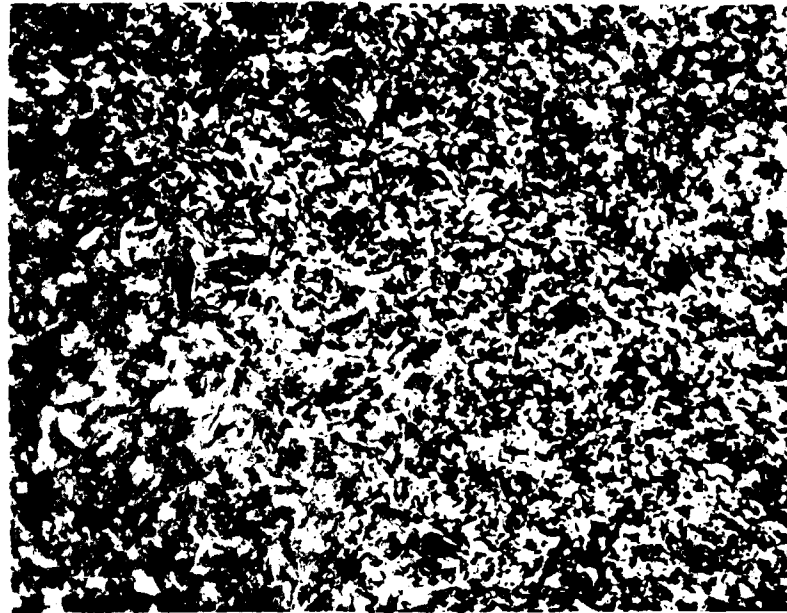

800X

Figure 18. Laser-Transformed 4340 Steel Cam  
(Microstructure is Fine Martensite)

## TOLERANCE CONTROL

One of the problems encountered in laser treating the Mk 10 cams was tolerance distortion caused by heat buildup. This occurred primarily on the high lip of the cam. Also, corners and edges, especially at the bevels and the alignment hole, were rounded because of the high heat intensity, causing difficulties in gaging the necessary dimensions. The distortion occurred as heat gradually built up in the relatively thin cam body as the number of laser passes increased. Heat buildup can more readily cause a problem in the highest lip of the cam where there is only a small amount of mass to dissipate heat. Rounding of corners and bevel edges, caused by incipient melting, occurred because of the effect of laser heat intensity being increased by the edge geometry.

The heat buildup problem in the cam body and high lip was resolved by providing the appropriate dwell time between passes and stepping the laser to distribute the heat from one location to another. Except for the first few passes, which were made without dwells, the dwell time was 30 sec. It was especially important to keep from concentrating heat in the high lip. The second problem, incipient melt, was handled by wiping off the thermal spray coating of carbon precisely on the edges and corners. This reduced the heat intensity on these areas to the appropriate level.

A total of eleven 4340 steel cams were laser processed during the project and were used for tolerance evaluation. Tolerance data are provided in Table 3 and 4. (For an example of measurement locations, see Figure 5.) Cam tolerance requirements are 5 min on the train angles and  $\begin{matrix} +0.003 \\ -0.000 \end{matrix}$  in. on the elevation heights. An additional  $\pm 2$  min for train angle and  $\pm 0.001$ -in. elevation is allowed for operator error in measurement. Observation of Tables 3 and 4 shows that three cams were within or close to the dimensional/tolerance requirements.

Some tolerance distortion and warpage occurred because of the problems already mentioned. It should be mentioned here that rough machining of the cams also is a contributing factor in gaging and tolerance variation. This factor was especially notable for one cam (#10) in which the alignment hole was roughly machined. Additional information on cam tolerances will be collected as cams are produced for the fleet. If any distortion because of heat buildup continues to be a problem, water cooling will be used to reduce overall heat during laser processing. Otherwise, the laser power (wattage) and heat intensity can be reduced somewhat while still achieving surface hardness and penetration depth requirements.

Table 3. Cam Tolerance Chart

Cam Number	Angle (°)	Difference		Requirements		Accept/ Reject (A/R)	
		Train Angle (')	Elevation (in.)	Train Angle (5' ±2)	Elevation (±0.001 oper.)	Train	Elev.
1*	209††	+0.13 (+8)	+0.013	+5	+0.003 -0.000	R	R
(Prehardened** 4340 A-Arm†)	257 323 36	-0.05 (-3) -0.35 (-20) +0.07 (+4)	+0.005 +0.001 0	+5 -5 +5		R R A	R A A
	150††	-0.27 (-16)	+0.001	-5		R	A
2	209	+12	-0.001	+	-0.000 +0.003	R	A
(Prehardened 4340 B-Arm)	322 37 102	-8 +10 -3	-0.001 +0.005 +0.001	- + -		R R A	A R A
	150	-9	-0.001	-		R	A
3	209	+3	+0.002	+		A	A
(Prehardened 4340 B-Arm)	322 37 101	+9 +6 +8	+0.002 0 +0.001	- + -		R A R	A A A
	150	+5	0	-		R	A
4	209	+2	+0.003	+		A	A
(Prehardened 4340 A-Arm)	257 322 37	+3 +2 -2	+0.004 +0.001 +0.002	+ - +		A A A	A A A
	150	0	0	-		A	A
5	209	+6	+0.006	+		A	R
(Prehardened 4340 A-Arm)	257 322 37	+11 +5 -2	+0.007 +0.004 +0.001	+ - +		R R A	R A A
	150	-4	+0.002	-		A	A
6	209	-3	-0.001	+		R	A
(Prehardened 4340 B-Arm)	322 37 102	+4 +1 +1	0 0 0	- + -		R A A	A A A
	150	+3	0	-		R	A

\* There were no cams numbered 8 and 9.

\*\* As a result of preliminary laser processing studies, it was determined that the cams must be prehardened by conventional heat treatment in order to prevent/reduce soft zones at the laser pass overlap interfaces.

† A-Arm and B-Arm designate two different cam configurations. There is a pair of cams (an A- and B-Arm) on each ship with two launchers.

†† The 209° and 150° angles include the high lip, which poses the most difficult tolerance control.

Table 3. Cam Tolerance Chart (Continued)

Cam Number	Angle (°)	Difference		Requirements		Accept/ Reject (A/R)	
		Train Angle (')	Elevation (in.)	Train Angle (5' ±2)	Elevation (±0.001 oper.)	Train	Elev.
7  (Unhardened 1045 B-Arm)	209	-8	-0.006	+	-0.000 +0.003	R	R
	322	-2	-0.007	-		A	R
	37	-2	-0.007	+		A	R
	102	-4	-0.006	-		A	R
	150	-3	-0.008	-		A	R
10  (Prehardened 4340 B-Arm)	209	-11	-0.003	+	+0.003 -0.000	R	R
	322	+4	+0.001	-		R	A
	37	+3	+0.001	+		A	A
	102	-3	-0.002	-		A	R
	150	-10	-0.004	-		R	R
11  (Prehardened 4340 B-Arm)	209	-3	0	+		R	A
	322	+3	0	-		R	A
	37	+1	0	+		A	A
	102	+1	0	-		A	A
	150	0	0	-		A	A
12  (Prehardened 4340 A-Arm)	209	-5	+0.006	+		R	R
	259	0	+0.008	+		A	R
	312	+2	+0.004	-		A	A
	47	-9	0	+		R	A
	150	-9	+0.004	-		R	A
13  (Prehardened 1045 A-Arm)	210	-11	+0.002	+		R	A
	259	-3	-0.002	+		R	R
	313	-2	-0.005	-		A	R
	47	-9	-0.003	+		R	R
	150	-8	-0.007	-		R	R

\* There were no cams numbered 8 and 9.

\*\* As a result of preliminary laser processing studies, it was determined that the cams must be prehardened by conventional heat treatment in order to prevent/reduce soft zones at the laser pass overlap interfaces.

† A-Arm and B-Arm designate two different cam configurations. There is a pair of cams (an A- and B-Arm) on each ship with two launchers.

†† The 209° and 150° angles include the high lip, which poses the most difficult tolerance control.

Table 4. Cam Tolerance Summary

Cam Number*	Tolerance Evaluation		Comments
	Rating††	Train (')/Elev. (in.) (Total Error)**	
1†	Poor	30/0.012	
2†	Fair	19/0.005	Correct angular direction
3†	Fair	18/0	Gaging shift (angles)
4	Acceptable	0/0.001	
5	Poor	14/0.008	
6	Acceptable	10/0.001	
7 (1045 Steel)	(See Comment)	8/0.019	Pos. Gaging shift (angles and elev.)
10 Demo	(See Comment)	20/0.009	Alignment hole not properly machined.
11	Acceptable	7/0	
12	(See Comment)	20/0.010	Pos. Gaging shift (angles and elev.)
13 (1045 Steel)	(See Comment)	26/0.017	Gaging shift (angles and elev.)
		Acceptable 10/0.005 Error	

\* There were no cams numbered 8 and 9.

\*\* Total error is the sum of the error outside the stringent tolerance control range. The sum is for five train angles and five elevations. The 10' total acceptable error for train angle is the sum of a 2' measurement for each of five angles (2' x 5 = 10'). The 0.005-in. total acceptable error for elevation is the sum of a 0.001 measurement error for five elevations (0.001 in. x 5 = 0.005 in.).

† No attempt was made to control tolerances for the first three cams. These cams were used to develop the laser processing technique and laser parameters. Therefore, by eliminating the first three cams from the data, three out of eight cams were acceptable from a tolerance standpoint. Gaging difficulties or machining quality may have prevented cams numbered 7, 10, 12, and 13 from being acceptable. A larger data base for statistics is needed.

†† The ratings are defined as follows: poor - neither train nor elevation requirements were met; fair - either train or elevation requirements were met; and acceptable - both train and elevation requirements were met.

## WEAR TEST

A wear test was conducted to determine how well the laser surface held up in contact with the cam follower (shown in Figure 19) in comparison with the nitrided surface.<sup>5</sup> Photographs of the wear test setup are shown in Figures 20 and 21. Figure 20 shows the cam follower in contact with the laser-processed cam, while Figure 21 shows the follower free from the cam surface. The test was set up such that the nitrided cam and laser-treated cam were coupled together on a single shaft and were, therefore, rotated together in contact with two cam followers. (The second follower is not visible in the photographs.) The compressive spring force from each follower was calibrated to 4.7 lb prior to placement in contact with the cams. The cams were rotated at approximately 7 rpm for approximately 80 hr providing about 33,600 total revolutions. These test conditions simulated actual operating conditions for the Mk 10 cam and were equivalent to several years of service. (This test was conducted per Reference 5). Cams have an average life of three years and some see as long as six to seven years of service. No cam has worn out to date. Cams are generally replaced when a new configuration is required.

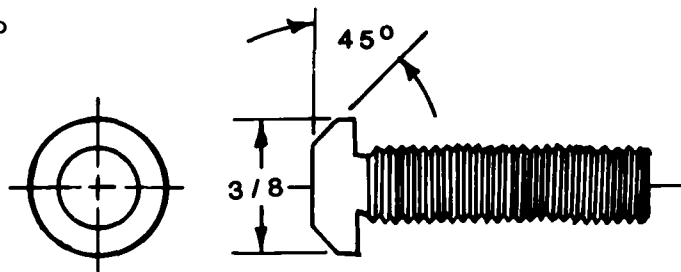


Figure 19. Cam Follower Used on the Mk 10 Type Firing Cutout Cam

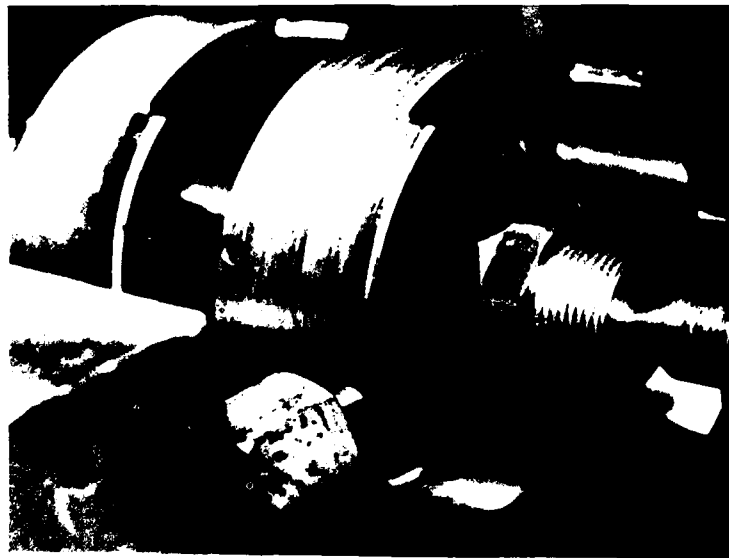


Figure 20. Photograph of Wear Test Setup Showing Laser-Treated Cam (Right) and Nitrided Cam (Left)





Figure 21. Photograph of Wear Test Setup Showing Follower for the Laser-Treated Cam

The most severe wear on the cam occurs at the initial edge of contact between the follower and the cam. This test was designed to represent the repeated movement of the follower over an edge each time the launcher is loaded (really an overtest). The wear at the edge of the cam was of primary importance in this test. This is so because wear at an edge causes tolerance change and therefore a change in cutout zone. The cams were lubricated at the start of the test as they are when first installed in the launcher. The maximum wear for the nitrided cam edges was 0.000070 in. and that for the laser-treated cam was 0.000100 in. These amounts are insignificant over the lifetime of the cams. The fact that the laser-treated cam edge wore more than the nitrided cam edge is attributed to a more roughly machined surface for the laser-treated cam. It should be noted that the cam follower was placed over a laser overlap "soft" zone (which was previously discussed). No wear at this zone could be observed.

## CORROSION TEST

A 48-hour accelerated corrosion salt-spray test was conducted on both nitrided and laser-treated cams and cam sections. Photographs of these sections after salt-spray testing are provided in Figures 22 and 23. Figure 23 simply shows the reverse side of Figure 22. The general result of the accelerated corrosion test was that there was no apparent difference in the corrosion resistance of the five sections shown in Figures 22 and 23. The five sections shown in these figures are nitrided nitralloy steel, parcoluberized-laser-treated 1045 and 4340 steels, and bare-laser-treated 1045 and 4340 steels.



Figure 22. Cam Sections After 48-Hour Salt-Spray Test



Figure 23. Cam Sections After 48-Hour Salt-Spray Test  
(Reverse of Figure 22)

One problem interpreting these results lies in the fact that much of the corrosion was caused by salt-spray runoff or spillage from an area where salt water collected. The corrosion appears worse than it normally would and interferes with proper interpretation. It was expected that the nitrided corrosion resistance would be better than untreated steel (non-nitrided). However, it is obvious that the nitrided cam corrodes.

It should be pointed out that no cams have been replaced due to corrosion or wear. The cams are initially lubricated upon installation in the launcher and are sheltered from seawater spray. In other words, the corrosion environment is not severe. (The corrosion test described herein was an overtest.) At any rate, laser-treated cams should be adequate in such an environment.

#### ADVANTAGES OF LASER PROCESSING

The advantages of laser processing over nitriding of cams are listed below:

1. Shorter times for process/turnaround
2. Lower cost on a quick turnaround basis
3. Better case depth and hardness than salt nitride
4. Deeper penetration on critical bevels and edges
5. No handling of cyanide salt required
6. Less dimensional growth than gas nitride
7. Significantly less energy consumed compared with present bath nitride

#### Cost Analysis

A comparison of costs for three processes is shown below: (based on a batch of four cams, or a total of 12 cams/yr)

- Salt Nitride\*:  
(Present Method)

$$\frac{\$6\text{K/yr (salt disposal)} + \$3\text{K/yr (electricity)} + \$9\text{K/yr (labor)}}{12 \text{ cams/yr}} = \$1500/\text{cam}$$

- Gas Nitride\*: \$1756/bath of four cams = \$439/cam

---

\* The estimate for both nitriding processes are based upon having a dedicated run/heat for a quick response.

• Laser Treatment:

$$\frac{\$680(\text{laser})/\text{day} \times 1/2 \text{ day (laser)} + (3.5 \text{ hr} \times \$50/\text{hr}) \text{ computer and engineering}}{4 \text{ cams}} = \$129/\text{cam}$$

The salt nitride process employs the currently used molten cyanide salt bath at NSWC for a 24-hour period (not including preparation). This process is energy intensive and requires disposal of the toxic salts.

The gas nitride process employs cracked ammonia for a 72-hour period. The cost using a nondedicated furnace at Drever Heat Treaters, Baltimore, Maryland, is currently only about \$50 per cam. However, because of scheduling and time required, this may not always be practical for a quick response required by the fleet. In addition, some dimensional growth can be expected using the gas nitride process (approximately 0.002-in. growth has been experienced in the past). This can be allowed for by proper machining and the gas nitride process is an entirely acceptable backup process.

The CO<sub>2</sub> laser process can be accomplished in 1-1/2 hr per cam, which includes 15 min or less of actual laser time. The laser (1.25 kW) uses tremendously less energy than either of the nitriding processes. The 1.25-kW laser at Laser Applications, Baltimore, Maryland, is available on a quick-response basis and can process a batch of four cams (the usual requirement) in approximately 6 hr. The cost savings using the laser on a quick-response basis is \$1,370 per cam in comparison with the salt nitride and \$310 per cam in comparison with the gas nitride process. A large intangible benefit of the laser hardening process is the elimination of cyanide salt handling and disposal.

A summary of the economic analysis required for the MANTECH program is provided in Table 5. This table shows a projected \$16.4K savings per year in the outyears and a savings (after payback of the initial investment) of about \$80K through FY 1988. (The above cost information in no way binds potential contractors to future prices.)

Table 5. Economic Analysis

	FY 79	FY 80	FY 81	FY 82	FY 83	FY 84	FY 85	FY 86	FY 87	FY 88
A. Scheduled Procurements										
1. Present Method (Nitriding)	12	12	12	12	12	12	12	12	12	12
2. Proposed Method (Laser Hardening)	--	--	12	12	12	12	12	12	12	12
B. Unit Cost—Present Method \$1000 per cam			\$18K	\$18K	\$18K	\$18K	\$18K	\$18K	\$18K	\$18K
C. Unit Cost—Proposed Method \$129 per cam			\$ 1.6K	\$ 1.6K	\$ 1.6K	\$ 1.6K	\$ 1.6K	\$ 1.6K	\$ 1.6K	\$ 1.6K
D. Gross Savings \$1,170 per cam			\$16.4K	\$16.4K	\$16.4K	\$16.4K	\$16.4K	\$16.4K	\$16.4K	\$16.4K
E. Investment—Proposed Method										
1. Manufacturing Technology		\$50.5K								
2. Other	0									
3. Carried Forward	0									
4. Total		\$50.5K								
5. Payback						\$15.1K	\$16.4K	\$16.4K	\$16.4K	\$16.4K

NOTE: Funding received late FY 79.

#### Applicability of Laser Processing to Other Navy Programs

The potential of the laser as applied to processing of naval weapons and components is immense as well as the potential dollar savings using the laser. This is so because of the versatility of the laser (surface hardening, cutting, welding, glazing, alloying, cladding, drilling, softening) and the speed of laser processing. Listed below are several programs and weapons systems and components to which the laser can be applied and which would be a direct outgrowth of this program.

1. Laser processing of Vertical Launch System (VLS) components:
  - Welding of steel plenum and uptake structures, canisters, etc.
  - Heat treatment of cams, bearings, shafts, etc.
  - Cutting and drilling of sheet metal
2. Laser surface treatment of depleted uranium and tungsten penetrators:
  - Glazing to improve penetrator surface resistance to corrosion
  - Hardening to improve penetrator performance
3. Laser transformation hardening of cams, bearings, shafts, etc. for gun mounts (Mk 75-76mm)

4. Laser transformation hardening, alloying, cladding of gun barrels and liners
5. Laser processing of metal matrix composites
6. Laser cutting of Kevlar armor panels and components
7. Laser welding of high-pressure argon/coolant bottles for the 5" Guided Projectile
8. Laser scoring of warheads and projectiles for controlled fragmentation
9. Laser transformation hardening, alloying, and cladding of Terrier and other missile launcher rails

#### CONCLUSIONS

1. Laser surface hardening of Mk 10 cams is both a feasible and economical alternative to cyanide salt bath nitriding. The requirements of 0.010-0.020 in. case depth and hardness of 55-67 R<sub>c</sub> have been easily met or exceeded using the laser.

2. Cam tolerances can be controlled by proper control of laser power and heat input, through rub-off of carbon spray coating on edges, and through water-cooling techniques if needed.

3. Laser processing of cams can be done on a quick-response basis--one day turnaround if needed.

4. Cost savings using the laser process is \$16.4K per year (for 12 cams).

#### RECOMMENDATIONS

1. Generate a producibility data base of laser-hardened cams to implementation of the laser process.

2. Discontinue use of cyanide salt nitride process and place the furnace on surplus.

3. Pursue the vast potential of the laser in processing naval surface weapon systems and components.

#### REFERENCES

1. Jon E. Miller and James A. Wineman, "Laser Hardening at Saginaw Steering Gear," *Metal Progress* (May 1977).
2. Ray Larsen, "GM Buys Power Lasers to Heat Treat Engine Components in Production," *American Metal Market/Metalworking News* (20 September 1976).
3. Richard A. Hella and Daniel S. Granamuthur, "High Power Lasers in Materials Processing," *SPIE*, Vol. 69 (1975).
4. John F. Ready, Editor, *Lasers in Modern Industry*, Published by Society of Manufacturing Engineers (1979).
5. B. C. Fenton and R. W. Lowry, *The Evaluation of Alternate Steels for the GMLS Firing Cutout Cam*, NWL TN-T/1-68 (Dahlgren, Va., March 1968).

DISTRIBUTION

Under Secretary of Defense  
for Research and Engineering  
Pentagon  
Washington, DC 20301  
ATTN: Honorable William J. Perry (Room 3E1006)  
Dr. Arden Bement (Room 3E114)  
Dr. Lloyd Lehn (Room 3D1079)  
Honorable David E. Mann (Room 4E736)

Deputy Under Secretary of Defense  
(Acquisition Policy)  
Pentagon  
Washington, DC 20301  
ATTN: Dale W. Church (Room 3E144)

Defense Industrial Resources Support Office  
Dwyer Building  
Cameron Station  
Alexandria, VA 22314  
ATTN: Charles P. Downer  
Burton E. Bartsch

OSD OUSDRE (ET)  
Pentagon  
Washington, DC 20301  
ATTN: Jerome Push (Room 3D1089)

U.S. Army Development and Readiness Command  
Chief, Office of Manufacturing Technology  
5001 Eisenhower Avenue  
Alexandria, VA 22333  
ATTN: COL John Tipton

Industrial Base Engineering Activity  
Chief, Manufacturing Technology Division  
Rock Island, IL 61201  
ATTN: James Cartens (DRXIB-MT)  
Gordon B. Ney (DRXIB-MT)

U.S. Army Production Equipment Agency  
c/o Rock Island Arsenal  
Rock Island, IL 61201

Office of Assistant Secretary of Navy  
Washington, DC 20360  
ATTN: E. Pyatt (MRA&L)



DISTRIBUTION (Continued)

Naval Material Command  
Director, Manufacturing Technology Program  
Washington, DC 20360  
ATTN: CAPT F. B. Hollick (Code 064)

Officer-In-Charge  
Naval Material Command Industrial Resources Detachment  
Philadelphia Naval Base  
Philadelphia, PA 19112  
ATTN: Bldg. 75-2  
Bldg. 77L

Naval Sea Systems Command  
Washington, DC 20362  
ATTN: RADM W. J. McGarrah (Code 05)  
CAPT M. R. Norby (Code 05R)  
John Freund (Code 05R2)  
Thomas Draschil (Code 05R23)  
Harry B. Byron (Code 05R24)  
RADM C. J. Rorie (Code 06)  
RADM J. K. Nunneley (Code 07)  
Library (09G3)  
G. Brown (62C5)  
W. Heisenbuttel (62Z1C3) (3)

Manufacturing Technology Utilization  
NASA Headquarters  
600 Independence Avenue, SW  
Washington, DC 20030  
ATTN: Ray L. Gilbert

Department of Commerce  
Maritime Administration  
Commerce Building 4610  
Washington, DC 20030  
ATTN: John Garvey

Peterson Builders  
334 South First  
Sturgeon Bay, WI 54235  
ATTN; Elsworth L. Peterson

Bath Iron Works  
Bath, ME 04530  
ATTN: Igo Jekkals

DISTRIBUTION (Continued)

Raytheon Company  
Director, Manufacturing Engineering  
141 Spring St.  
Lexington, MA 02173  
ATTN: Frank McCarty

TRW, Inc.  
Group Vice President for Operations  
23555 Euclide Avenue  
Cleveland, OH 44117  
ATTN: Gus Schrader

American Defense Preparedness Association  
740 15th Street, NW, Suite 819  
Washington, DC 20015  
ATTN: GEN Henry Miley, U.S. Army (Ret)

Department of Industrial and Systems Engineering  
Ohio State University  
1971 Niel Avenue  
Columbus, OH 43210  
ATTN: J. Temple Black

Air Force Materials Laboratory  
Wright-Patterson AFB, OH 45433  
ATTN: James Maltice (AFML/LT)  
Henry A. Johnson (MLTM)

Mcdonnell-Douglas Astronautic Corp.  
Dept. 380, M/S 12-2  
5301 Bolsa Avenue  
Huntington Beach, CA 92647  
ATTN: Jim Ripkin

Naval Air Systems Command  
Washington, DC 20360  
ATTN: Richard Recta (Code 52022)  
(Code 5162C)

Naval Ship Systems Engineering Station  
Philadelphia, PA 19112  
ATTN: Edward Sigal (Code 035)  
Joseph Bloomer (Code 035.1)

Naval Electronics Systems Command  
Washington, DC 20362  
ATTN: Ray Hill (Code 50451)

DISTRIBUTION (Continued)

Martin Marietta Aerospace  
Manager R&D Programs  
6801 Rockledge Drive  
Bethesda, MD 20034  
ATTN: John S. Greene, Jr.

Naval Ocean Systems Center  
San Diego, CA 92152  
ATTN: Richard A. Gamble (Code 9254)

Mr. George Sorkin  
7315 Rebecca Drive  
Alexandria, VA 22307

NMCIRD  
Philadelphia, PA 19112  
ATTN: William J. Welsh

Naval Research Laboratory  
Washington, DC 20375  
ATTN: Dr. R. L. Hettche (Code 6300)

Naval Ship Research and Development Center  
Annapolis, MD 21402  
ATTN: J. Crisci

Naval Material Command  
Washington, DC 20362  
ATTN: D. Carstater (Code 0641)

OC-ALC/MASE  
Tinker AFB, OK 73145  
ATTN: Marvin Williams  
S. D. Tatum

Laser Applications, Inc.  
2058 Lord Baltimore Drive  
Baltimore, MD 21207  
ATTN: R. Ulrich

Office of Naval Material  
800 N. Quincy St.  
Arlington, VA 22217  
ATTN: Dr. Lem Hill (MAT 07)

Defense Technical Information Center  
Cameron Station  
Alexandria, VA 22314

DISTRIBUTION (Continued)

Library of Congress  
Washington, DC 20540  
ATTN: Gift and Exchange Division (4)

GIDEP Operations Office  
Corona, CA 91720

Local:

E  
E13 (Hastings)  
E13 (Walters)  
E13 (Stout)  
E41  
F  
G10  
G20 (Edmonds)  
G20 (Johndrow)  
G20 (Sloop)  
G30  
G40  
G50  
G52 (Thompson)  
G53  
G53 (R. Lowry) (25)  
G53 (Baird)  
G53 (Bettadapar)  
G53 (Grigsby)  
G60  
N32 (Ebbets)  
N53 (Dowling)  
R  
R32 (Fishman)  
R32 (Crowe)  
R32 (Foltz)  
R32 (Newborn)  
T  
U  
X210 (6)