


MoDOT

Research, Development and Technology

RDT 00-001
Final Report

SuperPave Overlay of Sand Anti-Fracture Layer Over PCCP

RI 97-045

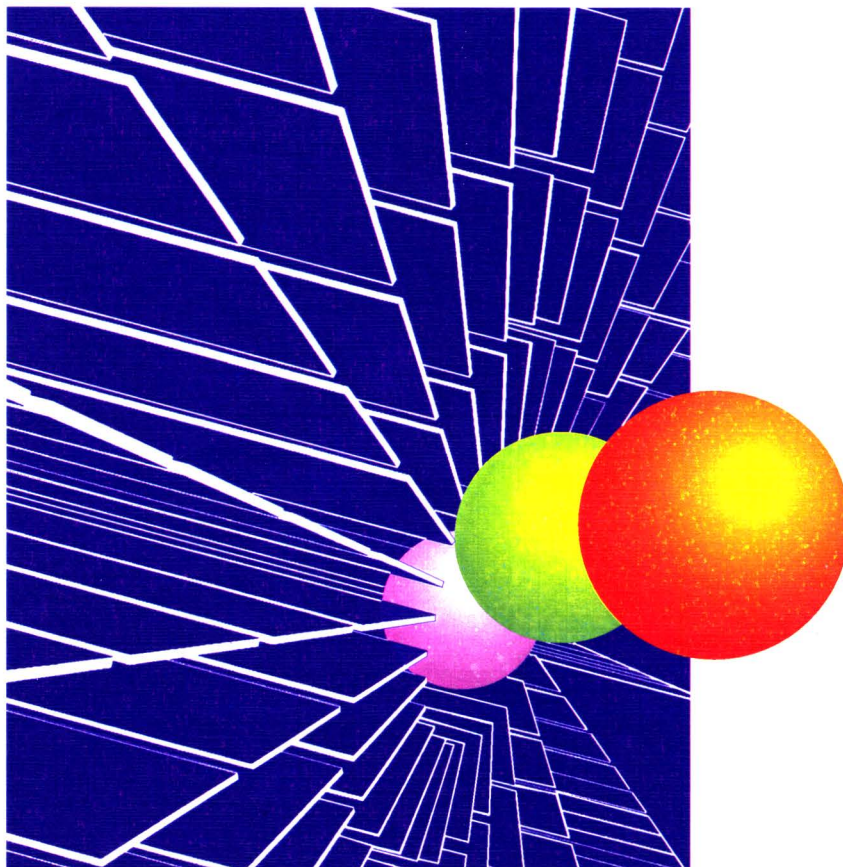

March, 2000

TECHNICAL REPORT DOCUMENTATION PAGE

1. Report No. RI97-045		2. Government Accession No.		3. Recipient's Catalog No.	
4. Title and Subtitle SuperPave Overlay of Sand Anti-Fracture Layer over PCCP				5. Report Date March, 2000	
				6. Performing Organization Code MoDOT	
7. Author(s) Missouri Department of Transportation				8. Performing Organization Report No. RDT 00-001 / RI97-045	
9. Performing Organization Name and Address Missouri Department of Transportation Research, Development and Technology Division P. O. Box 270 Jefferson City, MO 65102				10. Work Unit No.	
				11. Contract or Grant No.	
12. Sponsoring Agency Name and Address Missouri Department of Transportation Research, Development and Technology Division P. O. Box 270 Jefferson City, MO 65102				13. Type of Report and Period Covered Construction and First Annual Report	
				14. Sponsoring Agency Code MoDOT	
15. Supplementary Notes The investigation was conducted in cooperation with the U. S. Department of Transportation, Federal Highway Administration.					
16. Abstract A new technology called a sand anti-fracture (SAF) layer was proposed as an efficient and cost effective method of pavement rehabilitation. The SAF layer is a fine aggregate graded asphalt mixture using highly polymerized asphalt cement and is placed between a Portland Cement Concrete (PCC) pavement and an asphalt overlay. The purpose of the SAF layer is to retard reflective cracking in asphalt overlays over PCC pavements and reduce PCC pavement repair costs. Eight test sections were constructed in summer 1998 on Route I-29 in Holt County to evaluate the SAF layer. The test sections contains two degrees of pavement repair, two different overlay thicknesses, two different grades of asphalt cement, and sections incorporating the recommended 1" SAF layer. These test sections will be compared to each other to evaluate the performance of the SAF layer, as well as the SuperPave overlay design and to determine which provides the greatest benefit-to-cost ratio. This report contains information from beginning of the project until the end of 1999. Visual distress surveys and falling weight deflectometer (FWD) testing were conducted prior to construction and on a bi-yearly basis. The conclusions and recommendations presented are preliminary and are subject to change as additional data are obtained.					
17. Key Words			18. Distribution Statement		
Sand Anti-Fracture, SuperPave, Portland Cement Concrete, Visual Distress Survey, Falling Weight Deflectometer (FWD)			No restrictions. This document is available to the public through the National Technical Information Center, Springfield Virginia 22161.		
19. Security Classification (of this report) Unclassified		20. Security Classification (of this page) Unclassified		21. No. of Pages 18 w/o Appendices	22. Price

RESEARCH INVESTIGATION RI97-045

**CONSTRUCTION AND FIRST ANNUAL REPORT
SUPERPAVE OVERLAY OF
SAND ANTI-FRACTURE LAYER OVER PCCP**

**PREPARED BY
MISSOURI DEPARTMENT OF TRANSPORTATION
RESEARCH, DEVELOPMENT, AND TECHNOLOGY**

Written by:

**JASON M. BLOMBERG, E.I.T.
Intermediate Research and Development Assistant**

**JEFFERSON CITY, MISSOURI
Date Submitted: March 2000**

The opinions, findings and conclusions expressed in this publication are those of the principal investigator and the Research, Development, and Technology Division of the Missouri Department of Transportation.

They are not necessarily those of the U.S. Department of Transportation, Federal Highway Administration. This report does not constitute a standard, specification or regulation.

ACKNOWLEDGMENTS

The author gratefully acknowledges the contributions of the following individuals:

Manda Brandt, MoDOT initial principal investigator, coordinated the sampling, testing, and monitoring throughout construction of the project.

Ron Netemeyer & Joe Shroer, MoDOT Field Office, contact for materials.

Phil Blankenship, Koch Materials, performed SAF mix design.

Eric Burks, Stowe Johnson, Steve Clark, and Michael Blackwell, performed field testing and sampling.

The author is also grateful to John Donahue and Patty Lemongelli for manuscript review.

EXECUTIVE SUMMARY

This project on Route I-29 in Holt County was constructed during the summer of 1998 in District 1. The project consisted of using a new technology, which involved placing a sand anti-fracture (SAF) layer. The SAF layer is placed between a Portland Cement Concrete pavement (PCCP) and an asphalt overlay. The purpose of the SAF layer is to retard reflective cracking in asphalt overlays over PCCP and reduce initial PCC pavement repair cost. If successful, the SAF layer will extend the service life of a pavement and may justify decreasing the amount of original pavement repair and/or the thickness of an asphalt overlay. The project was also Missouri's first SuperPave project to be implemented in District 1. Information regarding the design, construction, and implementation of SuperPave in the project can be found in Appendix A of this report.

The surface of the original pavement consisted of approximately a 9-inch reinforced concrete pavement on a 4-inch, Type 3 aggregate base. The pavement had severe deterioration at the joints and mid-panel cracks caused by durability "D" cracking that constituted the need for an extensive rehabilitation of the pavement. Before an asphalt overlay was constructed, a 1-inch SAF layer was placed on the original PCC pavement. The SAF layer is composed of a fine aggregate graded asphalt mixture using highly polymerized asphalt cement with high voids in the mineral aggregate (VMA) and asphalt content and low air voids. The purpose of the SAF layer is to reduce the progression of reflective cracking with little or no pavement repair. After the SAF layer was placed, an asphalt overlay was constructed using the new SuperPave design methods.

This project includes eight test sections containing two degrees of pavement repair, two different overlay thicknesses, two different grades of asphalt cement, and sections incorporating the recommended 1" SAF layer. These test sections will be compared to each other to evaluate the performance of the SAF layer, as well as the SuperPave overlay design and to determine which provides the greatest benefit-to-cost ratio.

The most recent distress surveys indicate that all test sections that were constructed on I-29 in Holt County are still performing very well after 1-½ years of service. No reflective

cracking has appeared in either of the overlays, with or without the SAF layers. At this time no conclusions can be drawn from the performance of the eight test sections based on the distress surveys and the Falling Weight Deflectometer (FWD) data. Future monitoring and testing is needed to compare the performance of each of the test sections.

Presently, there are no apparent differences in the performance between the SAF and conventional overlays. Therefore, making recommendations on using the SAF layer to reduce reflective cracking and initial PCCP repair cost would be premature. However, another project on Route 36 in DeKalb County has already been proposed to use the new SAF technology. This project consists of constructing an asphalt overlay using an underlying SAF layer on an existing asphalt overlay over jointed reinforced concrete pavement. The actual performance and cost savings benefit that Missouri will receive from using the sand anti-fracture layer is still to be determined. Meanwhile, Research, Development, and Technology will continue monitoring the eight test sections on Route I-29 in order to validate the SAF layer as an efficient and cost-effective method of pavement rehabilitation.

TABLE OF CONTENTS

List of Figures.....	ii
List of Tables.....	ii
Introduction	1
Objectives	2
Discussion of Present Conditions.....	3
Technical Approach.....	3
Project Origin.....	3
Project Layout.....	4
Sampling and Testing.....	5
Project Construction.....	6
Results and Discussion.....	8
Pre-construction.....	8
Post construction.....	8
Project Costs.....	9
Conclusions.....	10
Recommendations.....	10
Bibliography.....	11
Appendix A – SuperPave Construction	
Appendix B – Work Plan	
Appendix C – Mix Designs	
Appendix D – SAF Special Provisions	

LIST OF FIGURES

Figure 1 – Project Limits.....	12
Figures 2-5 – Pre-construction Photos.....	13
Figure 6 – Test Section Layout.....	14
Figure 7 – SAF layer sticking to roller wheel.....	15
Figure 8 – SAF layer tearing from paver screed.....	15
Figure 9 – Blisters forming on SAF layer.....	15

LIST OF TABLES

Table 1 – Analysis Matrix.....	16
Table 2 – Monitoring Area Layout.....	17
Table 3 – Cost Estimate of Test Sections.....	18

INTRODUCTION

One of the main challenges MoDOT has with asphalt overlays over PCC pavements is to prevent or retard reflective cracking. In order to decrease reflective cracking occurring in asphalt overlays, MoDOT has spent a great deal of money on PCC pavement repair before an overlay is constructed. In an effort to reduce pavement repairs, Koch Materials Company presented MoDOT a new technology called a sand anti-fracture (SAF) mixture layer. This technology originated in France and has been brought to the United States by Koch Materials. The SAF layer is a sand asphalt mixture placed between a PCC pavement and an asphalt overlay. According to Koch Materials, the SAF layer will fill pop-outs and other pavement irregularities and resist reflective cracking thereby reducing the need for PCC pavement repair before an asphalt overlay is constructed.

The first project in the United States implementing the SAF layer was constructed in Oklahoma in 1995. An evaluation of the project, conducted in 1997, substantiated an increase in resistance to reflective cracking by using the SAF layer with a stone mastic asphalt (SMA) wearing course. However, the Oklahoma DOT concluded that the SAF mix caused a greater number of distresses than the standard leveling course and fabric membrane treatments, and the SAF layer was not recommended to replace Oklahoma conventional methods. Oklahoma DOT's approach in rehabilitating a PCCP on an interstate route consisted of placing a 1 ½-inch wearing course over a 1-inch SAF layer. The overlay may not have been sufficient to handle the traffic loading capacity, thus resulting in significant rutting and bleeding.

A legitimate concern of the SAF layer is its sensitivity to rutting and lower structural integrity compared to standard asphalt concrete. Koch Materials recommends that a wearing surface be placed within one or two days following the placement of the SAF layer. The SAF layer in Oklahoma was exposed to traffic for seven days, and significant rutting and bleeding occurred on the SAF layer. Rutting was also a challenge to the I-29 project in Holt County. However, rutting was not a problem if proper temperature of the high polymer asphalt binder was achieved. The SAF layer on the I-29 project withstood traffic for approximately one week without any pavement distresses.

Another issue of the SAF layer is its structural integrity. The SAF layer has a modulus value of only half of a standard asphaltic concrete mix. Because of the lower modulus value, the thickness of the SAF layer should not exceed 1-inch, and the SAF thickness should not be included with the calculated pavement design thickness of the asphalt overlay.

Unlike the project in Oklahoma, MoDOT used the SAF layer as a stress relieving membrane between an old PCC pavement and an asphalt overlay to prevent reflective cracking and reduce initial pavement repair costs. The SAF layer fills pop-outs and other irregularities and resists reflective cracking, thereby reducing pavement repairs to only the most severely damaged areas. MoDOT also used SuperPave mix design methods and a greater asphalt thickness compared to the Oklahoma project. This should give the asphaltic concrete overlay the structural integrity required to prevent rutting and other pavement distresses.

The SuperPave and SAF project was constructed in the summer of 1998 on Route I-29 in Holt County. This project included eight different test sections containing a combination of two degrees of pavement repair, two different overlay thicknesses, two different grades of asphalt cement, and some sections incorporating the recommended 1-inch SAF layer. Each test section will be monitored and evaluated in an effort to procure the most efficient and cost effective pavement design. A 5-year study on the performance of the SuperPave and SAF layers was proposed. Further monitoring may be warranted depending upon the performance and service life of the pavement. This report contains information from beginning of the project until the end of 1999. The recommendations and conclusions included in this report are drawn from the pre-construction, construction, and post-construction sampling, testing, and observations. The conclusions and recommendations presented are preliminary and are subject to change as additional data are obtained.

OBJECTIVES

The objective of this research investigation is to evaluate the effectiveness of the sand anti-fracture layer in reducing reflective cracking in asphalt overlays over PCC pavements. The benefits that MoDOT anticipates from the SAF layer are the savings from the reduction of initial

pavement repair costs, possibilities of a reduction in overlay thickness, and a longer lasting service life of the asphalt overlay.

DISCUSSION OF PRESENT CONDITIONS

When PCC pavements need rehabilitation, the most widely used method that MoDOT has implemented in the past is a standard IC or IB asphalt overlay over the PCCP. The thickness of the asphalt overlay depended on traffic and pavement condition. Usually, a 1 ¾-inch IC mix was placed as the wearing surface, while 2 to 4 inches of an IB mix was placed as a binder course layer. Recently, MoDOT has required a new SuperPave mix design for all pavements over 3500 ADT. The SuperPave mix design is an improved system for specifying asphalt binders and mineral aggregates and developing asphalt mixture designs to establish a better performing pavement. Construction and design information regarding SuperPave are included in Appendix A of this report.

Another problem MoDOT has with asphalt overlays of PCC pavements is reflective cracking that occurs in the asphalt layer due to the underlying deteriorated PCCP joints and cracks. The research performed during this investigation is essential in determining the benefits that MoDOT anticipates by supplementing the sand anti-fracture layer with the SuperPave asphalt overlays.

TECHNICAL APPROACH

Project Origin

The SAF project is located on both northbound and southbound lanes of Route I-29, Holt County, Missouri, between Station 790+02 (south of Mound City) and Station 1045+00 (south of Route 159) for a total project length of 4.829 miles. A map showing the project location and limits can be found in Figure 1.

The original pavement was built in 1974 under project number I-IG-29-2 (10) 76. The pavement was a 24-foot wide reinforced, 9-inch Portland Cement Concrete Pavement with 61.5 ft. sawed contraction joints. The materials and respective proportions used in the pavement were as follows:

Coarse Aggregate: Plattsmouth Limestone, Kerford Quarries, Weeping Waters, Nebraska.
Fine Aggregate: Missouri River Class A Sand from Holiday Sand and Gravel, 5 miles south of Craig, MO.
Cement: Type 1 Cement from Missouri Portland Cement Co., Sugar Creek, MO.
Mix Proportions: 1.00: 2.00: 2.85
Air: Air Entrainment Agent, Ad Aire Single Strength, Average % Air = (4.9 – 5.4).
Water: 4.7 – 4.9 gallons per sack of cement.

A 4-inch, Type 3 Aggregate Limestone Base (Erving Creek Limestone) was the original constructed base material. The underlying subgrade consisted of a silty clay loam material. The subgrade had to be reworked to obtain suitable stability before pavement construction. After approximately 20 years of service, the PCC pavement showed signs of major D-cracking and joint deterioration, which constituted the need for a complete rehabilitation of the road. Photographs in Figures 2-5 illustrate the original pavement condition that was typical in this project.

Project Layout

The I-29 project was agreed upon to be an excellent candidate for minimal pavement repair and evaluation of the effectiveness of the SAF layer in reducing reflective cracking. MoDOT personnel from District 1 and the Research, Development, and Technology Division, evaluated the SAF layer performance by monitoring reflective cracking and rutting, determining load transfer at underlying PCCP joint locations, and visual examination of drilled cores, if necessary. By analyzing the data collected from each of the test sections, MoDOT hopes to determine the optimum method of rehabilitating PCC pavements.

The SAF layer was constructed in 1998 on Route I-29 in Holt County. This project includes eight test sections containing a combination of the following: two degrees of pavement repair, two different overlay thicknesses, two different grades of asphalt cement, and some sections incorporating the recommended 1-inch SAF layer. The layout of the eight test sections is shown in Figure 6. The test sections' analysis matrix is shown in Table 1.

The two degrees of pavement repair used for this project were normal pavement repair and minimum pavement repair. Normal pavement repair included maintenance at all locations that showed medium to severe pavement distress. This is a conventional method used on most pavements in order to maximize the performance of the overlay. Minimum pavement repair included maintenance of only the most severe pavement deterioration in which there would be a loss of support and structural integrity if the pavement were not repaired. On this project, minimum pavement repair resulted in 75% reduction in pavement repair costs as compared to normal repair.

Due to the 10 mile total project length, the actual monitoring area was reduced to shorter 500 – 1000 feet lengths within the 0.5 – 3.0 mile test section. In addition, test section six was split into two 1000 feet monitoring areas, because of its 3 mile length. The other test sections have one monitoring area each. The sampling and monitoring area layout is listed in Table 2.

Sampling and Testing

Originally, the SAF project test sites were designed for inclusion into the long-term pavement performance (LTPP) program as part of an SPS-6 site. This did not occur. However, the testing and sampling protocol did meet most LTPP standards for all materials, mixes, and pavement and base layers.

The SAF project work plan in Appendix B gives an outline of the work performed in this project. All testing and evaluations were performed within the monitoring areas of each of the eight test sections. A pre-construction distress survey was conducted on the existing pavement to record pavement joints, cracks, and severity of distresses. The joints and cracks were also marked using a nail on the in-slope. The nail was used to re-locate the joints and cracks after the overlay was constructed. Falling Weight Deflectometer (FWD) testing was conducted prior to the overlay to obtain load transfer data at the PCCP joints and pavement moduli.

After pre-construction data were obtained, the same monitoring areas were used for testing during construction. The location and dimensions of all PCCP joint and crack repairs were recorded. Also, the joints and cracks that were not repaired, but would have been repaired under

normal pavement repair procedures, were recorded. The marking of PCCP repairs and non-repairs was necessary in order to help draw conclusions of the SAF layer's effectiveness in retarding reflective cracking versus normal pavement repairs. After the pavement repairs were completed, the construction of the overlay commenced. During the placement of the top wearing course, thermoplastic markers were placed on the finished asphalt surface to locate the underlying PCCP joints and cracks.

After project completion, a distress survey and FWD testing were conducted on the new asphaltic concrete surface. Annual monitoring of the project will occur in 2000, 2001, 2002, and 2003. The annual monitoring will include conducting distress surveys, measuring rutting, and FWD testing.

Project Construction

The rehabilitation of I-29 in Holt County (from Route 118, 4.829 miles south to Route 159) was one of Missouri's first SuperPave projects. It was also Missouri's first project for evaluating a new sand anti-fracture (SAF) technology. The I-29 project presented all parties involved with many technical challenges. Numerous lessons were learned about both the SuperPave and SAF mixes and construction practices.

The SAF mix design can be found in Appendix C, and the SAF's special provisions can be found in Appendix D. Compared to a conventional asphalt mix, the SAF mix has a higher voids in the mineral aggregate (VMA), higher asphalt binder content, and lower air voids. The SAF also contains more sand or finer graded aggregate than a conventional mix. The intent of the SAF mix is to utilize the high polymer binder characteristics in resisting more pavement strains than conventional asphalt concrete. Koch Materials has conducted SHRP 4-Point Beam Fatigue Tests on the SAF. Laboratory results show that the SAF can withstand approximately 4.5 times more strain without cracking at one million loading cycles than a conventional asphalt mix. The SAF is able to dissipate energy induced by thermal and load related stresses. The SAF layer, however, has a lower modulus value compared to standard asphaltic concrete. The SAF layer should not be a factor in the design thickness of the asphalt overlay.

Placement of the SAF layer had some initial constructibility problems. One problem was getting the right amount of the high polymer asphalt for the mix. Due to the inexperience in dealing with the binder's high polymer characteristics, the asphalt plant had difficulties in establishing the binder's proper temperature to accurately measure and control the flow of the binder. The asphalt plant's meter devices would "gum up" and may have given erroneous readings. During the construction of test section eight, the asphalt content was apparently too high. As a result, the SAF layer had poor workability and rutted severely. A high asphalt content also created difficulty keeping the truck beds clean, and the mix would stick to truck tires and rollers as shown in Figure 7. In addition, the mix was very hard to finish and appeared to tear from the screed during placement. Figure 8 illustrates the blemishes on the SAF layer after placement. The severe rutting that occurred in test section eight resulted in the removal of a short stretch between stations 1038+00 to 1041+49. Despite the initial problems, once the proper temperature was established for the high polymer asphalt binder, measuring and controlling the flow of asphalt was no longer a problem. Consequently, the occurrence of pavement rutting had diminished, and placement and workability problems were improved.

Another concern was the formation of blisters, as shown in Figure 9, which occurred after placement of the SAF layer. According to Koch Materials, evaporated gases from trapped moisture cause the blisters to form, but they disappeared once the overlay was placed and did not cause any significant problems to the pavement structure or the SAF layer.

Despite the problems that occurred during construction, the finished product seemed to be a success. The SAF layer's effectiveness in reducing reflective cracking will be monitored for a 5-year performance period. This report includes test data and surveys for approximately the first 1-½ years of service life of the project. The construction issues concerning SuperPave can be found in Appendix A, and the SuperPave mix designs can be found in Appendix C of this report.

RESULTS AND DISCUSSION

Pre-construction

Pre-construction sampling and testing was performed on the subgrade. The original subgrade was primarily composed of a silty clay soil. In some locations, however, the subgrade was composed of mostly sand material. The plasticity index (PI) of the soil ranged from as low as 2 in the sand-silt areas to as high as 12 in the silt-clay areas. Concrete cores were also taken from the roadway to determine the overall concrete strength. Out of a total of 18 cores that were sampled, the average compressive strength and the average split tensile strength were 5760 psi and 709 psi, respectively. Overall, the structural evaluation of the subgrade, base, and original pavement were in good condition. However, the severe D-cracking and deterioration at the joints and cracks constituted the need for rehabilitation. The Falling Weight Deflectometer (FWD) testing results performed on the original pavement indicated that approximately 46% of the joints tested had a load transfer below 70%. The distress surveys performed on the original pavement concluded that there was high severity cracking and deterioration at many of the joints. Also, there were many areas of low to moderate severity cracks that would soon become major pavement distresses.

Post construction

Post construction testing included FWD testing and pavement distress surveys. The FWD data obtained from the annual monitoring has been used to compare each section and help determine the effectiveness of the SAF layer in reducing reflective cracking. Poor load transfers of the PCC joints and cracks indicate areas with a possibility of reflective cracks perpetrating through the asphalt overlay. Although the PCC joints and cracks within the monitoring areas were marked on the finished asphalt surface with thermoplastic markers, the FWD loading plate was difficult to align in the same position as the previous tests. However, the thermoplastic markers kept the FWD loading plate in the relatively same locations as the previous tests so that comparisons can continue to be made. The FWD testing performed as of October 1999 indicated that approximately 96 % of the joints tested within the monitoring areas of the test sections had load transfers greater than 70 %. No significant comparisons of the individual test sections can be recognized, at this time, by comparing the FWD data.

Distress surveys taken after the construction of the overlay show that virtually no cracks are appearing in any of the test sections after 1½ years of service life. Two transverse cracks are starting to appear in test section eight and will be monitored throughout the investigation. One crack extends across the driving lane at station 1040+37. The crack is located in the problem area where the SAF layer was removed and replaced. The other transverse crack extends approximately 6 feet across the driving lane measured from the edge of the roadway at station 1043+73.

Project Costs

The construction cost of each test section varied depending on overlay thickness, grade of asphalt, degree of pavement repair, and whether the SAF layer was used. Table 3 lists the cost estimate of each test section. The construction cost of the SAF layer was not always less than performing normal pavement repairs. However, when pavement repairs exceed \$40,000, like test section eight, the construction cost of the SAF layer is less than performing normal pavement repairs. In most cases, there is not a significant difference between the construction cost of the SAF layer compared to normal pavement repair. The actual pavement performance of each test section in the future will dictate which method is the most cost effective.

CONCLUSIONS

- The most recent distress surveys indicate that all test sections that were constructed on I-29 in Holt County are still performing very well after 1 ½ years of service.
- No significant reflective cracking has appeared in test sections incorporating the 1-inch SAF layer or test sections constructed by conventional methods.
- No distinct differences of performance of the eight test sections can be made from the distress surveys or the FWD data to indicate which sections are performing better than the others.
- The difference in construction cost between the SAF layer and normal pavement repair methods depend on the amount of pavement repair that is needed.

RECOMMENDATIONS

- Based on current test results and observations recommendations on the SAF implementation for pavement rehabilitation cannot be given.
- Further testing and monitoring of the eight test sections on Route I-29 is needed in order to validate the SAF technology as an effective and economical solution for pavement rehabilitation.
- It is recommended that the SAF technology be considered for other projects. (Note: A follow up project on the SAF technology is underway for Route 36 in Dekalb County, where Research, Development & Technology will continue monitoring the SAF performance.)

BIBLIOGRAPHY

1. **Brewer, Wilson B., "Sand Anti-Fracture Mixture I-35 Logan County, Oklahoma", Research, Development and Technology Transfer, March 1997.**
2. **Koch Materials Company, "Sand Anti-Fracture (SAF) Mixture Trial", 1997.**

MISSOURI HIGHWAY AND TRANSPORTATION COMMISSION PLANS FOR PROPOSED STATE HIGHWAY

HOLT COUNTY

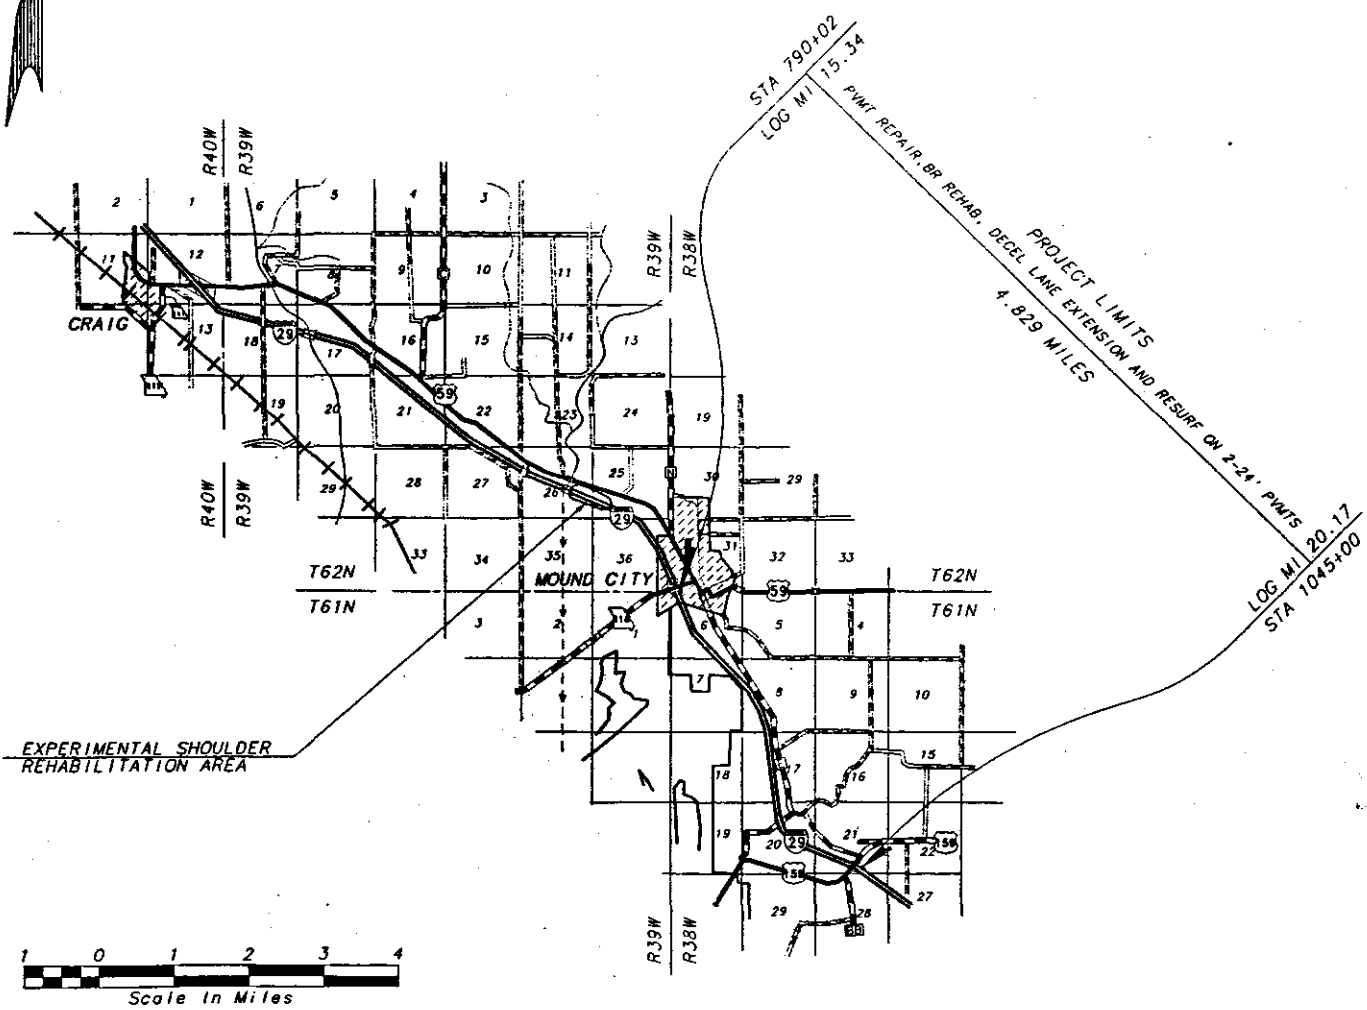




Figure 2 (Station 836+16 NBL)

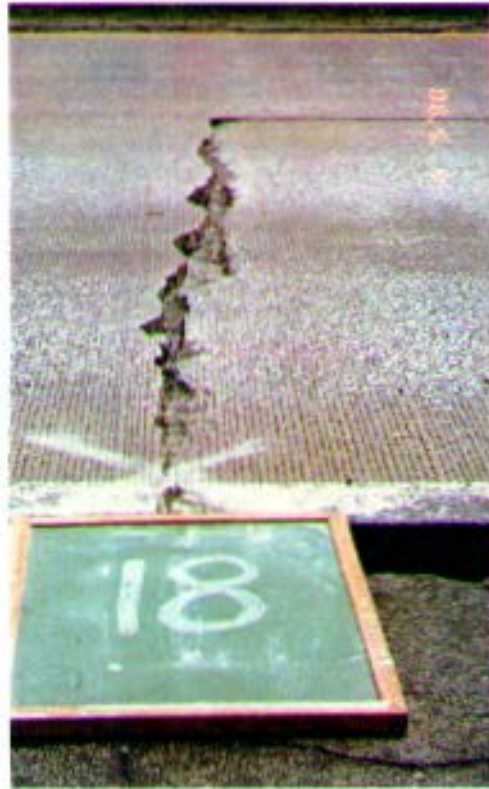


Figure 3 (Station 957-96 SBL)

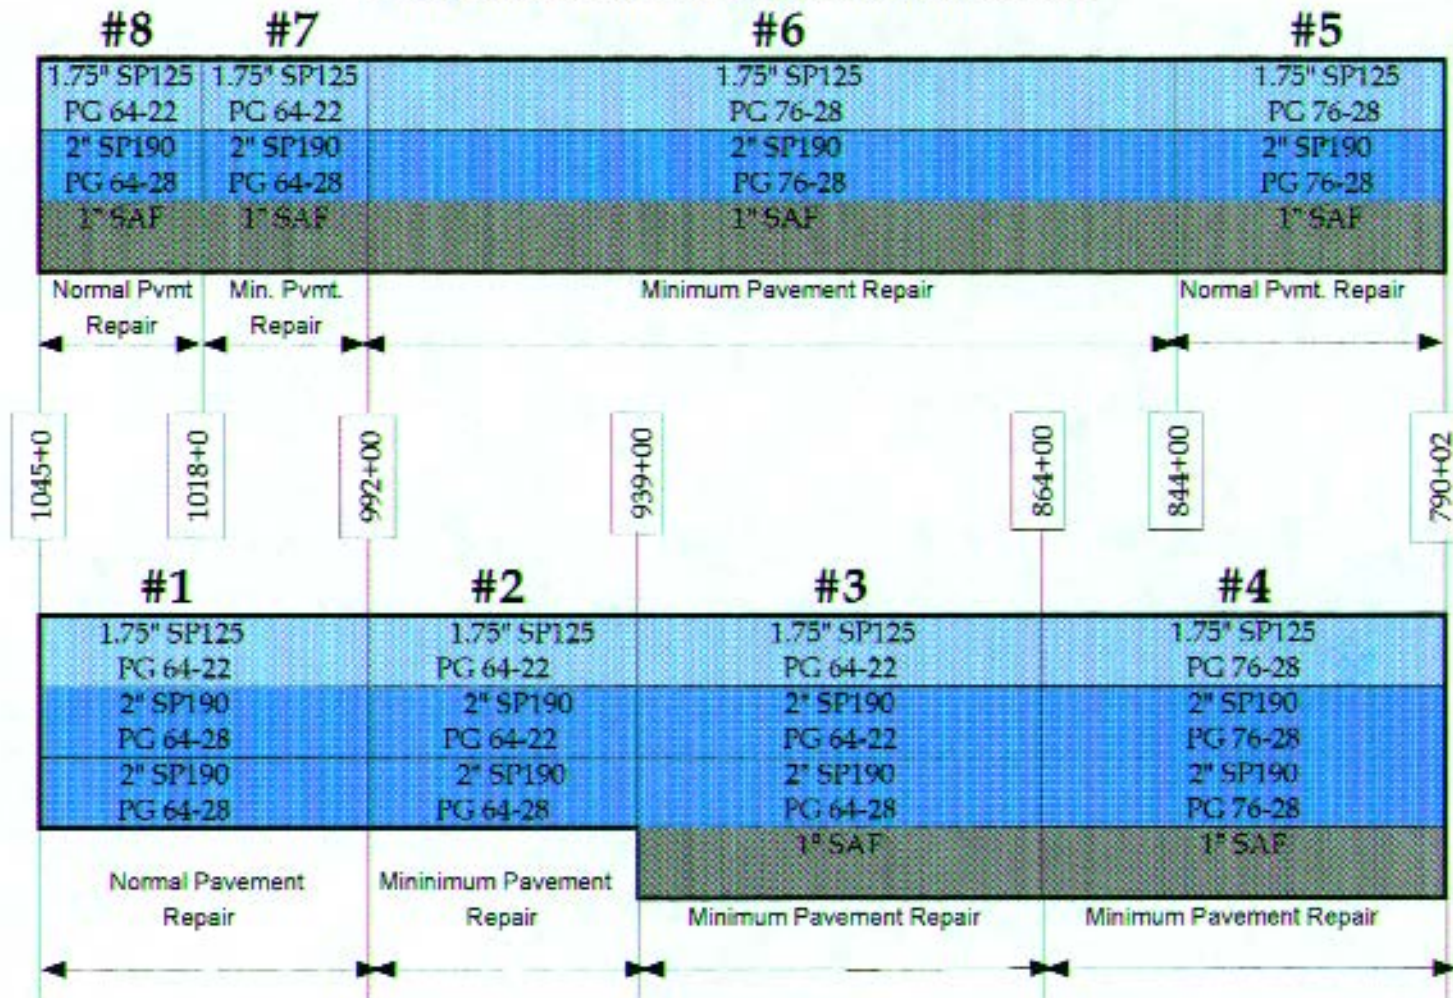


Figure 4 (Station 913+16 NBL)



Figure 5 (Station 1000+06 SBL)

I-29 Southbound Driving Lane, Profile View



I-29 Northbound Driving Lane, Profile View

Figure 6 - Test Section Layout

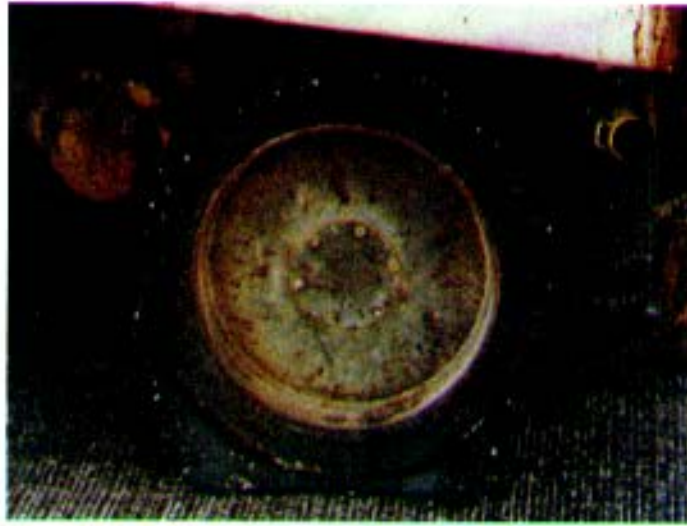


Figure 7 - SAF layer sticking to roller wheel



Figure 8 - SAF layer tearing from screeder



Figure 9 - Blisters forming on SAF layer

Analysis Matrix								
Test Section	Pavement Repair		1" SAF Layer		PG Grade Asphalt		Asphalt Thickness	
	Minimal	Normal	Yes	No	PG64-28*	PG76-28	3 3/4"	5 3/4"
1		X		X	X			X
2	X			X	X			X
3	X		X		X			X
4	X		X			X		X
5		X	X			X	X	
6	X		X			X	X	
7	X		X		X		X	
8		X	X		X		X	

*PG 64-28 became unavailable during construction. The wearing course was replaced with grade PG 64-22.
(See Test Section Layout, page 12.)

Table 1 – Analysis Matrix

Monitoring Area Layout		
Monitoring Area Number	Limits	General Description
290011	1045+00 to 992+00 (NBL) 1003+00 to 1002+00 1002+00 to 997+00 997+00 to 996+00	Test Section No. 1 Lead In Monitoring Area Lead Out
290021 290021	992+00 to 939+00 (NBL) 963+00 to 962+00 962+00 to 952+00 952+00 to 951+00	Test Section No. 2 Lead In Monitoring Area Lead Out
290031	939+00 to 864+00 (NBL) 918+00 to 917+00 917+00 to 912+00 912+00 to 911+00	Test Section No. 3 Lead In Monitoring Area Lead Out
290041	864+00 to 790+02 (NBL) 838+00 to 837+00 837+00 to 827+00 827+00 to 826+00	Test Section No. 4 Lead In Monitoring Area Lead Out
290051	790+02 to 844+00 (SBL) 826+00 to 827+00 827+00 to 837+00 837+00 to 838+00	Test Section No. 5 Lead In Monitoring Area Lead Out
290061 290062	844+00 to 992+00 (SBL) 848+00 to 849+00 849+00 to 859+00 859+00 to 860+00 951+00 to 952+00 952+00 to 962+00 962+00 to 963+00	Test Section No. 6 Lead In Monitoring Area Lead Out Lead In Monitoring Area Lead Out
290071	992+00 to 1018+00 (SBL) 996+00 to 997+00 997+00 to 1002+00 1002+00 to 1003+00	Test Section No. 7 Lead In Monitoring Area Lead Out
290081	1018+00 to 1045+00 (SBL) 1038+00 to 1039+00 1039+00 to 1044+00 1044+00 to 1045+00	Test Section No. 8 Lead In Monitoring Area Lead Out

Table 2 – Monitoring Area Layout

Cost Estimate of Test Sections					
Test Section	SuperPave Mix Cost /per mile*	SAF Layer Cost/per mile*	Pavement Repair Cost/per mile*		Total Cost/ Per mile*
			Normal	Minimum	
Test Section 1	\$167,714	Not used	\$26,273	-	\$193,987
Test Section 2	\$167,714	Not used	-	\$4,405	\$172,119
Test Section 3	\$167,714	\$40,410	-	\$1,228	\$209,352
Test Section 4	\$185,483	\$40,410	-	\$2,193	\$228,086
Test Section 5	\$122,154	\$40,410	\$37,107	-	\$199,671
Test Section 6	\$122,154	\$40,410	-	\$5,095	\$167,659
Test Section 7	\$110,320	\$40,410	-	\$4,523	\$155,261
Test Section 8	\$110,320	\$40,410	\$93,018	-	\$243,748

* Cost based on a 24' width

Table 3 – Cost Estimates of Test Sections

APPENDIX A
SuperPave Construction

SuperPave Overlay

The following paragraphs include pertinent information regarding the construction of the SuperPave asphaltic concrete overlay constructed over the sand anti-fracture (SAF) layer. This project was Missouri's first SuperPave project to be implemented in District 1. SuperPave is a new asphalt mix design method that incorporates performance based asphalt materials characterization with the design environmental conditions to improve the performance of asphalt pavements.

The SuperPave mix designs, SP125 and SP190, can be found in Appendix B. The verification of the SuperPave mix design presented many technical challenges from the beginning of the project. During mix verification, it was discovered that there was a difference in the combined bulk specific gravity of the stone (Gsb) that the contractor had used versus the Gsb that MoDOT used. Evidently, the test procedures between MoDOT and the contractor varied considerably. The different Gsb led to differences in the values of voids in the mineral aggregate (VMA) and percent air voids in the mix (Va). Also, there were conflicting data compiled by the different brand of gyratory compactors used. MoDOT used a Pine Gyratory while the contractor used a Troxler Gyratory. Due to these differences, there was no verification of either the SP-190 or SP-125 SuperPave mixes.

Another challenge that developed throughout the course of the project was the determination of asphalt content in the mix. The asphalt content directly affects the voids in the mineral aggregate (VMA) of the mix. An ignition oven designed by the National Center for Asphalt Technology (NCAT) was used to determine the asphalt content. Test results from the ignition oven proved erratic compared to the asphalt nuclear gauge, daily tank sticks, and plant totalizer readings.

Also, early during construction, the supply of asphalt binder PG64-28 became depleted. A switch to asphalt binder grade PG 64-22 was necessary to complete the project. Despite the asphalt grade variable, the test sections were made more comparable by placing the PG 64-22 binder on the top 1 ¾-inch wearing surface on all test sections that

originally called for PG 64-28. Test sections 2 and 3 also had PG 64-22 as the top 2 inches of the bituminous base course. The original PG 64-28 was used as the bituminous base course for the remaining bituminous base layers of the test sections. (See Figure 6).

Only temporary solutions were proposed for the SuperPave mix design problems. Further testing and discussions are needed in order to achieve an agreement on some of the issues.

APPENDIX B

Work Plan

STUDY PROPOSAL

Date: 1/30/98

Project Number: RI 97-045

Title: Superpave Overlay of Sand Anti-Fracture Layer Over PCCP

Research Agency: Materials Field Office, Koch Materials, and RD&T Division

Investigators: Manda Brandt, RD&T - Principal Investigator
Joe Shroer/Ron Netemeyer, Field Office - Contact for Materials
Phil Blankenship, Koch Materials - Performing SAF Mixture Design


Objective: To evaluate the effectiveness of approximately one inch of Sand Anti-Fracture Mixture (SAF) in reducing reflective cracking in asphalt overlays over PCCP with minimum pavement repair.

Background and Significance of Work: The main problem MoDOT has with AC overlays of PCCP is reflective cracking. This SAF layer, according to Koch Materials, will reduce the amount of reflective cracking with a reduced pavement overlay thickness and only minimal PCCP pavement repair required. SAF is a fine graded asphalt mixture using a highly polymerized asphalt cement with high VMA and asphalt content and low air voids.

Action Plan: The SAF layer will be constructed on I-29 in Holt County on Job J110737. There will be 8 test sections, as shown in Table 1. The investigation includes pavements with two degrees of pavement repair, two different overlay thicknesses, and two different grades of asphalt cement, with some sections incorporating the recommended 1" SAF layer. The sections will be compared to evaluate: the performance of the SAF layer, as well as the pavement overlay design that provides the greatest benefit related to cost.


TEST SECTIONS

J110737
I-29
HoltCo.

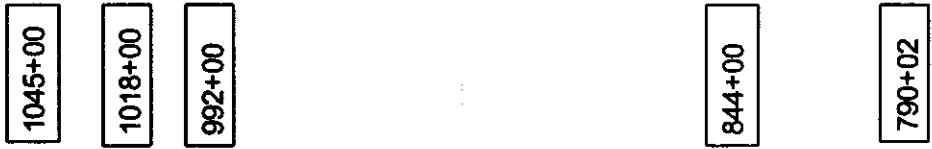

SB I-29	Norm	Min	Minimum	Normal	Pav'tRepair TestSection
	8	7	6	5	

NB I-29	Normal	Minimum	Minimum	Minimum	Pav'tRepair TestSection
	1	2	3	4	

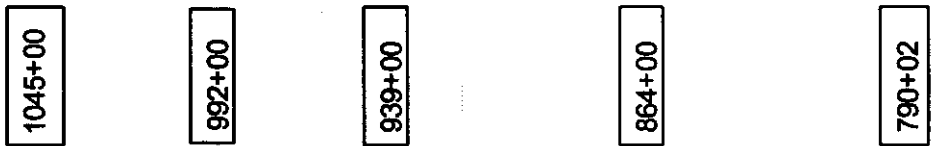

<u>TestSection</u>	<u>AC OL</u>	<u>SAF</u>	<u>PAVT REP</u>	<u>AC GRADE</u>	<u>MILES</u>
1	5 3/4"		Normal	64-28	1.0
2	5 3/4"		Minimum	64-28	1.0
3	5 3/4"	1"	Minimum	64-28	1.5
4	5 3/4"	1"	Minimum	76-28	1.5
5	3 3/4"	1"	Normal	76-28	1.0
6	3 3/4"	1"	Minimum	76-28	3.0
7	3 3/4"	1"	Minimum	64-28	0.5
8	3 3/4"	1"	Normal	64-28	0.5

Table 1. Test Section Layout

Literature Search: Koch Materials has supplied information regarding the SAF layer.

Method of Implementation: If this method is successful, we will propose implementation procedures based on a final report and presentations to design and materials related personnel.

Anticipated Benefits: It is anticipated that the SAF layer will reduce the amount of reflective cracking in asphalt overlays over PCCP, therefore extending the life of the asphalt overlay. There will also be cost savings through the reduction of overlay thickness and required pavement repair.

Research Period: There will be a construction report at the end of the 1998 construction season. The site will be monitored annually for five years and a final report will detail the performance of the test sections.

Funding: The test site construction will be funded by District 1's construction fund. The construction sampling, annual monitoring, and report expenses will be funded by the RD&T division with SPR funds.

WORK PLAN

Procedure:

➤ PLANNING PHASE -

Monitoring Areas and Numbering Scheme

Due to the 10 mile total project length, the actual monitoring area will be reduced to shorter 500-1000' lengths within the 0.5-3 mile test section. In addition, test section 6 will have two 1000' monitoring areas, because of its 3 mile length. The other test sections will have one monitoring area each. These monitoring areas will be numbered as follows: 2900XY, where X is the test section number as shown in **Table 1**, and Y is the consecutive number of the monitoring area within that test section. For example, 290062 would be the second monitoring area within test section 6. 290051 would be the first monitoring area within test section 5. This numbering scheme will allow the test section data to be incorporated into the existing LTPP database.

Designated Sampling Areas

There will be a sampling area, for destructive testing, at the beginning and end of each of the nine monitoring areas. These sampling areas will be 100' in length and will not overlap the monitoring areas. They are referred to as Lead In and Lead Out in **Table 2**.

Monitoring Area No.	Limits	General Description
290011	1045+00 to 992+00 (NBL)	Test Section #1
	1003+00 to 1002+00	Lead In
	1002+00 to 997+00	Monitoring Area
290021	997+00 to 996+00	Lead Out
	992+00 to 939+00 (NBL)	Test Section #2
	963+00 to 962+00	Lead In
290031	962+00 to 952+00	Monitoring Area
	952+00 to 951+00	Lead Out
	939+00 to 864+00 (NBL)	Test Section #3
290041	918+00 to 917+00	Lead In
	917+00 to 912+00	Monitoring Area
	912+00 to 911+00	Lead Out
290051	864+00 to 790+02 (NBL)	Test Section #4
	838+00 to 837+00	Lead In
	837+00 to 827+00	Monitoring Area
290061	827+00 to 826+00	Lead Out
	790+02 to 844+00 (SBL)	Test Section #5
	826+00 to 827+00	Lead In
290062	827+00 to 837+00	Monitoring Area
	837+00 to 838+00	Lead Out
	844+00 to 992+00 (SBL)	Test Section #6
290071	848+00 to 849+00	Lead In
	849+00 to 859+00	Monitoring Area
	859+00 to 860+00	Lead Out
290081	951+00 to 952+00	Lead In
	952+00 to 962+00	Monitoring Area
	962+00 to 963+00	Lead Out
290081	992+00 to 1018+00 (SBL)	Test Section #7
	999+00 to 1000+00	Lead In
	1000+00 to 1005+00	Monitoring Area
290081	1005+00 to 1006+00	Lead Out
	1018+00 to 1045+00 (SBL)	Test Section #8
	1038+00 to 1039+00	Lead In
290081	1039+00 to 1044+00	Monitoring Area
	1044+00 to 1045+00	Lead Out

Table 2. Sampling and Monitoring Area Layout

➤ **CONSTRUCTION IN 1998** - The test sections will be sampled and tested as follows:

Pre-Construction Sampling

March, 1998

A field crew from the RD&T division will perform the following within the monitoring areas:

- Marking of each joint and working crack with a nail on the in-slope. This nail will be used for joint/crack location reference in the future.
- Distress Survey of the existing PCCP.
- Falling Weight Deflectometer (FWD) Testing of the monitoring areas according to SPS-6 Protocol.

District 1 Construction Personnel will perform 5 point cross sections, of the existing PCCP, within the monitoring areas.

A field crew from the RD&T division will perform the following within the sampling areas:

- Sampling of the existing PCCP with 4", 6" and 12" cores.
- Within the 6" holes - augering of the base, and splitspoon or shelly tube of the subgrade to 4' below the surface of the subgrade.
- Within the 12" holes - augering to 12" below the top of the subgrade.
- Shoulder Augering - to depth of 20' or to refusal.

Construction Sampling

May - September(?), 1998

Within the monitoring areas, a field crew from the RD&T division will:

- Note the locations and dimensions of all PCCP joint/crack repairs.
- Mark the finished surface of the asphaltic concrete overlay with a thermoplastic pavement marker to locate the joints and working cracks.

Within the monitoring areas of the minimal pavement repair test sections, District 1 Construction personnel will note the joints and cracks that would have been repaired under normal pavement repair procedures.

Within the paving hoppers or the sampling areas when possible, an RD&T field crew will:

- Obtain bulk samples of the SAF and all SuperPave Mixes.

At the asphalt plant, the RD&T field crew will:

- Collect bulk aggregate and asphalt cement samples.

Post-Construction Sampling

September or October, 1998

Within the monitoring areas, the RD&T field crew will:

- Complete a distress survey if necessary.
- Perform FWD Testing of the finished asphaltic concrete surface.

Within the monitoring areas, District 1 Construction Personnel will perform 5 point cross section surveys of the finished asphaltic concrete surface.

Within the sampling areas, the RD&T field crew will:

- Obtain 4" cores of the asphaltic concrete overlay.

➤ **REPORTS AND ANNUAL MONITORING -**

- December 31, 1998 - The test site construction will be summarized in a construction report.
- 1999, 2000, 2001, 2002, and 2003 on the anniversary of the test sections being open to traffic - The annual monitoring will include but will not be limited to the following: five point cross sections, distress surveys, and FWD tests of the monitoring areas. As well as coring of the sampling areas in the years 2000 and 2003.
- December 31, 2003 - The annual surveys will be summarized to create a final report detailing the performance of the test sections.

Staffing:

Preliminary Planning

Manda Brandt, Intermediate Research Assistant	120 hours
Senior Field Testing Technician	40 hours
Testing Technician	120 hours

Construction Sampling

Manda Brandt, Intermediate Research Assistant	80 hours
Senior Field Testing Technician	240 hours
Testing Technician	240 hours
Temporary Employee	240 hours
Temporary Employee	240 hours

Annual Surveys (Five years at 40 hours/year)

Senior Field Testing Technician	200 hours
Senior Field Testing Technician	200 hours
Senior Field Testing Technician	200 hours
Senior Field Testing Technician	200 hours

Final Report and Presentations

Senior Research and Development Engineer	160 hours
--	-----------

Equipment:

At this time, it is estimated that we will have ample in-house equipment to complete this project. However, some incidental equipment and supplies may need to be purchased at the time of construction, this cost will be reflected in the budget.

Budget:

Estimated Construction Cost **\$3,500,000.00**

1998 EXPENSES:

RD&T Salaries:

Preliminary Planning

Intermediate Research Assistant	120 hours	@ \$19.00/hr	\$ 2,280.00
Senior Field Testing Technician	40 hours	@ \$17.00/hr	\$ 680.00
Testing Technician	120 hours	@ \$13.00/hr	\$ 1,560.00

Construction Sampling

Intermediate Research Assistant	80 hours	@ \$19.00/hr	\$ 1,520.00
Senior Field Testing Technician	240 hours	@ \$17.00/hr	\$ 4,080.00
Testing Technician	240 hours	@ \$13.00/hr	\$ 3,120.00
Temporary Employee	240 hours	@ \$ 7.50/hr	\$ 1,800.00
Temporary Employee	240 hours	@ \$ 7.50/hr	\$ 1,800.00

Sub-Total Salaries	\$16,840.00
Salary Additive (@67%)	\$11,282.80
Possible Overtime	\$ 5,000.00
<u>Total 1998 Salaries</u>	<u>\$33,122.80</u>

RD&T Equipment: All per mile costs include operating and depreciation costs, respectively.

1998 Construction Sampling

5107 Bridge Van	12 trips X 550 mi @(\$0.212/mi+\$0.130/mi)	\$ 2,257.20
Pool Car	12 trips X 550 mi @(\$0.131/mi+\$0.142/mi)	\$ 1,801.80
5757 Drill Truck	2 trips X 550 mi @(\$0.293/mi+\$0.141/mi)	\$ 477.40
FWD Van	2 trips X 550 mi @(\$0.250/mi+\$0.150/mi)	\$ 440.00

Incidental Equipment and Supplies **\$15,000.00**

Total 1998 Equipment **\$ 19,976.40**

TOTAL FOR 1998 **\$53,099.20**

1999 Annual Survey

5 Senior Field Testing Technicians	40 hours	@ \$17.00/hr	\$ 3,400.00
Salary Additive		(@67%)	\$ 2,278.00
5107 Bridge Van	1 trips X 550 mi @(\$0.212/mi+\$0.130/mi)		\$ 188.10
Pool Car	1 trips X 550 mi @(\$0.131/mi+\$0.142/mi)		\$ 150.15
FWD Van	1 trips X 550 mi @(\$0.250/mi+\$0.150/mi)		\$ 220.00

TOTAL FOR 1999 **\$ 6,236.25**

2000 Annual Survey

5 Senior Field Testing Technicians	40 hours	@ \$17.00/hr	\$ 3,400.00
Salary Additive		(@67%)	\$ 2,278.00
5107 Bridge Van	1 trips X 550 mi	@(\$0.212/mi+\$0.130/mi)	\$ 188.10
Pool Car	1 trips X 550 mi	@(\$0.131/mi+\$0.142/mi)	\$ 150.15
5757 Drill Truck	1 trips X 550 mi	@(\$0.293/mi+\$0.141/mi)	\$ 238.70
FWD Van	1 trips X 550 mi	@(\$0.250/mi+\$0.150/mi)	\$ 220.00

TOTAL FOR 2000

\$ 6,474.95

2001 Annual Survey

5 Senior Field Testing Technicians	40 hours	@ \$17.00/hr	\$ 3,400.00
Salary Additive		(@67%)	\$ 2,278.00
5107 Bridge Van	1 trips X 550 mi	@(\$0.212/mi+\$0.130/mi)	\$ 188.10
Pool Car	1 trips X 550 mi	@(\$0.131/mi+\$0.142/mi)	\$ 150.15
FWD Van	1 trips X 550 mi	@(\$0.250/mi+\$0.150/mi)	\$ 220.00

TOTAL FOR 2001

\$ 6,236.25

2002 Annual Survey

5 Senior Field Testing Technicians	40 hours	@ \$17.00/hr	\$ 3,400.00
Salary Additive		(@67%)	\$ 2,278.00
5107 Bridge Van	1 trips X 550 mi	@(\$0.212/mi+\$0.130/mi)	\$ 188.10
Pool Car	1 trips X 550 mi	@(\$0.131/mi+\$0.142/mi)	\$ 150.15
FWD Van	1 trips X 550 mi	@(\$0.250/mi+\$0.150/mi)	\$ 220.00

TOTAL FOR 2002

\$ 6,236.25

2003 Annual Survey

5 Senior Field Testing Technicians	40 hours	@ \$17.00/hr	\$ 3,400.00
Salary Additive		(@67%)	\$ 2,278.00
5107 Bridge Van	1 trips X 550 mi	@(\$0.212/mi+\$0.130/mi)	\$ 188.10
Pool Car	1 trips X 550 mi	@(\$0.131/mi+\$0.142/mi)	\$ 150.15
5757 Drill Truck	1 trips X 550 mi	@(\$0.293/mi+\$0.141/mi)	\$ 238.70
FWD Van	1 trips X 550 mi	@(\$0.250/mi+\$0.150/mi)	\$ 220.00

2003 Final Report

Senior R & D Engineer	160 hours	@ \$24.00/hr	\$ 3,840.00
Salary Additive		(@67%)	\$ 2,572.80

TOTAL FOR 2003

\$ 12,887.75

TOTAL RD&T PROJECT COST

\$91,170.65

APPENDIX C

Mix Designs

MISSOURI HIGHWAY AND TRANSPORTATION DEPARTMENT - DIVISION OF MATERIALS

SAF98-3

ASPHALTIC CONCRETE SAND ANTI-FRACTURE MIXTURE

JOB NO.- J110737

PROJECT ACIM-ACIMG-29-2(139)

ROUTE- I-29

COUNTY- Holt

DATE- 6/18/98

PRODUCT CODE / FACILITY CODE / PRODUCER-LOCATION	IDENT.	BULK SP. GR.	APPAR. SP. GR.	FORMATION / LEDGES / % CHERT	% ABS
1002SGAFLS / 3061800211 / Ideker-Amazonia Quarry, Amazonia, MO	98- 4631	2.343	2.733	Plattsmouth / 3P	6.1
1002SGAFLS / 3030693411 / Martin Marietta No. 934, Savannah, MO	98- 5372	2.530	2.742	Amazonia / 8AZ	3.0
1002MSAFMS / 3030693411 / Martin Marietta No. 934, Savannah, MO	98- 4629	2.540	2.760	Amazonia / 8AZ	3.1
1002FAAFNS / 3020700111 / Holliday S&G No. 1, St. Joseph, MO	98- 4628	2.615	2.644	Missouri River Sand	0.4

1015ACPG. 70-34 / 3025937027 / Koch No. 2370, Muskogee, OK 98- 5269 1.016 PG 70-34 Gyro Mold Temp. 275° F

MATERIAL IDENT.	98- 4631	98- 5372	98- 4629	98- 4628		98- 4631	98- 5372	98- 4629	98- 4628	COMB
98-3	LSS	LSS	MFS	NS	PERCENT	20.0	20.0	25.0	35.0	GRAD
3/4"	100.0	100.0	100.0	100.0		20.0	20.0	25.0	35.0	100.0
1/2"	100.0	100.0	100.0	100.0		20.0	20.0	25.0	35.0	100.0
3/8"	100.0	99.8	100.0	100.0		20.0	20.0	25.0	35.0	100.0
#4	98.0	71.2	100.0	99.9		19.6	14.2	25.0	35.0	93.8
#8	78.1	43.3	63.5	98.3		15.6	8.7	15.9	34.4	74.6
#16	56.6	28.4	34.1	93.2		11.3	5.7	8.5	32.6	58.1
#30	43.9	21.0	18.1	75.3		8.8	4.2	4.5	26.4	43.9
#50	33.6	16.6	8.2	29.1		6.7	3.3	2.1	10.2	22.3
#100	26.9	14.0	2.8	0.2		5.4	2.8	0.7	0.1	9.0
#200	25.1	12.5	1.6	0.1		5.0	2.5	0.4	0.0	7.9

LABORATORY CHARACTERISTICS	AASHTO T-4	Gmm= 2.315	Gsb= 2.531	Gyro Wt.= 4600		25 GYRATIONS (Ndes)	% VOIDS= 1.4	VMA= 17.6	Gmb= 2.283	Hveem	Stab. = 18	50 GYRATIONS (Nmax)	% VOIDS= 1.1	VMA= 17.3	Gmb= 2.290	Hveem	Stab. = 24	MIX COMPOSITION	MIN. AGG. 91.4 %	BINDER CONTENT 8.6 %
CALIBRATION NUMBER	MASTER GAUGE SERIAL NO.	= 80069	= 770			MAST. GA. BACK. CNT. =	2215	SAMPLE WEIGHT =	8100	A1 =	1.368282	A2 =	2.142846	Test Temp. =	538° C	Correction Factor =	0.37	Min. Test Wt. =	1200	

MISSOURI DEPARTMENT OF TRANSPORTATION - DIVISION OF MATERIALS

SP190 98-36 R3

ASPHALTIC CONCRETE TYPE SP190

JOB NO.= J110737

PROJECT ACIM-ACIMG-29-2(139)

ROUTE= I-29

COUNTY= Holt

DATE= 7/28/98

PRODUCT CODE / FACILITY CODE / PRODUCER-LOCATION								IDENT.	BULK SP. GR.	APPAR. SP. GR.	FORMATION / LEDGES / % CHERT				ABS.
100207SPLSE / 3030693411 / Martin Mari #934, Savannah, MO								98- 4510	2.554	2.730	Amazonia / 8AZ				2.5
100204SPLSE / 3030693411 / Martin Mari #934, Savannah, MO								98- 4511	2.538	2.739	Amazonia / 8AZ				2.9
100204SPLSE / 3030693411 / Martin Mari #934, Savannah, MO								98- 4362	2.532	2.764	Amazonia / 8AZ				3.3
1002MSACMS / 3030693411 / Martin Mari #934, Savannah, MO								98- 4363	2.582	2.775	Amazonia / 8AZ				2.7
100204ACGV / 3028501411 / Lyman Richey #14, Plattsmouth, Nebraska								98- 4364	2.568	2.631	Platte Fl.				0.9
1002HLACHL / 3001704018 / Ash Grove Cement Co., Springfield, MO								98- 691	2.251	Hyd. Lime					
1015ACPG.64-22 / 3042000124 / Shell Oil, Kansas City, MO (Mfg., Wood River, IL)								98- 1156	1.032	PG 64-22 Gyro Mold Temp. 286°-297°F					
MATERIAL IDENT.	98- 4510	98- 4511	98- 4362	98- 4363	98- 4364	98- 691		98- 4510	98- 4511	98- 4362	98- 4363	98- 4364	98- 691	COMB	
98036	19.0 mm	9.5 mm	9.5 mm	MFS	GV	HL	PERCENT	27.0	20.0	18.5	23.5	10.0	1.0	GRAD	
3/4"	100.0	100.0	100.0	100.0	100.0	100.0		27.0	20.0	18.5	23.5	10.0	1.0	100.0	
1/2"	57.9	100.0	100.0	100.0	100.0	100.0		15.6	20.0	18.5	23.5	10.0	1.0	88.6	
3/8"	23.9	100.0	100.0	100.0	100.0	100.0		6.5	20.0	18.5	23.5	10.0	1.0	79.5	
#4	3.6	26.9	42.2	99.8	88.4	100.0		1.0	5.4	7.8	23.5	8.8	1.0	47.5	
#8	3.3	4.9	3.5	68.2	64.0	100.0		0.9	1.0	0.6	16.0	6.4	1.0	25.9	
#16	3.1	3.8	2.7	38.2	42.5	100.0		0.8	0.8	0.5	9.0	4.3	1.0	16.4	
#30	3.0	3.6	2.4	22.1	27.0	100.0		0.8	0.7	0.4	5.2	2.7	1.0	10.8	
#50	2.9	3.5	2.1	12.0	15.6	100.0		0.8	0.7	0.4	2.8	1.6	1.0	7.3	
#100	2.7	3.4	1.9	5.9	9.4	99.5		0.7	0.7	0.4	1.4	0.9	1.0	5.1	
#200	2.4	3.2	1.7	3.7	6.0	99.0		0.6	0.6	0.3	0.9	0.6	1.0	4.0	
LABORATORY CHARACTERISTICS	Gmm=		2.449	% VOIDS=		4.0	TSR=	83	Nini=		9	MIX COMPOSITION			
AASHTO TP4	Gmb=		2.351	V.M.A. =		13.0	-200/AC=	1.1	Ndee=		126	MIN.AGG.		94.4 %	
	Gab=		2.551	% FILLED=		69	Gyro Wt.=	4800	Nmax=		204	ASPHALT CONTENT		5.6 %	

CALIBRATION NUMBER = 80104 MAST. GA. BACK. CNT.= 2211 A1 = 4.489089 Test Temp.= 538°C
 MASTER GAUGE SERIAL NO. = 770 SAMPLE WEIGHT = 7300 A2 = 3.183645 Correction Factor= +0.06

*Mixture properties based on contractor's mix design.

MISSOURI DEPARTMENT OF TRANSPORTATION - DIVISION OF MATERIALS

SP125 08-38R2

ASPHALTIC CONCRETE TYPE SP125

JOB NO.- J110737
 PROJECT- ACM-ACMG-29-2(139) ROUTE- I-29 COUNTY- Holt DATE- 7/26/96

PRODUCT CODE / FACILITY CODE / PRODUCER-LOCATION							IDENT.	BULK SP. GR.	APPAR. SP. GR.	FORMATION / LEDGES / % CHERT			% ABS.	
100207SPLSE / 3030883411 / Martin Marietta No. 934, Savannah, MO							98- 4510	2.554	2.730	Amazonia / 8AZ			2.5	
100204SPLSE / 3030883411 / Martin Marietta No. 934, Savannah, MO							98- 4511	2.538	2.739	Amazonia / 8AZ			2.9	
100204SPLSE / 3030883411 / Martin Marietta No. 934, Savannah, MO							98- 4362	2.532	2.764	Amazonia / 8AZ			3.3	
1002MSACMS / 3030883411 / Martin Marietta No. 934, Savannah, MO							98- 4363	2.582	2.775	Amazonia / 8AZ			2.7	
100204ACGV / 3028501411 / Lyman Richey #14, Plattsmouth, Nebraska							98- 4364	2.568	2.831	Platte River			0.9	
100204HLACHL / 3001704018 / Ash Grove Cement Co., Springfield, MO							98- 691	2.251	Hyd. Lime					
1015ACPG. 64-22 / 3042000124 / Shell Oil, Kansas City, MO (Mfg. Wood River, IL)							98- 1156	1.032	PG 64-22 Gyro Mold Temp. 286°-297°F					
MATERIAL	98-	98-	98-	98-	98-	98-		98-	98-	98-	98-	98-	98-	
IDENT.	4510	4511	4362	4363	4364	691		4510	4511	4362	4363	4364	691	COMB
98038	19.0 mm	9.5 mm	9.5 mm	MFS	GV	HL	PERCENT	15.0	21.0	24.0	29.0	10.0	1.0	GRAD
1"	100.0	100.0	100.0	100.0	100.0	100.0		15.0	21.0	24.0	29.0	10.0	1.0	100.0
3/4"	100.0	100.0	100.0	100.0	100.0	100.0		15.0	21.0	24.0	29.0	10.0	1.0	100.0
1/2"	57.9	100.0	100.0	100.0	100.0	100.0		8.7	21.0	24.0	29.0	10.0	1.0	93.7
3/8"	23.9	100.0	100.0	100.0	100.0	100.0		3.6	21.0	24.0	29.0	10.0	1.0	88.8
#4	3.6	26.9	42.2	99.8	88.4	100.0		0.5	5.6	10.1	26.9	8.6	1.0	54.9
#6	3.3	4.9	3.5	68.2	64.0	100.0		0.5	1.0	0.8	19.8	6.4	1.0	29.5
#16	3.1	3.8	2.7	36.2	42.5	100.0		0.5	0.8	0.8	11.1	4.3	1.0	18.3
#30	3.0	3.6	2.4	22.1	27.0	100.0		0.5	0.8	0.8	6.4	2.7	1.0	12.0
#50	2.9	3.5	2.1	12.0	15.6	100.0		0.4	0.7	0.5	3.5	1.6	1.0	7.7
#100	2.7	3.4	1.9	5.9	9.4	99.5		0.4	0.7	0.5	1.7	0.9	1.0	5.2
#200	2.4	3.2	1.7	3.7	6.0	99.0		0.4	0.7	0.4	1.1	0.6	1.0	4.2
LABORATORY CHARACTERISTICS	Gmm=		2.438	% VOIDS=		4.0	TSR=	83	Nini=	8	MIX COMPOSITION			
AASHTO TP4	Gmb=		2.340	V.M.A. =		14.9	-200/AC=	0.8	Ndee=	109	MIN. AGG.		93.7 %	
	Gab=		2.576	% FILLED=		73	Gyro WL=	4800	Nmax	174	ASPHALT CONTENT		6.3 %	

CALIBRATION NUMBER = 80090 MAST. GA. BACK CNT. = 2205 A1 = 4.288963 Test Temp. = 538°C
 MASTER GAUGE SERIAL NO. = 770 SAMPLE WEIGHT = 7500 A2 = 3.101697 Correction Factor = +0.06%

*Mixture Properties Based on Contractor's Design

APPENDIX D

SAF Special Provisions

Q. EXPERIMENTAL SAND ANTI-FRACTURE MIXTURE MSP-97-10

1.0 Description of MSP-97-10. This specification covers materials and construction requirements for producing and placing a Sand Anti-Fracture (SAF) bituminous mixture to be placed in one course in conformance with the lines, grades, and typical cross sections shown on the plans, or established by the engineer.

1.1 Unless otherwise stated, specification section references are from the English version, in effect at the time of this contract, of the Missouri Standard Specifications for Highway Construction and its supplements.

1.2 SAF bituminous mixture is a fine graded highly elastomeric polymer modified asphalt cement mixture. The SAF bituminous mixture shall meet all the requirements for asphaltic concrete in Sec 403, except as modified herein. Delete Sec 403.1 through 403.5 and subsections, Sec 403.8, Sec 403.13.1, Sec 403.18.1 and Sec 403.18.5.

2.0 Materials. All materials shall conform to Division 1000, Materials Details, unless otherwise noted.

2.1 Asphalt Cement. The asphalt cement shall be PG 70-34 meeting Sec 1015 and shall be Styrene-Butadiene (SB) or Styrene-Butadiene Styrene (SBS) polymer modified. In addition, the asphalt cement shall meet the following:

- Force Ductility Ratio, ASTM P226 0.8 minimum @ 4°C
- RTFO Elastic Recovery, ASTM D5976-96 Sec 6.2 75% minimum @ 25°C
- Separation Test, ASTM D5976-96 Sec 6.1 8°F difference max. after 48hr.
- Solubility in Trichloroethylene, AASHTO T 44 99.0% minimum

2.2 Blended Aggregate. The blended aggregate shall consist of natural sands, crusher fines and screenings which meet Sec 1002.2.1, except the non-plastic requirement shall not apply. In addition, it shall meet the following.

2.2.1 Gradation. The combined gradation shall meet the following ranges.

<u>Sieve</u>	<u>Percent Passing</u>
3/8 inch	100
No. 4	80 - 100
No. 8	60 - 85
No. 16	40 - 65
No. 30	30 - 55
No. 50	18 - 32
No. 100	8 - 18
No. 200	7 - 14

2.2.2 Natural Sand. No more than 50% natural sand by weight shall be used.

2.2.3 Sand Equivalent. The sand equivalent of the total blend shall be a minimum of 70% as determined by AASHTO T 176.

2.3 Material Acceptance. All aggregates shall be sampled, tested, and approved by the engineer, prior to use.

3.0 Job Mix Formulas. The contractor shall contact Larry Reddick, Koch Materials Company, 4915 Chelsea, Kansas City, Missouri, 64130-2623, (816) 922-3413, for preparation of the job mix formulas. Koch Materials Company will provide the testing equipment to perform the Force Ductility Ratio testing, the Hveem Stability testing and the Complex Shear Modulus testing, and will provide personnel to conduct the testing in the field lab. Koch Materials Company will provide technical support for production and placement of the SAF mixture.

3.1 The manufacturer of the SAF bituminous mixture shall obtain, in the presence of the engineer, representative samples of asphalt cement and mineral aggregates for tests. The samples of materials shall be of the size specified by the engineer and shall be submitted to the Central Laboratory for testing. The manufacturer shall also develop and submit the job mix formula and present certified test results for the engineer's approval. At least 60 days prior to the manufacturer preparing any of the mixture on the project, the engineer shall have received both the representative samples of the job mix materials and the manufacturer's proposed job mix formula.

3.1.1 No mixture will be accepted for use until the job mix formula for the project is approved by the engineer.

3.1.2 The job mix formula shall be within the master range specified for the SAF bituminous mixture, and shall include the type and sources of all materials, the gradations of the aggregates, the relative quantity of each ingredient, and shall state a definite percentage for each sieve fraction of aggregate and for asphalt cement.

3.1.3 The job mix formula approved for the SAF bituminous mixture shall be in effect until modified in writing by the engineer. When unsatisfactory results or other conditions occur, or should a source of material be changed, a new job mix formula may be requested.

3.2 Proportioning. The engineer will approve the job mix formula and all materials and methods prior to use and will approve the proportions to be used within the following limits.

Asphalt cement, percent	7.5 - 10
Additives	As required

3.3 Mixture Testing Procedures.

3.3.4 SAF bituminous mixture shall be tested in accordance with AASHTO Provisional Standard TP 4, Edition 1C, Standard Method for Preparing and Determining the Density of Hot Mix Asphalt (HMA) Specimens by Means of the SHRP Gyrotory Compactor, except as herein noted.

3.4 Compaction Criteria.

3.4.1 The number (N) of gyrations required for gyrotory compaction shall be as follows:

	<u>N_{design}</u>	<u>N_{max.}</u>
Revolutions:	25	50
Voids in the Mineral Aggregate (VMA):	18 - 24	18 - 24
Air Voids (V _a), percent:	1.5 - 2.5	0.5 - 2.0
Hveem Stability @ 60°C	20+	20+
Complex Shear Modulus, MPa, 1hz, 20°C:	100 - 150	—

4.0 Construction Requirements.

4.1 Surface preparation. Immediately prior to applying the SAF bituminous mixture, the surface shall be thoroughly cleaned of all vegetation, loose materials, dirt, mud, visible moisture and other objectionable materials, and blown dry with a jet drier as required.

4.2 Weather Limitations. SAF mixtures shall not be placed when either the air temperature or the temperature of the surface on which the SAF mixture is to be placed is below 50°F.

4.3 Application of Tack. The tack coat shall be applied as set forth in Sec 407 and shall be applied between all layers.

4.4 Gradation Control. In producing SAF mixtures for the project, the plant shall be operated so that no intentional deviations from the job mix formula are made, except as approved by the engineer. The maximum deviation from the approved job mix formula shall be as follows:

<u>Sieve</u>	<u>Maximum Tolerance</u> <u>(Percent Passing by Weight)</u>
No. 8	± 3.0
No. 200	± 1.0

4.5 Asphalt Content. The asphalt content shall be within ± 0.5% of the approved job mix formula.

4.6 Spreading and Finishing. It is recommended that the plant be hot before beginning production of the SAF mixture. The SAF layer shall have an average thickness of 1 inch and shall have a minimum thickness of 5/8 inch.

4.6.1 Density. Density of the in-place SAF mixture shall be 98 ± 1% of the maximum specific gravity as determined by AASHTO T 209. Compaction operations shall start promptly after placement of the SAF mixture. Compaction temperature ranges shall be as provided by the asphalt cement supplier. SAF mixture shall be compacted in pavement deformities greater than 3/4 inch in depth in front of the paver. Deformities larger than 3 inches in depth shall be filled with approved SP125, SP190 or I-C mixture prior to placement of the SAF mixture.

4.6.2 The SAF mixture shall be covered with the binder course within 5 days after placement.

4.7 Verification specimens of the SAF mixture produced for the project shall be made in accordance with MSP-95-03N "Superpave Asphaltic Concrete Pavement".

4.7.1 The Voids in the Mineral Aggregate (VMA) and Air Voids (V_a) shall be within $\pm 1.0\%$ of the approved job mix formula when compacted to N_{design} .

4.8 Test Strip. This work shall consist of constructing SAF bituminous test strips for each mix design to determine the compactive effort necessary to provide the specified density.

4.8.1 Test strips shall be constructed after approval of a job mix formula and calibration of the SAF bituminous mixing plant. Tack coat shall be applied to the roadbed section followed by the placement of approximately 250 tons or one hour's production, whichever is less, of approved mix in a single lane within the project limits. The paver and rollers to be used on the project shall be used to put down the test strip. Separate test strips shall be provided for each mix design. Acceptable test strips shall meet density and all other specification requirements for the mixture tested.

4.8.2 Density will be determined in accordance with this specification. Steel wheel rollers in the static mode shall be used for compaction of the mixture. Pneumatic rollers and steel wheel rollers in the vibratory mode shall not be used. If necessary additional test strips shall be constructed until a rolling pattern has been established which will provide the specified density. A new test strip shall also be required whenever a change in the job mix formula occurs, the compaction method or the compaction equipment is changed or unacceptable results occur. Test strips which do not have the specified density shall be removed as directed by the engineer. No additional mix shall be laid until a rolling pattern, acceptable to the engineer, has been established on a test strip.

4.8.3 The materials in test strips approved by the engineer will be paid for at the unit price bid for those materials as provided in the contract. All materials in unacceptable test strips removed by the contractor shall become the property of the contractor and will be disposed of by the contractor at the expense of the contractor.

4.9 Any traffic damaged or marred areas shall be repaired by the contractor at no additional charge.

5.0 Method of Measurement.

5.1 Measurement of SAF bituminous mixture complete in place, including any multiple passes or courses, will be made to the nearest square yard. Measurement of individual passes or courses will not be made. Final measurement of the completed surface will not be made except for authorized changes during construction, or where appreciable errors are found in the contract quantity. The revision or correction will be computed and added to or deducted from the contract quantity.

6.0 Basis of Payment.

6.1 The accepted quantity of SAF bituminous mixture will be paid for at the contract unit price for SAF bituminous mixture, per square yard.

R. SUPERPAVE ASPHALTIC CONCRETE PAVEMENT MSP-95-03N

1.0 DESCRIPTION OF MSP-95-03N. This work shall consist of providing a SuperPave bituminous mixture (Type SP125, SP125LP, SP190, or SP250) to be placed in one or more courses on a prepared base or underlying course in conformance with the lines, grades, thicknesses, and typical cross sections shown on the plans, or established by the engineer.

1.1 Unless otherwise stated, specification section references are from the English version, in effect at the time of this contract, of the Missouri Standard Specifications for Highway Construction and its supplements.

1.2 SuperPave (SP) bituminous mixtures are dense graded bituminous mixtures compacted in the Laboratory with a SuperPave Gyrotory Compactor. The bituminous mixtures shall meet all the requirements for asphaltic concrete in Sec 403, except as modified herein. Delete Sec 403.1 through 403.5 and subsections.

2.0 MATERIALS. All materials shall conform to Division 1000, Materials Details, unless otherwise noted.

2.1 Asphalt Cement. The asphalt cement shall be a Performance Graded material of the grade specified in the contract for the SP125, SP125LP, SP190 and SP250 mixtures.

2.2 Aggregates. Aggregates shall meet the requirements of Sec 1002 for Type I-C when a SP125/SP125LP mixture is specified and for Type I-B when a SP190 or SP250 mixture is specified except as herein modified.

2.2.1 Sec 1002.1.1.1, 1002.1.3.1, 1002.1.5, 1002.1.8, 1002.2.2, and 1002.2.3 will not apply. However, gravel aggregates shall be washed sufficiently to remove any objectionable coating, and crushing of gravel aggregates will be required to meet the coarse or fine aggregate angularity specified herein.

2.2.2 Fine aggregates manufactured by the mechanical reduction of sound durable rock shall be manufactured from ledges which meet the same soundness requirements as for the coarse aggregate.

2.2.3 Blended Aggregate. The blended aggregate shall meet the grading for the specified SP mixture.

2.2.3.1 For SP125LP mixtures, at least 50 percent by volume of the plus number 8 material shall be from crushed porphyry as specified in Sec 1002. Depending on the actual gradation of porphyry aggregate furnished, the amount of crushed porphyry required will vary, however at least 40 percent by weight of crushed porphyry will be required.

2.2.3.2 Material Limitations

2.2.3.2.1 Steel slag shall not exceed 20% by weight of the mineral aggregate for design ESAL's greater than three million. For ESAL's less than three million, no restriction will be placed on the amount of steel slag.

2.2.3.2.2 Flint chat produced in the Joplin area shall not exceed 10% by weight of the mineral aggregate.

2.2.3.2.3 Crushed gravel shall not exceed 20% by weight of the mineral aggregate.

2.2.3.3 Fine Aggregate Angularity. Fine aggregate angularity is measured on the fine portion of the blended aggregate. When tested in accordance with AASHTO TP-33 Method A, aggregate particles passing the No. 8 sieve shall meet the following criteria for the minimum percent air voids in loosely compacted fine aggregate.

Design Traffic (ESALs)	Mixture Depth from Surface	
	<u><=4 in.</u>	<u>>4 in.</u>
< 300,000	—	—
300,000 to < 1,000,000	40	—
1,000,000 to < 3,000,000	40	40
3,000,000 to < 30,000,000	45	40
30,000,000 to < 100,000,000	45	45
>=100,000,000	45	45

2.2.3.4 Coarse Aggregate Angularity. Coarse aggregate angularity is measured on the coarse portion of the blended aggregate. It is defined as the percent by weight of the aggregate particles larger than #4 sieve with one or more fractured faces. A fractured face is an angular, rough, or broken surface of an aggregate particle created by crushing or other artificial means. When tested in accordance with ASTM D 5821, "Standard Test Method for Determining the Percentage of Fractured Particles in Coarse Aggregate", the coarse aggregate shall meet the following criteria. As shown, the criteria denotes the minimum allowable percentage of the coarse aggregate with "one / two" fractured faces, e.g. an "85/80" requirement means that the coarse aggregate shall have a minimum of 85 percent particles by weight with one fractured face and a minimum of 80 percent particles by weight with two fractured faces.

Design Traffic (ESALs)	Mixture Depth from Surface	
	<u><= 4 in.</u>	<u>> 4 in.</u>
<300,000	55/-	-/-
300,000 to <1,000,000	65/-	-/-
1,000,000 to <3,000,000	75/-	50/-
3,000,000 to <10,000,000	85/80	60/-
10,000,000 to <30,000,000	95/90	80/75
30,000,000 to <100,000,000	100/100	95/90
>=100,000,000	100/100	100/100

2.2.3.5 Clay Content. When tested in accordance with AASHTO T 176, aggregate particles passing the No. 4 sieve shall meet the following sand equivalent criteria.

<u>Design Traffic (ESALs)</u>	<u>Sand Equivalent</u>
< 3,000,000	40
3,000,000 to < 30,000,000	45
>=30,000,000	50

2.2.3.6 Thin, Elongated Particles. For design traffic ESALs greater than 1,000,000, no more than 10 percent of the blended aggregate particles retained on the No. 4 sieve shall have a ratio of maximum to minimum dimensions greater than 3 when tested in accordance with ASTM D 4791.

3.0 COMPOSITION OF MIXTURES.

3.1 Prior to mixing with asphalt cement, the combined aggregate gradation, including filler if needed, shall meet the following gradation for the type of mixture specified in the contract.

Percent Passing by Weight

<u>Mixture-</u>	<u>SP250</u>	<u>SP190</u>	<u>SP125/SP125LP</u>
	(1 in.)	(3/4 in.)	(1/2 in.)
<u>Sieve Size</u>	<u>Nom. Max. Size)</u>	<u>Nom. Max. Size)</u>	<u>Nom. Max. Size)</u>
1 1/2 in.	100	—	—
1 in.	90-100	100	—
3/4 in.	90 max.	90 - 100	100
1/2 in.	—	90 max.	90 - 100
3/8 in.	—	—	90 max.
No. 8	19-45	23 - 49	28 - 58
No. 200	1-7	2 - 8	2 - 10

3.1.1 The combined aggregate gradation shall not pass through the restricted zone as shown in the table below and as plotted on a 0.45 power chart.

<u>Sieve Size</u>	<u>SP250</u>	<u>Aggregate Restricted Zone</u>	
		<u>SP190</u>	<u>SP125/SP125LP</u>
No. 4	39.5	—	—
No. 8	26.8-30.8	34.6	39.1
No. 16	18.1-24.1	22.3-28.3	25.6-31.6
No. 30	13.6-17.6	16.7-20.7	19.1-23.1
No. 50	11.4	13.7	15.5

3.1.2 A job mix formula may be approved which permits the combined aggregate gradation to be outside the limits of the master range when the full tolerances specified herein are applied.

3.1.3 All mixtures shall contain a minimum of one percent hydrated lime in accordance with Sec 403.5(e).

4.0 JOB MIX FORMULAS.

4.1 General. The contractor shall provide the job mix formula for each mixture. Representative samples of asphalt cement and mineral aggregates shall be submitted to the Central Laboratory for mixture verification. At least 30 days prior to the contractor preparing any of the mixture on the project, the engineer shall have received both the representative samples of the job mix materials and the contractor's proposed job mix formula.

4.1.1 The mix design shall contain the following information:

- a. Source, grade and specific gravity of asphalt cement.
- b. Source, type (formation, etc.), ledge number if applicable, and gradation of the aggregates.
- c. Bulk and apparent specific gravities of each aggregate fraction in accordance with AASHTO T85 for coarse aggregates and AASHTO T84 for fine aggregates.
- d. Specific gravity of hydrated lime or mineral filler, if used, in accordance with AASHTO T100.
- e. Percentage of each aggregate component.
- f. Combined gradation of the job mixture.
- g. Percent asphalt cement, by weight, based on the total mix.

h. Bulk specific gravity (G_{mb}) by AASHTO T166 Method A of a laboratory compacted mixture compacted N_{design} gyrations .

i. Percent air voids (V_a) of the laboratory compacted specimen compacted to N_{design} gyrations .

j. Voids in the mineral aggregate (VMA) and voids in the mineral aggregate filled with asphalt cement (VFA) at N_{design} gyrations.

k. Maximum specific gravity (G_{mm}) as determined by AASHTO T209 after the sample has been short term aged in accordance with AASHTO TP4 , Edition 1D.

l. The tensile strength ratio as determined by AASHTO T283.

m. The gyratory sample weight to produce a 115 mm minimum height specimen.

n. Gyratory molding temperature.

o. Number of gyrations at $N_{initial}$, N_{design} , and $N_{maximum}$.

p. Dust proportion ratio ($-200/P_{be}$).

q. Bulk specific gravity (G_{sb}) of the combined aggregate.

4.1.2 No mixture will be accepted for use until the job mix formula for the project is approved by the engineer.

4.1.3 The job mix formula shall be within the master range specified for the particular type of asphaltic concrete, and shall include the type and sources of all materials, the gradations of the aggregates, the relative quantity of each ingredient, and shall state a definite percentage for each sieve fraction of aggregate and for asphalt cement.

4.1.4 The job mix formula approved for each mixture shall be in effect until modified in writing by the engineer. When unsatisfactory results or other conditions occur, or should a source of material be changed, a new job mix formula may be required.

4.2 Mixture Testing Procedures.

4.2.1 SP bituminous mixtures shall be tested in accordance with AASHTO Provisional Standard TP 4, Edition 1D, Standard Method for Preparing and Determining the Density of Hot Mix Asphalt (HMA) Specimens by Means of SHRP Gyratory Compactor, except as herein noted.

4.2.2 SP mix design shall follow the procedures defined for Level 1, Chapter 3, of SHRP Publication SHRP-A-407, the SuperPave Mix Design Manual for New Construction and Overlays.

4.2.3 The contractor is advised that SP mix design will require gradation design, asphalt cement content design, moisture susceptibility testing, and nuclear gauge calibration. It may also require testing of the blended aggregate once the mixture design is completed. MoDOT will perform the nuclear gauge calibration at the time of the mixture verification.

4.3 Compaction Criteria.

4.3.1 The number (N) of gyrations required for gyratory compaction shall be as follows:

<u>(ESALs)</u>	$N_{initial}$	N_{design}	$N_{maximum}$
< 300,000	7	68	104
300,000 to < 1,000,000	7	76	117
1,000,000 to < 3,000,000	7	86	134
3,000,000 to < 10,000,000	8	96	152
10,000,000 to < 30,000,000	8	109	174
30,000,000 to < 100,000,000	9	126	204
\geq 100,000,000	9	143	235

In addition, the compaction level, as a percent of theoretical maximum specific gravity, shall be less than 89 percent at $N_{initial}$, equal to 96 percent at N_{design} , and less than 98 percent at $N_{maximum}$.

4.3.2 When compacted in accordance with AASHTO Provisional Standard TP4, Edition 1D, the mixture shall meet the following criteria.

4.3.2.1 Air Voids (V_a).

<u>(ESALs)</u>	<u>Design Air Voids (percent)</u>
All Levels	4.0

4.3.2.2 Voids in the Mineral Aggregate (VMA).

<u>Mixture</u>	<u>VMA Minimum (percent)</u>
SP250	12.0
SP190	13.0
SP125/SP125LP	14.0

4.3.2.3 Voids Filled With Asphalt (VFA).

<u>(ESALs)</u>	<u>VFA (percent)</u>
< 300,000	70-80
300,000 to <3,000,000	65-78
>= 3,000,000	65-75

4.4 Other Criteria.

4.4.1 The ratio of minus No. 200 material to effective asphalt cement (P_{be}) shall be between 0.6 and 1.2.

4.4.2 The mixture shall have a tensile strength ratio (TSR) greater than 80 percent when tested in accordance with AASHTO T 283. Specimens for AASHTO T 283 shall be compacted to 95mm with 7 ± 1 percent air voids.

4.5 If difficulty is experienced in obtaining a satisfactory mixture with the aggregate combinations submitted, the contractor will be advised and new types or sources of materials may be required by the engineer. Note that additional aggregate other than local stone or sand such as a clean 3/8" chip or well graded manufactured sand composed of quality material, porphyry or higher quality limestone may be required in order to modify the mixture for compliance.

5.0 CONSTRUCTION. For the purposes of placement, SP250/SP190 shall be treated like Type I-B mixture and SP125/SP125LP like Type I-C mixture, except that the compacted thickness for SP250 shall be between 3 inches and 4 inches and the compacted thickness for SP190 shall be between 2 inches and 3 inches.

5.1 Weather Limitations.

5.1.1 SP190 and SP125/SP125LP mixtures shall be placed in accordance with the weather limitations of Sec 403.

5.1.2 SP250 mixtures shall be placed in accordance with the following weather limitations. SP250 mixtures shall not be placed (1) when either the air temperature or temperature of the surface on which the mixture is to be placed is below 40 F, (2) on any wet or frozen surface, or (3) when weather conditions prevent the proper handling or finishing of the mixture. Temperatures are to be obtained in accordance with MHTD Test Method T20.

5.2 Gradation Control. In producing mixtures for the project, the plant shall be operated so that no intentional deviations from the job mix formula are made. The maximum deviation from the approved job mix formula shall be as follows:

<u>Sieve</u>	<u>Max. Tolerance</u> <u>(Percent Passing by Mass)</u>
Nominal Maximum Sieve size for Mixture	± 5.0
No. 8	± 3.0
No. 200	± 1.0

5.3 Density. The final density of the in-place mixture shall be between 92 and 95 percent of the field determined maximum specific gravity (AASHTO T 209).

5.4 Asphalt Content. The asphalt content shall be within ±0.3 percent of the approved job mix formula.

5.5 Recompacted Mixture. When the produced mixture is recompacted using the SuperPave Gyratory Compactor, the mixture shall meet the following criteria.

5.5.1 The Voids in the Mineral Aggregate (VMA) shall be within ± 1.2 percent of the approved job mix formula at N_{design} gyrations. The VMA will be determined using the average field determined bulk specific gravity's (AASHTO T 166) of the two SuperPave gyratory compacted specimens, the field calculated percent aggregate, the field measured percent asphalt as determined by the nuclear gauge method MHTD Test Method T54-10-94 or binder ignition method AASHTO TP53-95, Edition 1A, and the job mix formula aggregate bulk specific gravity.

5.5.2 The air voids (V_v) shall be within ±1.0 percent of the approved job mix formula at N_{design} gyrations. The air voids will be calculated from the field determined maximum specific gravity's (AASHTO T 209) and the field determined bulk specific gravity's (AASHTO T 166).

5.6 Test Strips. Bituminous test strips shall be constructed for each SP mixture of 2000 tons or more per contract to determine the compactive effort necessary to provide the specified density.

5.6.1 The test strips shall be constructed after approval of a job mix formula and calibration of the bituminous mixing plant. Prime or tack coat, if specified, shall be applied to the roadbed section followed by the placement of approximately 250 tons or one hour's production, whichever is less, of approved mix in a single lane within the project limits. The paver and rollers to be used on the project shall be used to put down the test strip. Separate test strips shall be provided for each mixture, using the thickness specified on the typical section. If more than one thickness is used for a specified mixture, the thicker lift shall be placed in a test strip as a minimum. Test strips for subsequent lifts which incorporate a new mix design may, at the contractor's option, be placed after completion of the previous lift. Acceptable test strips shall meet density, gradation, percent asphalt cement, and the volumetric requirements of the contract.

5.6.2 Density will be determined. If necessary, additional test strips shall be constructed until a rolling pattern has been established which will provide the specified density. A new test strip shall also be required whenever a change in the job mix formula occurs, the compaction method or the compaction equipment is changed or unacceptable results occur. No additional mix shall be laid until a rolling pattern, acceptable to the engineer, has been established on a test strip.

5.6.3 The materials in test strips approved by the engineer will be paid for at the unit price bid for those materials as provided in the contract. Test strips which do not meet specification requirements for density, air void and voids in the mineral aggregate shall be removed. All materials in unacceptable test strips removed by the contractor shall become the property of the contractor and will be disposed of by the contractor at the contractor's expense.

5.6.4 Accepted test strips meeting requirements of Section 5.6.1 for the SP asphalt mix will be paid for at the contract unit price per test strip. No payment will be made for test strips required as a result of a contractor initiated change in job mix formula, compaction method, compaction equipment, or if unacceptable results occur as determined by the engineer.

6.0 PAYMENT. Payment for the above described work including all materials, equipment, labor, and any other incidental work necessary to complete this item shall be considered as completely covered by the unit price as set out in this proposal. The accepted quantities of SuperPave mixtures will be paid for at the contract unit price for asphalt cement (for PG Grade and mixture specified, SP125, SP125LP, SP190, or SP250, tons), and mineral aggregate (SP125, SP125LP, SP190, or SP250, ton).

6.1 In addition to any adjustments in pay due to profile, the contract unit price for the SuperPave mixture represented by each set of cores will be adjusted based on actual field density above or below the specified density using the following schedule. No cores shall be taken later than the day following placement for any payment purposes.

<u>Field Density</u>		<u>Pay Factor</u>
<u>Percent of laboratory maximum theoretical density</u>		<u>Percent of contract unit price</u>
	91.5 to 95.4 inclusive	100%
95.5 to 96.0	or 90.9 to 91.4 inclusive	97%
96.1 to 96.4	or 90.5 to 90.8 inclusive	94%
96.5 to 96.7	or 90.2 to 90.4 inclusive	90%
96.8 to 96.9	or 90.0 to 90.1 inclusive	80%
97.0 and above	or 89.9 and below	0%

S. SAND ANTI-FRACTURE INVESTIGATION MSP-98-01C

1.0 Description of MSP-98-01C. This specification includes the description of work to be performed on eight test sections located on Interstate 29, Holt County, on Job No. J110737 between Stations 790+02 and 1045+00.

1.1 Unless otherwise stated, specification section references are from the version, in effect at the time of this contract, of the Missouri Standard Specifications for Highway Construction and its supplements.

1.2 This specification explains the experimental features of eight test sections. The purpose of this investigation is to study rehabilitation methods for portland cement concrete pavement (PCCP). The test sections feature varying methods of pavement repair. Some sections include a Sand-Anti Fracture (SAF) layer. Two different performance graded binders are to be used in the SuperPave overlay. These test sections are explained in more detail in Section 2.5 of this specification.

2.0 General.

2.1 Contract specified tests and procedures shall govern the contractor's operations and the acceptance of the completed work. Due to the research nature of this project, there will be other extensive testing of materials and procedures during construction. Additional testing by the department or other interested parties for research purposes will not be used for contract compliance.

2.2 The contractor shall keep the engineer advised of all work schedules and changes. A schedule of work order is required seven days prior to work beginning and any changes, except those caused by weather or the engineer, shall be transmitted to the engineer in writing three days prior to the change in the work schedule occurring.

2.2.1 If notice of work schedule change is not received in the required time period, the contractor shall cease work until the required testing or data collection can be completed by the department or other interested parties.

2.3 The department and other interested parties shall be allowed access to all operations and be given the full cooperation of the contractor or approved subcontractors, whether work is accomplished on the project or at an off-site location.

2.4 Testing and Sampling. The contractor is advised that some testing or data collection, by department personnel, between operations may affect work scheduling. These possible interruptions will be discussed as part of the pre-construction meeting and are to be included as part of the required written work schedule. Some possible instances include but are not limited to the following.

2.4.1 Distress surveying of the PCCP prior to overlay.

2.4.2 Five point cross sectioning of the PCC pavement by MoDOT construction personnel prior to and after the placement of the overlay, for thickness measurement as described in Section 5.1.

2.4.3 Photographic record, taken by MoDOT construction personnel, within the minimum repair test section monitoring areas, of the PCCP joints that would have been repaired under normal pavement repair practices.

2.4.4 Sampling of the PCCP, base or subgrade by means of coring or test pits.

2.4.5 Sampling of the SAF and asphaltic concrete by coring and bulk sampling.

2.4.6 Marking of the surface course of the asphaltic concrete by MoDOT Research, Development & Technology (RD&T) personnel as described in Section 5.2.

2.5 **Test Section Locations and General Descriptions.** There are eight test sections to be constructed on this project as listed below. NBL and SBL refer to Northbound Lane and Southbound Lane, respectively. The specified pavement treatments will span the full width of the roadway as described in this contract.

<u>TEST SECTION #</u>	<u>LIMITS</u>	<u>GENERAL DESCRIPTION</u>
1	1045+00 to 992+00 (NBL)	5 3/4" Asphalt Overlay with PG 64-28 Normal Pavement Repair
2	992+00 to 939+00 (NBL)	5 3/4" Asphalt Overlay with PG 64-28 Minimum Pavement Repair
3	939+00 to 864+00 (NBL)	5 3/4" Asphalt Overlay with PG 64-28 1" SAF Minimum Pavement Repair
4	864+00 to 790+02 (NBL)	5 3/4" Asphalt Overlay with PG 76-28 1" SAF Minimum Pavement Repair
5	790+02 to 844+00 (SBL)	3 3/4" Asphalt Overlay with PG 76-28 1" SAF Normal Pavement Repair
6	844+00 to 992+00 (SBL)	3 3/4" Asphalt Overlay with PG 76-28 1" SAF Minimum Pavement Repair
7	992+00 to 1018+00 (SBL)	3 3/4" Asphalt Overlay with PG 64-28 1" SAF Minimum Pavement Repair

<u>TEST SECTION #</u>	<u>LIMITS</u>	<u>GENERAL DESCRIPTION</u>
8	1018+00 to 1045+00 (SBL)	3 3/4" Asphalt Overlay with PG 64-28 1" SAF Normal Pavement Repair

2.5.1 Monitoring Areas and Numbering Scheme. Due to the 10 mile total project length, the actual RD&T monitoring area will be reduced to shorter 500 - 1000 foot lengths within the 0.5 - 3 mile test section. In addition, test section 6 will have two 1000 foot monitoring areas, because of its 3 mile length. The other test sections will have one monitoring area each. These monitoring areas will be numbered as follows: 2900XY, where X is the test section number as shown in Section 2.5, and Y is the consecutive number of the monitoring area within that test section. For example, 290062 would be the second monitoring area within test section 6. 290051 would be the first monitoring area within test section 5. This numbering scheme will allow the test section data to be incorporated into an existing RD&T database.

2.5.2 Designated Sampling Areas. There will be a sampling area, for destructive testing, at the beginning and end of each of the nine monitoring areas. These sampling areas will be 100 feet in length and will not overlap the monitoring areas. They are referred to as Lead In and Lead Out in the following table.

<u>Monitoring Area No.</u>	<u>Limits</u>	<u>General Description</u>
290011	1045+00 to 992+00 (NBL) 1003+00 to 1002+00 1002+00 to 997+00 997+00 to 996+00	Test Section #1 Lead In Monitoring Area Lead Out
290021	992+00 to 939+00 (NBL) 963+00 to 962+00 962+00 to 952+00 952+00 to 951+00	Test Section #2 Lead In Monitoring Area Lead Out
290031	939+00 to 864+00 (NBL) 918+00 to 917+00 917+00 to 912+00 912+00 to 911+00	Test Section #3 Lead In Monitoring Area Lead Out
290041	864+00 to 790+02 (NBL) 838+00 to 837+00 837+00 to 827+00 827+00 to 826+00	Test Section #4 Lead In Monitoring Area Lead Out
290051	790+02 to 844+00 (SBL) 826+00 to 827+00 827+00 to 837+00 837+00 to 838+00	Test Section #5 Lead In Monitoring Area Lead Out

<u>Monitoring Area No.</u>	<u>Limits</u>	<u>General Description</u>
290061	844+00 to 992+00 (SBL)	Test Section #6
	848+00 to 849+00	Lead In
	849+00 to 859+00	Monitoring Area
	859+00 to 860+00	Lead Out
290062	951+00 to 952+00	Lead In
	952+00 to 962+00	Monitoring Area
	962+00 to 963+00	Lead Out
290071	992+00 to 1018+00 (SBL)	Test Section #7
	999+00 to 1000+00	Lead In
	1000+00 to 1005+00	Monitoring Area
	1005+00 to 1006+00	Lead Out
290081	1018+00 to 1045+00 (SBL)	Test Section #8
	1038+00 to 1039+00	Lead In
	1039+00 to 1044+00	Monitoring Area
	1044+00 to 1045+00	Lead Out

3.0 Pavement Repairs. The joints or cracks requiring pavement repair are specified in this contract, however the engineer reserves the right to require the repair of additional joints or cracks during construction. The designated pavement repair locations are not to be modified without concurrence from the engineer.

4.0 Sand Anti-Fracture. The Sand Anti-Fracture mixture shall be placed in accordance with the version of MSP-97-10 included in the contract.

5.0 SuperPave Asphaltic Concrete Overlay. Asphaltic concrete shall meet all the applicable requirements of the version of MSP-95-03 included in the contract.

5.1 Total Compacted Thickness Requirement. Due to the research nature of this work, the total final compacted thickness of the SuperPave asphaltic concrete overlay within the monitoring areas shall not vary more than ± 0.50 inch from the thickness required by the typical section.

5.1.1 The thickness will be based on the average of five point cross-sections taken at 100 foot intervals within the monitoring areas listed in Section 2.5.2.

5.1.2 If the above thickness tolerances are exceeded, the following deductions will apply for each monitoring area involved.

5.1.2.1 The contract price for all affected plan quantities for the deficient monitoring area will be reduced by 10 percent for a total variance of ± 0.50 inch to ± 1.00 inch.

5.1.2.2 Total variances greater than ± 1.00 inch are not acceptable. Pavement shall be removed and replaced to be within these tolerances to the satisfaction of the engineer.

5.2 Marking of Asphaltic Concrete Overlay. The asphaltic concrete surface immediately over the PCCP joints and working cracks will be permanently marked by RD&T personnel as follows.

5.2.1 A 4 inch x 4 inch square of thermoplastic pavement marking shall be placed in front of the finish roller immediately over the location of the PCCP joint in order to permanently mark the finished surface of the SuperPave asphaltic concrete over the joint. The thermoplastic square will be placed in front of the roller by a person standing on the shoulder of the roadway. This mark will allow the RD&T division to determine the existence of reflective cracks in the future.

5.2.2 The asphaltic concrete overlay will be marked within the monitoring areas.

5.2.3 The contractor shall fully cooperate with this marking operation. If the above described method of marking is unsatisfactory to the RD&T personnel, the contractor shall cooperate with any modifications as directed by the engineer.

5.2.4 There will be no additional pay for this marking operation. The thermoplastic squares will be provided and placed by the RD&T division.

5.3 Construction Joints. Due to the research nature of this project, it is necessary to provide continuous, uniform lifts beginning 500 feet before the lead in, and continuing throughout the monitoring and lead out areas. Transverse construction joints shall be avoided in these areas.

5.3.1 In the event that for any reason there is any transverse construction joint within these areas, at the contractor's expense the affected asphaltic concrete lift shall be completely removed to the full width of original placement by an approved method, to 500 feet before the lead in area and to the end of the lead out area, and the entire area replaced until a continuous, uniform lift meeting this specification has been provided. There will be no direct payment to the contractor for any expense involved in meeting this portion of the specification, other than as designated for approved work.