

LIBRARY  
RESEARCH REPORTS DIVISION  
NAVAL POSTGRADUATE SCHOOL  
MONTEREY, CALIFORNIA 93943

AD-A145201

THEORY OF NONLOCAL ELASTICITY  
AND SOME APPLICATIONS

A. Cemal Eringen  
PRINCETON UNIVERSITY

Technical Report No. 62  
Civil Engng. Res. Rep. No. 84-SM-9

Research Sponsored by the  
OFFICE OF NAVAL RESEARCH  
under  
Contract N00014-83-K-0126 Mod 4  
Task No. NR 064-410

August 1984

Approved for public release:  
Distribution Unlimited

Reproduction in whole or in part is permitted  
for any purpose of the United States Government

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM	
1. REPORT NUMBER #62	PRINCETON UNIVERSITY	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) THEORY OF NONLOCAL ELASTICITY AND SOME APPLICATIONS		5. TYPE OF REPORT & PERIOD COVERED technical report	
		6. PERFORMING ORG. REPORT NUMBER 84-SM-9	
7. AUTHOR(s) A. Cemal Eringen		8. CONTRACT OR GRANT NUMBER(s) N00014-83-K-0126 Mod 4	
9. PERFORMING ORGANIZATION NAME AND ADDRESS PRINCETON UNIVERSITY Princeton, NJ 08544		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 064-410	
11. CONTROLLING OFFICE NAME AND ADDRESS OFFICE OF NAVAL RESEARCH (Code 471) Arlington, VA 22217		12. REPORT DATE April 1984	
		13. NUMBER OF PAGES 55	
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified	
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report)			
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)			
18. SUPPLEMENTARY NOTES			
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) nonlocal elasticity, lattice dynamics, fracture mechanics, dislocations, dispersive waves, nonlocal elastic moduli			
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Constitutive equations of finite nonlocal elasticity are obtained. Thermodynamic restriction are studied. The linear theory is given for anisotropic and isotropic solids. The physical and mathematical properties of the nonlocal elastic moduli are explored through lattice dynamics and dispersive wave propagations. The theory is applied to the problems of surface waves, screw dislocation and a crack. Excellent agreements with the results			

DD FORM 1473 1 JAN 73 EDITION OF 1 NOV 63 IS OBSOLETE

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

known in atomic lattice dynamics and experiments display the power and potential of the theory.

# THEORY OF NONLOCAL ELASTICITY AND SOME APPLICATIONS

A. Cemal Eringen  
PRINCETON UNIVERSITY  
Princeton, NJ 08544

## ABSTRACT

Constitutive equations of finite nonlocal elasticity are obtained. Thermodynamic restriction are studied. The linear theory is given for anisotropic and isotropic solids. The physical and mathematical properties of the nonlocal elastic moduli are explored through lattice dynamics and dispersive wave propagations. The theory is applied to the problems of surface waves, screw dislocation and a crack. Excellent agreements with the results known in atomic lattice dynamics and experiments display the power and potential of the theory.

## 1. INTRODUCTION

All physical theories possess certain domain of applicability outside of which they fail to predict the physical phenomena with reasonable accuracy. While the boundaries of these domains are not known precisely, often the failure of a given mathematical model is indicated by its predictions that deviate considerably from experimental results or dramatically displayed by mathematical singularities that it leads to.

The domain of applicability of a theory is a function of some internal characteristic length and time scales of the media for which it is constructed. When these scales are sufficiently small as compared to the corresponding external scales, then the classical field theories give successful results. Otherwise, they fail.

Such is the situation with the classical elasticity theory which possesses no internal scales. Yet all elastic materials possess inner structures in the molecular and atomic scales. Consequently, when the external scales (such as wave length, period, the size of the area over which applied loads are continuous), becomes comparable with the inner scales (such as granular distance, relaxation time, lattice parameter), the theory fails to apply.

In classical elasticity, this situation is demonstrated dramatically by the singular stress field predicted at a sharp crack tip and the phase velocities that do not depend on wave lengths of propagating waves. As a result of the former a perfectly sensible physical criterion of fracture, based on maximum stress hypothesis, was replaced by various

ersatzs (e.g. Griffith energy, J-integral, etc). Clearly, the infinite stress is a sharp signal for the failure of the theory rather than the failure of the fracture criterion which must be based on the physical concept of cohesive stress. Regarding the phase velocity, at all wave lengths from infinite to the atomic distances, we have ample experimental measurements of dispersion curves. Only at the very large wave lengths is there an agreement with classically predicted constant phase velocity. Waves having short wave lengths have been observed to propagate with much smaller phase velocities and in fact they cease to propagate near the boundaries of the Brillouin zone.

The question arises: "Should we altogether abandon classical field theories and appeal to atomic theories only?" The answer depends on the characteristic scale ratios. Indeed if the motion of each atom in a body is essential for the description of a physical phenomenon, then the lattice dynamics is the only answer. If, on the other hand, the collective behavior of large number of atoms is adequate for the description, then continuum theory offers much simpler and practical methodology. Between these two extremes, there lies a large domain full of rich physical phenomena.

Real materials possess a very complicated inner structure full of dislocations and impurities. Moreover the force law among the substructure is not known. Consequently, it is virtually impossible to carry out calculations on the basis of the atomic theories. Even if it were possible to accomplish such voluminous and difficult computations, results would be of no practical value. All experimental probes possess some characteristic lengths so that they can only measure statistical averages. Consequently

we need to calculate theoretically certain statistical averages so that comparison can be made with experimental observations. Hence we are back in the domain of continuum. Thus, continuum theory makes sense on its own grounds, provided it is properly constructed to predict these averages with sufficient accuracy.

Linear theory of nonlocal elasticity, which has been proposed independently by various authors [1]-[6], incorporates important features of lattice dynamics and yet it contains classical elasticity in the long wave length limit. It is capable of addressing small as well as large scale phenomena. Large number of references on the topic may be found in [7]-[9]. Interested readers may also consult [10], [11] for the nonlocal fluid dynamics and [12], [13] for nonlocal electromagnetic continua.

Here I present the theory of nonlocal nonlinear elasticity from a continuum point of view. (See also [14]-[17]). Constitutive equations are given in Section 3, where I employ the global entropy inequality rather than the local Clausius-Duhem inequality to place restrictions on the constitutive functionals. In Section 4, I derive a special class of stress-strain law for the additive functionals. Isotropic solids are studied in Section 5 and linear theory is presented in Section 6.

In nonlocal elasticity, the stress at a point is regarded as a functional of the strain tensor. For linear, homogeneous solids, this introduces material moduli which are functions of the distance. Physical and mathematical properties of these moduli are studied in Section 7. Section 8 gives the field equations.

Applications of the linear theory begins with Section 9 to wave

propagation. Dispersion curves are obtained for the plane harmonic waves in an infinite solid and for surface waves. Results are in excellent agreement with the corresponding ones obtained by means of lattice dynamics. In Section 10, I determine the stress distribution due to a screw-dislocation. Cohesive stress that holds the atomic bonds together in a perfect crystal is found to coincide with the so-called theoretical stress estimated on the basis of atomic theory or experiments. The last section (Section 11) treats the crack tip problem for anti-plane case (Mode III). Contrary to the classical result, the crack tip stress vanishes at the tip and possesses a finite maximum near the tip. The maximum stress hypothesis of fracture can now be restored. This enables us to calculate the fracture toughness which is shown to agree well with experimental results on several materials.

These few examples are sufficient to demonstrate the power and potential of the theory. There exist several other solutions in the literature, dealing with dislocations, cracks, wave propagations, defects, continuous distribution of dislocations. They also make successful predictions.

The purpose of this lecture is to share my enthusiasm with you and to draw your attention to the exploration of these new theories.

## 2. BALANCE LAWS

Just as in classical field theories, the motion of a material point  $\underline{X}$  in a body  $B$  with volume  $V$ , enclosed by its surface  $\partial V$ , is described by the mapping

$$(2.1) \quad \underline{x} = \underline{x}(\underline{X}, t) \quad (2.1)$$

where  $\underline{x}$ , at time  $t$ , is the spatial image of  $\underline{X}$ , in the deformed configuration  $B$  having volume  $V$  enclosed within its surface  $\partial V$ . We employ rectangular coordinates  $X_K$  and  $x_k$  to denote the position of  $\underline{X}$  and  $\underline{x}$  respectively, and assume that

$$(2.2) \quad J \equiv \det(\partial x_k / \partial X_K) > 0$$

throughout  $B$ , so that the inverse of (2.1)

$$(2.3) \quad \underline{X} = \underline{X}(\underline{x}, t) \quad , \quad \underline{X} \in B$$

exists and is unique.

Under some mild assumptions, local balance laws of continuum mechanics are valid for the nonlocal theory. Thus, we assume that the body is made up of single nonpolar species and it is inert. Moreover, nonlocal gravitational effects can be neglected. Under these assumptions, the nonlocal residuals may be dropped and we have the usual balance laws



$$(2.4) \quad \dot{\rho} + \rho v_{k,k} = 0,$$

$$(2.5) \quad t_{k\ell,k} + \rho(f_\ell - \dot{v}_\ell) = 0,$$

$$(2.6) \quad t_{k\ell} = t_{\ell k},$$

$$(2.7) \quad -\rho \dot{\varepsilon} + t_{k\ell} v_{\ell,k} + q_{k,k} + \rho h = 0$$

and corresponding jump conditions which we do not list here (cf. Eringen [7],[15],[17]). Here,  $\rho$ ,  $v_k$ ,  $t_{k\ell}$ ,  $f_\ell$ ,  $\varepsilon$ ,  $q_k$  and  $h$  are, respectively, the mass density, velocity vector, stress tensor, body force density, internal energy density, heat vector and the energy source density. The usual summation convention is valid on repeated indices and a superposed dot ( $\dot{\phantom{x}}$ ) denotes the material time rate and an index following a comma partial derivative, e.g.

$$\begin{aligned} \dot{v}_\ell &= \frac{\partial v_\ell}{\partial t} + v_{\ell,m} v_m, & v_{\ell,k} &= \frac{\partial v_\ell}{\partial x_k} \\ x_{k,K} &= \frac{\partial x_k}{\partial X_K} \end{aligned}$$

In contrast to classical (local) field theories, the entropy inequality is a global statement covering the entire body. It is expressed as

$$(2.8) \quad \int_V [\rho \dot{\eta} - (q_k/\theta)_{,k} - (\rho h/\theta)] dv \geq 0$$

where  $\eta$  is the entropy density and  $\theta > 0$  is the absolute temperature.

By eliminating  $h$  between (2.7) and (2.8), we have

$$(2.9) \quad \int_V \frac{1}{\theta} [-\rho(\dot{\psi} + \eta\dot{\theta}) + t_{k\ell} v_{\ell,k} + \frac{1}{\theta} q_k \theta_{,k}] dv \geq 0$$

where we also introduced the Helmholtz' free energy

$$(2.10) \quad \psi = \varepsilon - \theta\eta$$

For some purpose, it is convenient to introduce the material tensors

$$(2.11) \quad \begin{aligned} T_{KL} &= J t_{k\ell} X_{K,k} X_{L,\ell}, & Q_K &= J q_k X_{K,k}, \\ C_{KL} &= x_{k,K} x_{k,L}, & J &= \rho_0/\rho \end{aligned}$$

which enables us to write Eq. (2.9) in the form

$$(2.12) \quad \int_V \frac{1}{\theta} [-\rho_0(\dot{\psi} + \eta\dot{\theta}) + \frac{1}{2} T_{KL} \dot{C}_{KL} + \frac{1}{\theta} Q_K \theta_{,K}] dV \geq 0$$

This is the material form of the global entropy inequality which is valid for the nonlocal field theories. Clearly, the Clausius-Duhem inequality which constitute the integrands of (2.9) and (2.12) are much too restricted. For example, it is not valid for the phase transformation where certain thermodynamic quantities exhibit discontinuities and/or singularities.

### 3. CONSTITUTIVE EQUATIONS

According to the axiom of causality, [6,18] all physical processes are the result of motions (deformations) of all material points of the body in the past up to and including the present time. For thermomechanical phenomena, the independent variables are therefore

$$(3.1) \quad Y' \equiv \{ \underline{x}', \theta', \theta'_{,K} \}$$

where a prime is used to denote the values of these functions at  $(X', t - \tau')$ , e.g.

$$(3.2) \quad \begin{aligned} \underline{x}' &= \underline{x}(X', t - \tau'), & \theta' &= \theta(X', t - \tau'), \\ \underline{X}' \in B, & & 0 \leq \tau' < \infty \end{aligned}$$

Constitutive equations express the functional dependence of the set

$$(3.3) \quad Z \equiv \{ \psi, \eta, T_{KL}, Q_K \}$$

at  $(\underline{X}, t)$  on the set (3.1), e.g.,

$$(3.4) \quad \psi(\underline{X}, t) = F[\underline{x}', \theta', \theta'_{,K}]$$

For inhomogeneous materials,  $\psi$  also depends on  $\underline{X}'$  explicitly. Response functionals, such as  $F$ , must be form-invariant under

arbitrary spatial translations and rotations. This implies that  $\psi$  will depend on  $\underline{x}'$  and  $\underline{x}$  only through  $|\underline{x}' - \underline{x}|$ . Since the distance can be expressed as a functional of  $C_{KL}$ , it proves to be convenient to replace  $\underline{x}'$  in (3.4) by  $C'_{KL} \equiv C_{KL}(\underline{x}', t - \tau')$ , i.e.

$$(3.5) \quad \psi(\underline{x}, t) = F[C'_{KL}, \theta', \theta'_K, \underline{x}']$$

This functional equation constitutes a fundamental source from which constitutive equations of large classes of nonlocal memory-dependent thermo-mechanical materials (solids and fluids) can be derived (cf. [6]).

Here we consider nonlocal elastic solids. In this case,  $\theta'$  is uniform throughout  $B$  and the memory-dependence is not present. Consequently,

$$(3.6) \quad \psi(\underline{x}, t) = \Psi[C_{KL}(\underline{x}'), \underline{x}'; \theta]$$

where in  $C_{KL}(\underline{x}')$  denotes  $C_{KL}(\underline{x}', t)$ , i.e.,  $t$  is suppressed for brevity.

We assume that  $C_{KL}(\underline{x}')$  is continuously differentiable and it belongs to a Hilbert space with an inner product defined by

$$(3.7) \quad (C_1, C_2)_H = \int_V H(\underline{x}' - \underline{x}) \text{tr}(C_1' C_2') dV'$$

where the influence function  $H$  is a positive decreasing function of its argument such that the integral in (3.7) exists and

$$(3.8) \quad H(0) = 1$$

In this case, the space of functions  $\underline{C}'$  is a Hilbert space  $H$  with a finite norm defined by

$$(3.9) \quad \|\underline{C}'\| = (\underline{C}', \underline{C}')_H$$

In a Hilbert space, any continuous, linear, real-valued function  $f(F)$  has the unique Riez-Fréchet representation

$$(3.10) \quad f(F) = (F, \underline{C}')_H$$

There exists a great variety of influence functions. As an example, we mention

$$(3.11) \quad H(\underline{X}) = \exp(-\alpha |\underline{X}|), \quad \alpha > 0$$

It is now possible to calculate  $\dot{\psi}$ . Let

$$(3.12) \quad \rho_0 \psi = F$$

then

$$(3.13) \quad \rho_0 \dot{\psi} = \delta F(C'_{KL} | \dot{C}'_{KL}, \underline{X}') + \frac{\partial F}{\partial \theta} \dot{\theta}$$

where  $\delta F$  is the Fréchet derivative of  $F$  with the norm defined by (3.9).

It is linear in  $\dot{C}'_{KL}$ . Consequently, it can be expressed in the form

$$(3.14) \quad \delta F = \int_V \frac{\delta F}{\delta C'_{KL}} \dot{C}'_{KL} dV'$$

where the operator  $\delta(\ )/\delta(\ )$  represents Fréchet partial derivative.

Substituting (3.13) into (2.12), we organize it into

$$(3.15) \quad - \int_V \frac{1}{\theta} \left( \eta + \frac{\partial F}{\partial \theta} \right) \dot{\theta} \, dV + \frac{1}{2} \int_V \left[ \frac{1}{\theta} T_{KL} - 2 \int_V \frac{1}{\theta'} \left( \frac{\delta F}{\delta C'_{KL}} \right)^* \, dV' \right] \dot{C}_{KL} \, dV \\ + \int_V \frac{1}{\theta^2} Q_K \theta_{,K} \, dV + \int_V \int_V \left[ \frac{1}{\theta'} \left( \frac{\delta F}{\delta C'_{KL}} \right)^* \dot{C}_{KL} - \frac{1}{\theta} \frac{\delta F}{\delta C'_{KL}} \dot{C}'_{KL} \right] \, dV' \, dV \geq 0$$

where a superposed asterisk (\*) indicates interchange of  $\underline{x}$  and  $\underline{x}'$ , e.g.,

$$\overset{*}{A}(\underline{x}', \underline{x}) = A(\underline{x}, \underline{x}')$$

It should be observed that the kernel of the last double integral in (3.15) is skew-symmetric in  $\underline{x}$  and  $\underline{x}'$ . Hence it vanishes. Moreover, this inequality is linear in  $\dot{\theta}$ ,  $\dot{C}_{KL}$  and  $\theta_{,K}$ . For arbitrary and independent variations of these quantities throughout  $V$ , this inequality cannot be maintained unless

$$(3.16) \quad \eta = - \frac{\partial F}{\partial \theta} \, ,$$

$$(3.17) \quad T_{KL} = 2 \int_V \left( \frac{\delta F}{\delta C'_{KL}} \right)^* \, dV'$$

$$(3.18) \quad Q_K = 0$$

Note also that we set  $\theta' = \theta$  since  $\theta$  is assumed to be uniform throughout  $V$ . The spatial forms of the constitutive equations follow from (2.11) which gives for the stress tensor

$$(3.19) \quad t_{k\ell} = \frac{\rho}{\rho_0} x_{k,K} x_{\ell,L} T_{KL}$$

#### 4. ADDITIVE FUNCTIONALS

For additive functions, in the sense of Friedman and Katz [19], a representation theorem exists, according to which

$$(4.1) \quad \rho_0 \psi = F = \int_V G(C'_{KL}, C_{KL}, \underline{X}', \underline{X}) dV'$$

Since the integral of  $F$  over the volume  $V$  must be symmetric in  $\underline{X}'$  and  $\underline{X}$ , we set

$$(4.2) \quad G = G^*$$

Consequently,

$$(4.3) \quad T_{KL} = \int_V \left[ \left( \frac{\partial G}{\partial C'_{KL}} \right)^* + \frac{\partial G}{\partial C_{KL}} \right] dV'$$

and the Cauchy's stress tensor is given by (3.19).

Crystalline materials possess certain symmetry regulations. All thirty-two classes of perfect crystals can be characterized by a subgroup  $\{S_{KL}\}$  of the full group of orthogonal transformations and translations  $\{B_K\}$  of the material frame of reference, namely

$$(4.4) \quad \bar{X}_K = S_{KL} X_L + B_K$$

$$\underline{S} \underline{S}^T = \underline{S}^T \underline{S} = \underline{1}, \quad \det \underline{S} = \pm 1$$

In the case of amorphous materials,  $S_{KL}$  and  $B_K$  may be different for different species. Here we consider that  $\{S_{KL}\}$  and  $\{B_K\}$  are constants.  $\psi$  is invariant under the transformations (4.4) and therefore:

$$(4.5) \quad \bar{G} = G,$$

for all members of  $\{S_{KL}\}$  and  $\{B_K\}$ , where

$$(4.6) \quad \bar{G} = G(\underline{SC}'\underline{S}^T, \underline{SCS}^T, \underline{SX}' + \underline{B}, \underline{SX} + \underline{B})$$

For a given symmetry group, these expressions restricts the functional forms of the constitutive equations.

In the case of homogeneous materials,  $G$  will not depend on  $B$ , so that

$$(4.7) \quad G = G(\underline{C}', \underline{C}, \underline{X}' - \underline{X})$$

For isotropic materials,  $\{S\}$  is the full group of orthogonal transformations.



## 5. ISOTROPIC SOLIDS

For isotropic solids,  $\{\underline{S}\}$  is the full group of orthogonal transformations and Eq. (4.5) states that  $G$  is a function of the invariants of  $\underline{C}$ ,  $\underline{C}'$  and  $\underline{R} = \underline{X}' - \underline{X}$ , i.e.

$$(5.1) \quad G = G(I_\alpha, \overset{*}{I}_\alpha; I_\beta) \quad \begin{array}{l} \alpha=1,2,\dots,6 \\ \beta=7,8,\dots,10 \end{array}$$

and a function of  $\theta$ , where

$$(5.2) \quad \begin{array}{lll} I_1 = \text{tr } \underline{C}, & I_2 = \text{tr } \underline{C}^2, & I_3 = \text{tr } \underline{C}^3, \\ I_4 = \text{tr } \underline{C}^2 \underline{C}', & I_5 = \underline{R} \cdot \underline{C} \underline{R}, & I_6 = \underline{R} \cdot \underline{C}^2 \underline{R}, \\ I_7 = \text{tr } \underline{C} \underline{C}', & I_8 = \text{tr}(\underline{C}^2 \underline{C}'^2), & I_9 = \underline{R} \underline{C} \underline{C}' \underline{R} \\ I_{10} = \underline{R} \cdot \underline{R} \end{array}$$

From (4.2), it follows that

$$(5.3) \quad G(I_\alpha, \overset{*}{I}_\alpha; I_\beta) = G(\overset{*}{I}_\alpha, I_\alpha; I_\beta) \equiv \overset{*}{G}$$

since  $\overset{*}{I}_\beta = I_\beta$ .

Substituting (5.1) into (4.3), we obtain

$$\begin{aligned}
 (5.4) \quad T_{KL} = 2 \int_V & \left[ \frac{\partial G}{\partial I_1} \delta_{KL} + 2 \frac{\partial G}{\partial I_2} C_{KL} + 3 \frac{\partial G}{\partial I_3} C_{KM} C_{ML} \right. \\
 & + \frac{\partial G}{\partial I_4} (C_{KM} C'_{ML} + C'_{KM} C_{ML}) + \frac{\partial G}{\partial I_5} R_K R_L \\
 & + \frac{\partial G}{\partial I_6} (R_K C'_{LM} R_M + R_M C'_{MK} R_L) + \frac{\partial G}{\partial I_7} C'_{KL} \\
 & + \frac{\partial G}{\partial I_8} (C_{KM} C'_{MN} C'_{NL} + C_{LM} C'_{MN} C'_{NK}) \\
 & \left. + \frac{\partial G}{\partial I_9} (R_K C'_{LM} R_M + R_L C'_{KM} R_M) \right] dV'
 \end{aligned}$$

The spatial expression of the stress tensor follows from (3.19).

The exact constitutive equations (5.4) may be useful in dealing with finite deformation problems. In general, they are too complicated for practical applications. However, for certain simple geometries and loading and in those problems where the nonlinear region is localized (e.g., the crack tip), the solution may be tractable. Of course, there exists some important problems where the nonlinearity is the rule rather than the exception, e.g. phase transition, rubber elasticity.

## 6. LINEAR THEORY

For linear theory, it is useful to employ the linear strain measure

$$(6.1) \quad E_{KL} = \frac{1}{2} (C_{KL} - \delta_{KL}) \approx \frac{1}{2} (U_{K,L} + U_{L,K})$$

where  $U_k$  is the displacement vector in  $B$ . A second degree polynomial for  $G$  satisfying Eq. (4.2) has the form

$$(6.2) \quad G = \Sigma^1 + \Sigma_{KL}^1 E_{KL} + \overset{*}{\Sigma}_{KL}^1 E_{KL} + \frac{1}{2} \Sigma_{KLMN}^1 E_{KL} E_{MN} \\ + \frac{1}{2} \overset{*}{\Sigma}_{KLMN}^1 E_{KL} E_{MN} + \frac{1}{2} \Sigma_{KLMN}^2 E_{KL} E_{MN} + \frac{1}{2} \overset{*}{\Sigma}_{KLMN}^2 E_{KL} E_{MN}$$

where constitutive coefficients  $\Sigma^1, \dots, \overset{*}{\Sigma}_{KLMN}^2$  are functions of  $\underline{\underline{X}}' - \underline{\underline{X}}$  and  $\theta$  and they have the symmetry regulations

$$(6.3) \quad \Sigma_{KL}^1 = \Sigma_{LK}^1, \quad \Sigma_{KLMN}^1 = \Sigma_{LKMN}^1 = \Sigma_{KLNM}^1, \\ \Sigma_{KLMN}^2 = \Sigma_{LKMN}^2 = \Sigma_{KLNM}^2 = \Sigma_{MNKL}^2$$

Substituting (6.2) into (4.3), we obtain

$$(6.4) \quad T_{KL} = \Sigma_{KL}^0 + \Sigma_{KLMN}^0 E_{MN} + \int_V \Sigma'_{KLMN} E'_{MN} dv'$$

where

$$\begin{aligned}
 (6.5) \quad \Sigma_{KL}^0 &= \int_V \Sigma_{KL}^1 dV', \\
 \Sigma_{KLMN}^0 &= \int_V \Sigma_{KLMN}^2 dV', \\
 \Sigma'_{KLMN} &= \frac{1}{2} (\Sigma_{KLMN}^1 + \Sigma_{MNKL}^{*1})
 \end{aligned}$$

from which and (6.3), we deduce the symmetry regulations

$$\Sigma_{KL}^0 = \Sigma_{LK}^0, \quad \Sigma_{KLMN}^0 = \Sigma_{LKMN}^0 = \Sigma_{KLNM}^0 = \Sigma_{MNKL}^0,$$

(6.6)

$$\Sigma'_{KLMN} = \Sigma'_{LKMN} = \Sigma'_{KLNM} = \Sigma_{MNKL}^{*'}$$

Constitutive moduli  $\Sigma_{KL}^0$ ,  $\Sigma_{KLMN}^0$  are functions of  $\underline{X}$  and  $\theta$ , but  $\Sigma'_{KLMN}$  are functions of  $\underline{X}' - \underline{X}$  and  $\theta$ .

From Eq. (6.4), it is clear that the nonlocal effects are represented by the volume integral, i.e. when  $\Sigma'_{KLMN} = 0$  we obtain the classical Hookes law of elasticity.

One may be tempted to incorporate  $\Sigma_{KLMN}^0$  into the nonlocal moduli  $\Sigma'_{KLMN}$  by writing

$$(6.7) \quad \Sigma_{KLMN} = \Sigma_{KLMN}^0 \delta(\underline{X}' - \underline{X}) + \Sigma'_{KLMN}$$

where  $\delta(\underline{X}' - \underline{X})$  is the three-dimensional Dirac-delta measure. With this, Eq. (6.4) becomes

$$(6.8) \quad T_{KL} = \Sigma_{KL}^0 + \int_V \Sigma_{KLMN}(\underline{X}' - \underline{X}, \theta) E'_{MN}(\underline{X}') dV(\underline{X}')$$

In this form, the continuity requirement imposed on the stress functional is violated. As we shall see, this form is useful for mathematical treatment, but in some instances (for compact operators), it leads to unbounded inverses which may or may not be acceptable on physical grounds.

In Eq. (6.8),  $\Sigma_{KL}^0$  represents the initial stress present in the reference state, in the absence of which we set  $\Sigma_{KL}^0 = 0$ .

The material symmetry group  $\{S_{KL}\}$  place restrictions on  $\Sigma_{KLMN}$ . These are of the form

$$(6.9) \quad \Sigma_{KLMN}(\underline{SR}, \theta) = S_{KP} S_{LQ} S_{MR} S_{NT} \Sigma_{PQRT}(\underline{R}, \theta)$$

where  $\underline{R} = \underline{X}' - \underline{X}$ .

The spatial form of the stress tensor is obtained by carrying (6.8) into (3.19) and using

$$(6.10) \quad E_{KL} = e_{k\ell} x_{k,K} x_{\ell,L}, \quad R_{KL} = r_{k\ell} x_{k,K} x_{\ell,L}$$

$$x_{k,K} \approx (\delta_{MK} + E_{MK} + R_{MK}) \delta_{Mk}, \quad \rho/\rho_0 \approx 1 - e_{rr}$$

where  $R_{KL}$  and  $r_{k\ell}$  are the material and spatial rotation tensors, respectively.  $\delta_{Mk}$  is the Kronecker delta when the spatial and material coordinates are coincident. In terms material and spatial displacement vectors  $U_k$  and  $u_k$ , we have

$$(6.11) \quad R_{KL} = \frac{1}{2} (U_{K,L} - U_{L,K}),$$

$$r_{k\ell} = \frac{1}{2} (u_{k,\ell} - u_{\ell,k}), \quad e_{k\ell} = \frac{1}{2} (u_{k,\ell} + u_{\ell,k})$$

With these, Eq. (3.19) gives

$$(6.12) \quad \begin{aligned} \tau_{k\ell} = & (1 - e_{rr}) \delta_{ok\ell} + \sigma_{om\ell} (e_{km} + r_{km}) + \sigma_{okm} (e_{\ell m} + r_{\ell m}) \\ & + \int_V \sigma_{k\ell mn}(\underline{x}' - \underline{x}, \theta) e_{mn}(\underline{x}') dv(\underline{x}') \end{aligned}$$

where

$$(6.13) \quad \sigma_{ok\ell} = \Sigma_{OKL} \delta_{Kk} \delta_{L\ell}, \quad \sigma_{k\ell mn} = \Sigma_{KLMN} \delta_{Kk} \delta_{L\ell} \delta_{Mm} \delta_{Nn}$$

For homogeneous and isotropic materials, we can show that, [7], [13],

$$(6.14) \quad \begin{aligned} \sigma_{ok\ell} &= \sigma_0 \delta_{k\ell}, \\ \sigma_{k\ell mn} &= \lambda' \delta_{k\ell} \delta_{mn} + \mu' (\delta_{km} \delta_{\ell n} + \delta_{kn} \delta_{\ell m}) \\ &\quad + \lambda_1 r^{-2} (r_m r_n \delta_{k\ell} + r_k r_\ell \delta_{mn}) \\ &\quad + \lambda_2 r^{-2} (r_k r_m \delta_{\ell n} + r_k r_n \delta_{\ell m} + r_\ell r_m \delta_{kn} + r_\ell r_n \delta_{km}) \\ &\quad + \lambda_3 r^{-4} r_k r_\ell r_m r_n \end{aligned}$$

where

$$(6.15) \quad r^2 = r_k r_k \quad r_k = x'_k - x_k$$

and  $\sigma_0$  is a function of  $\underline{x}$  and  $\theta$  but  $\lambda'$ ,  $\mu'$  and  $\lambda_\alpha$  are functions of  $r = |\underline{x}' - \underline{x}|$  and  $\theta$ , i.e.

$$(6.16) \quad \begin{aligned} \sigma_0 &= \sigma_0(\underline{x}, \theta), & \lambda' &= \lambda'(|\underline{x}' - \underline{x}|, \theta), & \mu' &= \mu'(|\underline{x}' - \underline{x}|, \theta) \\ \lambda_\alpha &= \lambda_\alpha(|\underline{x}' - \underline{x}|, \theta), & & & \alpha &= 1, 2, 3 \end{aligned}$$

The appearance of  $\lambda_\alpha$  in (6.14) indicates that the nonlocal effects can cause directional dependence, even in isotropic solids. These terms are expected to be small as compared to  $\lambda'$  and  $\mu'$  because of the strong attenuation of the intermolecular forces with the distance. Henceforth, we shall drop these terms and also assume that the reference state is stress free, so that

$$(6.17) \quad t_{kl} = \int_V \sigma_{klmn}(\underline{x}' - \underline{x}, \theta) e_{mn}(\underline{x}') dv(\underline{x}')$$

valid for linear anisotropic solids, but for isotropic solids

$$(6.18) \quad \sigma_{klmn} = \lambda'(|\underline{x}' - \underline{x}|, \theta) \delta_{kl} \delta_{mn} + \mu'(|\underline{x}' - \underline{x}|, \theta) (\delta_{km} \delta_{ln} + \delta_{kn} \delta_{lm})$$

## 7. NONLOCAL ELASTIC MODULI

The nonlocal elastic moduli  $\sigma_{k\ell mn}(\underline{x}'-\underline{x}, \theta)$  are required to possess certain physically acceptable properties:

(i) From (6.17), it is clear that

$$(7.1) \quad \text{Dimension } (\sigma_{k\ell mn}) = \text{stress}/(\text{length})^3$$

This indicates that elastic properties of materials depend on some internal characteristic lengths (in general, three), a property which is lacking from the classical (local) theory. If  $\varepsilon(\theta)$  denotes this internal characteristic length for isotropic solids, then we can put

$$(7.2) \quad \lambda' = \lambda(\theta) \alpha_1(|\underline{x}'-\underline{x}|/\varepsilon), \quad \mu' = \mu(\theta) \alpha_2(|\underline{x}'-\underline{x}|/\varepsilon)$$

where  $\lambda$  and  $\mu$  are the classical Lamé constants, and  $\alpha_1$  and  $\alpha_2$  are the attenuation functions.

The internal characteristic length  $\varepsilon$  can be taken to be proportional to the lattice parameter, average granular distance, or some other internal length, depending on the inner structure of the material and the accuracy desired. We may put

$$(7.3) \quad \varepsilon = e_0(\theta)a$$

where  $a$  is the internal characteristic length and  $e_0(\theta)$  is a non-dimensional material function.



In the limit as  $\epsilon \rightarrow 0$ , nonlocal theory should convert to classical (local) theory. Hence

$$(7.4) \quad \lim_{\epsilon \rightarrow 0} (\alpha_1, \alpha_2) = \delta(\tilde{x}' - \tilde{x})$$

It is also clear that  $\alpha_1$  and  $\alpha_2$  should assume their maxima at  $\tilde{x}' = \tilde{x}$ . Similar limits are valid for the anisotropic moduli  $\sigma_{k\ell mn}(\tilde{x}' - \tilde{x}, \theta)$ .

(ii) The nonlocal moduli must be continuous and bounded. This is the case, at least for  $\epsilon \neq 0$ , because of the function space to which they belong. One may also be tempted to consider compact operators since they transform bounded sequences to sequences that have convergent subsequences. This however leads to unbounded inverse in an infinite dimensional space. In some physical situation, this could be acceptable (e.g. crack tip, where the strain may be infinite). Contrary to  $\sigma_{k\ell mn}$ , in the original Eq. (6.4)  $\Sigma'_{KLMN}$ , and the corresponding spatial moduli may define a compact operator.

(iii) The group symmetry of  $\sigma_{k\ell mn}(\tilde{x}' - \tilde{x}, \theta)$  is identical to (6.9) as is clear from (6.13). For isotropic solids, it is expected that the attenuation of intermolecular attractions are the same in all directions. Consequently, we may also take

$$(7.5) \quad \alpha_1 = \alpha_2 = \alpha(|\tilde{x}' - \tilde{x}|/\epsilon),$$

subject to

$$(7.6) \quad \alpha(0) = \max \alpha, \quad \lim_{\epsilon \rightarrow 0} \alpha = \delta(\tilde{x}' - \tilde{x})$$

(iv) All materials, at some internal length scale, must be considered discrete. This characteristic of solids can be introduced by means of a cut-off length either through the so-called quasi-continuum approach [1],[4], or equivalently using a finite support for the Fourier transform of the nonlocal moduli  $\sigma_{k\ell mn}$  and  $\alpha$ , [4],[13].

The idea is the same one that is used in lattice dynamics and information theory: Let  $f(\underline{n})$  be a scalar or tensor valued function of a vector  $\underline{n}$  which takes discrete values at lattice points through all displacements of the origin by vectors  $\underline{n} = n^k \underline{e}_k$  ( $n^k$  and  $k$  are integers  $\underline{e}_k = (e_{k1}, e_{k2}, e_{k3})$ ). Let  $\underline{e}^k$  be the reciprocal triad to  $\underline{e}_k$ , i.e.

$$(7.7) \quad \underline{e}^k \cdot \underline{e}_\ell = \delta_\ell^k$$

Define a sampling function

$$(7.8) \quad \delta_B(\underline{x}) = (2\pi)^{-3} \int_B \exp(i\underline{k} \cdot \underline{x}) \, dv(\underline{k})$$

where the domain of integration  $B$  is a parallelepiped  $B\{-\pi \leq k_j \leq \pi\}$ . Suppose that the Fourier transform  $\bar{f}(\underline{k})$  of a continuous function  $f(\underline{x})$  can be represented by a Fourier series

$$(7.9) \quad \bar{f}(\underline{k}) = v_0 \sum_{\underline{n}} f(\underline{n}) \exp(i\underline{n} \cdot \underline{k}), \quad \underline{k} \in B$$

where  $v_0$  is the volume of the cell  $B$ , and  $f(\underline{k}) = 0$  outside of  $B$ .

From the inversion theorem, it follows that

$$(7.10) \quad f(\underline{x}) = v_0 \sum_{\underline{n}} f(\underline{n}) \delta_B(\underline{x}-\underline{n})$$

Since, according to (7.8),  $\delta_B(0) = v_0$  and  $\delta_B(\underline{n}) = 0$  for all other points, the continuous function  $f(\underline{x})$  takes the discrete values  $f(\underline{n})$  at lattice points. This representation can be shown to be unique. Of course, between the lattice points  $f(\underline{x})$  can be quite arbitrary. Thus, by means of the sampling function  $\delta_B$ , we can replace a function with discrete values by a continuous function.  $\delta_B$  plays the role of the Dirac-delta distribution. The following nonlocal elastic moduli

$$(7.11) \quad \sigma_{k\ell mn}(\underline{x}'-\underline{x}, \theta) = \sigma_{k\ell mn}^0(\theta) \delta_B(\underline{x}'-\underline{x})$$

satisfies all the invariance requirements. in addition to being a continuous function.

Sampling functions for several crystals are known. For example, for a cubic crystal, it has the form

$$(7.12) \quad \delta_B(\underline{x}'-\underline{x}) = \pi^{-3} \prod_{j=1}^3 (x'_j - x_j)^{-1} \sin[\pi(x'_j - x_j)/a]$$

where  $a$  is the lattice constant. For hexagonal, body and face-centered cubic lattices, see Kotowski [20]. For the so-called Debye continuum where the Brillouin zone is considered to be spherical,  $\delta_B$  was calculated by Kunin and coworkers [21],[22].

$$(7.13) \quad \delta_{\kappa}(\underline{r}) = (\kappa/2\pi^2 r^2) \left( \frac{\sin \kappa r}{\kappa r} - \cos \kappa r \right),$$

$$r \equiv |\underline{x}'-\underline{x}|, \quad \kappa = \pi/a$$

where  $a$  is the lattice parameter. For the two-dimensional case,  $\delta_B$  has the form

$$(7.14) \quad \delta_{\kappa}(\underline{x}' - \underline{x}) = (\kappa/2\pi r) J_1(\kappa r), \quad \kappa = \pi/a$$

where  $J_1$  is the Bessel's function.

We note that  $\delta_B$  and  $\delta_{\kappa}$  given above, have no singularity for finite  $a$ , but they go into Dirac-delta distribution when  $a \rightarrow 0$ , as they should.

The Fourier transform of  $\bar{\delta}_B = 1$  in  $B$ , and vanishes outside. Consequently, we have

$$(7.15) \quad \begin{aligned} \bar{t}_{k\ell}(\underline{k}) &= \bar{\sigma}_{k\ell}(\underline{k}) && \text{when } k_j \in B \\ &= 0 && \text{when } k_j \notin B \end{aligned}$$

where

$$(7.16) \quad \bar{\sigma}_{k\ell} = \bar{\sigma}_{k\ell mn}(\underline{k}) \bar{e}_{mn}(\underline{k})$$

From this, by inversion, we have

$$(7.17) \quad \bar{e}_{k\ell}(\underline{k}) = \bar{s}_{k\ell mn}(\underline{k}) \bar{t}_{mn}(\underline{k})$$

where  $\bar{s}_{k\ell mn}$  is the Fourier transform of the compliance subject to

$$(7.18) \quad \bar{\sigma}_{k\ell mn} \bar{s}_{mnr s} = \delta_{kr} \delta_{\ell s}$$

i.e., it is the inverse matrix to  $\bar{\sigma}_{k\ell mn}$ . For isotropic materials, it is given by

$$(7.19) \quad \bar{s}_{k\ell mn} = \frac{1}{4\bar{\mu}} (\delta_{km} \delta_{\ell n} + \delta_{kn} \delta_{\ell m}) - \frac{\bar{\lambda}}{2\bar{\mu}(3\bar{\lambda}+2\bar{\mu})} \delta_{k\ell} \delta_{mn}$$

For the case (7.5), it reads

$$(7.20) \quad \bar{s}_{k\ell mn} = s_{k\ell mn}^0(\theta) \bar{\beta}(\underline{k})$$

where  $s_{k\ell mn}^0$  has the form (7.19) with  $\bar{\lambda}$  and  $\bar{\mu}$  replaced by Lamé constants  $\lambda$  and  $\mu$ , and

$$(7.21) \quad \bar{\beta}(\underline{k}) = 1/\bar{\alpha}(\underline{k})$$

(v) In calculations, the moduli  $\bar{\alpha}(\underline{k})$  or  $\bar{\beta}(\underline{k})$  in their full generality, cause major mathematical complexities. Often approximate expressions replacing them by power series in  $\underline{k}$  are used. We give here two examples involving second degree expansions in  $\underline{k}$  for isotropic solids

$$(7.22) \quad \bar{\alpha}(\underline{k}) = 1 - \varepsilon^2 k^2$$

$$(7.23) \quad \bar{\beta}(\underline{k}) = 1 + \varepsilon^2 k^2$$

where  $k^2 = \underline{k} \cdot \underline{k}$  and  $\varepsilon$  given by (7.3) is independent of  $\underline{k}$ . We note that the linear term in  $\underline{k}$  is missing because of the isotropy and center of symmetry.

In physical space, these approximations are equivalent to constitutive equations of the forms

$$(7.24) \quad t_{k\ell} = (1 + \varepsilon^2 \nabla^2) \sigma_{k\ell}$$

for (7.22) and

$$(7.25) \quad \sigma_{k\ell} = (1 - \varepsilon^2 \nabla^2) t_{k\ell}$$

for (7.23), where  $\sigma_{k\ell}$  is the Hookean (local) stress tensor

$$(7.26) \quad \sigma_{k\ell} = \lambda e_{rr} \delta_{k\ell} + 2\mu e_{k\ell}$$

Applying the operator  $(1 - \varepsilon^2 \nabla^2)$  to the exact constitutive equation

$$(7.27) \quad t_{k\ell} = \int_V \alpha(\underline{x}' - \underline{x}, \theta) \sigma_{k\ell}(\underline{x}') dv(\underline{x}')$$

we obtain (7.25) if

$$(7.28) \quad (1 - \varepsilon^2 \nabla^2) \alpha = \delta(\underline{x}' - \underline{x})$$

This indicates that in this approximation,  $\alpha$  is a Green's function for this operator. This approach was used extensively by Eringen and his coworkers (cf. [23]-[25]).

Similarly, the application of the operator  $1 + \epsilon^2 \nabla^2$  to

$$(7.29) \quad \sigma_{k\ell} = \int_V \beta(\underline{x}' - \underline{x}, \theta) \tau_{k\ell}(\underline{x}') \, dv(\underline{x}')$$

gives (7.24) if

$$(7.30) \quad (1 + \epsilon^2 \nabla^2) \beta = \delta(\underline{x}' - \underline{x})$$

Even though  $\bar{\alpha}$  and  $\bar{\beta}$  are given approximately by (7.22) and (7.23). We may employ either (7.28) or (7.30) for the determination of the attenuation function. For example, when  $\alpha$  is determined from solving (7.28), we can then use (7.21) to determine  $\beta(\underline{x})$  exactly instead of solving (7.30) which is an approximate equation satisfied by  $\beta$ . In this sense, (7.27), with  $\alpha$  given by (7.28), represents an exact nonlocality. However,  $\bar{\alpha}$  being limited to a special class of function represented by Equation (7.22), is a limited or "short" nonlocality. Nevertheless, with this compromise, we have achieved a major gain in that the integro-partial differential equations for the displacement field are now reduced to singular partial differential equations through the use of (7.24) or (7.25).

Below, we give solutions of (7.28) for solids of infinite extents. For these and other types of moduli, see [5], [17] and [25].

(i) One Dimension:

$$(7.31) \quad \alpha(|x' - x|) = (2\epsilon)^{-1} \exp(-|x' - x|/\epsilon)$$

ii) Two Dimensions

$$(7.32) \quad \alpha(|\underline{x}'-\underline{x}|) = (2\pi \epsilon^2)^{-1} K_0(|\underline{x}'-\underline{x}|/\epsilon)$$

iii) Three Dimensions

$$(7.33) \quad \alpha(|\underline{x}'-\underline{x}|) = (4\pi \epsilon^2 |\underline{x}'-\underline{x}|)^{-1} \exp(-|\underline{x}'-\underline{x}|/\epsilon)$$

Excluding (7.31), these functions possess singularity at  $\underline{x}'=\underline{x}$  and they go over the Dirac delta distribution when  $\epsilon \rightarrow 0$ . From (7.31) we have

$$(7.34) \quad \bar{\alpha} = (1 + \epsilon^2 k^2)^{-1} \exp(ikx')$$

and since  $\bar{\beta} = 1/\bar{\alpha}$ , we have formally,

$$(7.35) \quad \beta = \delta(\underline{x}'-\underline{x}) - \epsilon^2 \delta''(\underline{x}'-\underline{x})$$

which upon substitution into (7.29), gives (7.25). Thus verifying our expectation.

Singular kernels such as (7.32) and (7.33) may lead singular  $\sigma_{k\ell}$  (hence singular strain) fields. For  $t_{k\ell}$  may be a continuous function but  $\nabla^2 t_{k\ell}$  may be singular at some point. The question arises whether this is allowable in a continuum theory. Recall that in the atomic scale there exists repulsive forces between ions when they are close



enough together. These forces become infinite when  $\underline{x}' = \underline{x}$ . Even in macroscopic levels at a sharp crack tip, classical elasticity leads to infinite strains. On these physical grounds, it seems that we are justified to employ such singular kernels. While these kernels do not possess an oscillatory character observed in crystal physics, it is possible to achieve such oscillations by adding a fourth degree term to the expansions (7.22) or (7.23), e.g.

$$(7.36) \quad \bar{\alpha} = 1 - \epsilon^2 k^2 + b k^4$$

where  $b$  is an appropriate constant.

In Section 9, we shall see that these kernels for the plane harmonic waves, lead to dispersion relations, which are nearly coincident to those obtained in lattice dynamics, in the entire Brillouin zone. Also, cohesive bond stresses in perfect crystals calculated by means of the nonlocal theory are in good agreement with those known in solid state physics (Section 10 and 11).

## 8. FIELD EQUATIONS

Upon substituting (7.27) into (2.5) we obtain

$$(8.1) \quad \int_V \alpha_{,k} \sigma_{kl}(\underline{x}') dv(\underline{x}') + \rho(f_\ell - \ddot{u}_\ell) = 0,$$

where

$$(8.2) \quad \sigma_{kl} = \sigma_{klmn}^0 e_{mn} = \sigma_{klmn}^0 u_{m,n}$$

which assumes a single attenuation function for anisotropic solids. We put

$$\frac{\partial \alpha}{\partial x'_k} \sigma_{kl}(\underline{x}') = - \frac{\partial \alpha}{\partial x'_k} \sigma_{kl} = - \frac{\partial(\alpha \sigma_{kl})}{\partial x'_k} + \frac{\partial \sigma_{kl}}{\partial x'_k}$$

in (8.1) and convert the first term to a surface integral by means of the Green-Gauss theorem.

$$(8.3) \quad \int_V \alpha(\underline{x}' - \underline{x}) \sigma_{kl,k}(\underline{x}') dv(\underline{x}') - \int_{\partial V} \alpha \sigma_{kl} da'_k + \rho(f_\ell - \ddot{u}_\ell) = 0$$

Using (8.2) this gives the field equation of the nonlocal elasticity for the displacement field

$$(8.4) \quad \int_V \alpha(\underline{x}' - \underline{x}) \sigma_{klmn}^0 u_{m,nk}(\underline{x}') dv(\underline{x}') - \int_{\partial V} \alpha(\underline{x}' - \underline{x}) \sigma_{klmn}^0 u_{m,n}(\underline{x}') da'_k(\underline{x}') + \rho(f_\ell - \ddot{u}_\ell) = 0$$

Here, the surface integral represents the contributions of the surface stresses (e.g. surface tension). Consequently, *nonlocal theory accounts for the surface physics as well.*

For the isotropic solids we replace  $\alpha \sigma_{klmn}^0 = \sigma_{klmn}$  by (6.17)

leading to

$$(8.6) \quad \int_V [(\lambda' + 2\mu') \nabla \nabla \cdot \underline{u}' - \mu' \nabla \times \nabla \times \underline{u}'] dv' + \rho(\underline{f} - \ddot{\underline{u}}) = \underline{0}$$

without the surface terms. If we assume (7.5), this gives

$$(8.7) \quad \int \alpha(|\underline{x}' - \underline{x}|) [(\lambda + 2\mu)\nabla\nabla\cdot\underline{u}' - \mu\nabla\times\nabla\times\underline{u}'] dv' + \rho(\underline{f} - \ddot{\underline{u}}) = \underline{0}$$

where  $\lambda$  and  $\mu$  are the classical Lamé constraints.

For  $\alpha$  we may choose various proposals made in section 7.

If we employ the approximation leading to (7.25) we will have

$$(8.8) \quad \sigma_{k\ell,k} + (1 - \varepsilon^2\nabla^2)(\rho f_\ell - \rho\ddot{u}_\ell) = 0$$

or in terms of the displacement field

$$(8.9) \quad (\lambda + 2\mu)\nabla\nabla\cdot\underline{u} - \mu\nabla\times\nabla\times\underline{u} + (1 - \varepsilon^2\nabla^2)(\rho\underline{f} - \rho\ddot{\underline{u}}) = \underline{0}$$

Here we see the advantage gained with the particular choice of  $\alpha$  satisfying (7.28).

The field equations obtained above must be solved to determine the displacement field  $\underline{u}(\underline{x}, t)$  under appropriate boundary and initial conditions. Boundary and initial conditions involving the displacement and velocity fields are identical to those of the classical theory.

Boundary condition on tractions is based on the stress field  $t_{k\ell}$ , not  $\sigma_{k\ell}$ , i.e.

$$(8.10) \quad t_{k\ell} n_k = t_{(n)\ell}$$

where  $t_{(n)\ell}$  are the prescribed boundary fractions.

## 9. PROPAGATION WAVES

### 1. Infinite Media

Using classical decomposition

$$(9.1) \quad \underline{u} = \nabla\phi + \nabla \times \underline{\psi} \quad \nabla \cdot \underline{\psi} = 0$$

Eq. (8.9) with  $\underline{f} = \underline{0}$  is satisfied if

$$(9.2) \quad c_1^2 \nabla^2 \phi - (1 - \epsilon^2 \nabla^2) \ddot{\phi} = 0,$$

$$(9.3) \quad c_2^2 \nabla^2 \underline{\psi} - (1 - \epsilon^2 \nabla^2) \ddot{\underline{\psi}} = \underline{0},$$

where

$$(9.4) \quad c_1 = [(\lambda + 2\mu)/\rho]^{1/2}, \quad c_2 = (\mu/\rho)^{1/2}$$

are the classical phase velocities of irrotational and equivoluminal waves. For plane harmonic waves, Eq. (9.2) leads to the dispersion relations

$$(9.5) \quad \omega/c_1 k = (1 + \epsilon^2 k^2)^{-1/2}$$

For  $\epsilon = 0.39 a$ , where  $a$  is the lattice parameter, the plot of  $\omega a/c$  versus  $ka$  is shown in Fig. 1, where the dispersion curve for the Born-Kármán model of lattice dynamics is also plotted for which

$$(9.6) \quad \omega a/c_1 = 2 \sin(ka/2)$$

The maximum deviation of this curve from the nonlocal result is less than 6% in the entire Brillouin zone. It should be remarked that Eq. (9.6) obeys the two natural conditions

$$(9.7) \quad \left. \frac{d\omega}{dk} \right|_{k=0} = c_1, \quad \left. \frac{d\omega}{dk} \right|_{k=\pi/a} = 0$$

but the nonlocal result (9.5) obeys only the first one of these. Accordingly, the group velocity does not vanish at the end of the Brillouin zone. However, this situation can be remedied easily by taking

$$(9.8) \quad \bar{\alpha}(k) = 1 - \epsilon^2 k^2 + b k^4$$

instead of (7.22) where  $b$  is a constant (cf. Kumins [8, II], p. 38).

Similarly, the dispersion relations of the equivoluminal waves are obtained by means of (9.3).

### (ii) Surface Waves

In the plane  $x_3 = 0$ ,  $\underline{\psi} = \underline{\psi}_3$  has a single component  $\psi(x_1, x_2, t)$  so that

$$(9.9) \quad u_1 = \frac{\partial \phi}{\partial x_1} + \frac{\partial \psi}{\partial x_2}, \quad u_2 = \frac{\partial \phi}{\partial x_2} - \frac{\partial \psi}{\partial x_1}$$

The general solution of (9.2) and (9.3) relevant to surface waves are of the form

$$(9.10) \quad \begin{aligned} \phi &= A \exp[-k\nu_1 x_2 + ik(x_1 - ct)], \\ \psi &= B \exp[-k\nu_2 x_2 + ik(x_2 - ct)] \end{aligned}$$

provided  $v_\alpha$  is given by

$$(9.11) \quad v_\alpha^2 = 1 - (c/c_\alpha)^2 [1 - \varepsilon^2 k^2 (c/c_\alpha)^2]^{-1}$$

Using (9.9) and (7.27), the stress field can be calculated. If we set  $t_{22} = t_{21} = 0$  on the surface  $x_2 = 0$ , we obtain the dispersion relations [25]:

$$(9.12) \quad [(c_1/c_2)^2 (v_1^2 - 1) + 2](1 + v_2^2) - 4 v_1 v_2 = 0$$

This can be arranged into a quartic equation

$$(9.13) \quad \gamma(a_1 \gamma^3 + a_2 \gamma^2 + a_3 \gamma + a_4) = 0$$

where

$$(9.4) \quad \begin{aligned} \gamma &= (c/c_2)^2, \\ a_1 &= \frac{1}{16} + \frac{1}{4} (m+1) (\varepsilon k)^2 + \frac{1}{4} (1+4m - 3m^2) (\varepsilon k)^4 + m(1-m) (\varepsilon k)^6, \\ a_2 &= -\frac{1}{2} + \frac{1}{2} (2m^2 - m - 3) (\varepsilon k)^2 - (1+m - 2m^2) (\varepsilon k)^4, \\ a_3 &= \frac{3}{2} - m + (2 - m - m^2) (\varepsilon k)^2 \\ a_4 &= 1 - m, \quad m = \frac{1-2\nu}{2(1-\nu)} \end{aligned}$$

A root of this equation for  $\varepsilon = 0.39 a$  and  $\nu = 0.3$  is plotted against  $ka$  in Fig. 2 where the result of lattice dynamic calculations of Wallis and Gaze [26] for  $KCl$  are also shown. If we note that no free constant is available for matching, the agreement is beyond our expectations.

The nonlocal theory also gives new types of waves which are not present in local theory. However, these waves disappear in the long wave length regions (cf. Kaliski and Rymarz [27]).

It is important to note that the nonlocal moduli  $\alpha(|\underline{x}'-\underline{x}|)$  is appropriate only to homogeneous and isotropic solids. Half-space ceases to be homogeneous in the vicinity of the surface  $x_2 = 0$ , where in a boundary layer of a few atomic distances, the material is inhomogeneous and therefore a perturbation is necessary in  $\alpha(|\underline{x}'-\underline{x}|)$ . The present results are however valid so long as the wave length is much larger than this boundary layer thickness.

## 10. SCREW DISLOCATION

Consider a screw dislocation located at  $x_3 = 0$  of rectangular coordinates  $x_k$  (Fig. 3). The displacement field has only single component  $u_3 = w(x_1, x_2)$  which satisfies the equation

$$(10.1) \quad \nabla^2 w = 0$$

whose solution relevant to our problem may be written in plane polar coordinates  $(r, \theta)$  as

$$(10.2) \quad w = \frac{b}{2\pi} \theta$$

where  $b$  is the Burger's vector. The non-zero components of  $\sigma_{k\ell}$  are given by

$$(10.3) \quad \sigma_{31} = \mu \frac{\partial w}{\partial x_1} = -\frac{\mu b}{2\pi r} \sin \theta,$$

$$\sigma_{32} = \mu \frac{\partial w}{\partial x_2} = \frac{\mu b}{2\pi r} \cos \theta$$

We now carry these into

$$(10.4) \quad (1 - \epsilon^2 \nabla^2) t_{k\ell} = \sigma_{k\ell}$$

and determine  $t_{k\ell}$  by imposing the conditions that as  $r \rightarrow \infty$   $t_{k\ell} = 0$  and at  $r=0$  (crack tip surface)  $t_{zr} = 0$ . This leads to [25] (see also [28]).



$$(10.5) \quad t_{z\theta} = \frac{\mu_0 b}{2\pi r} \left[ 1 - \frac{r}{\epsilon} K_1(r/\epsilon) \right], \quad t_{zr} = 0$$

where  $K_1$  is the Bessel's function. The plot of

$$(10.6) \quad T_{z\theta} = 2\pi \epsilon t_{z\theta} / \mu_0 b = \rho^{-1} [1 - \rho K_1(\rho)], \quad \rho = r/\epsilon$$

versus  $\rho$  is shown in Fig. 4, where is also plotted classical elasticity solution. We see that the stress at the center  $\rho = 0$  is singular for the classical solution, but zero for the nonlocal solution. The maximum stress occurs at  $\rho_c = 1.1$  and is given by

$$(10.7) \quad t_{z\theta \max} = 0.3995 \mu_0 b / 2\pi e_0 a$$

If we equate this to the yield stress (theoretical)  $t_y$  and write  $h = e_0 a / 0.3995$ , this agrees with the estimate of Frenkel, based on an atomic model. For  $e_0 = 0.39$ ,  $b/a = 1/\sqrt{2}$ , we obtain  $t_y/\mu = 0.12$ , which compares with the known value 0.11 for Al(fcc), W,  $\alpha$ -Fe(bcc) and 0.12 for NaCl, MgO (cf. [29], p. 160).

The strain energy per unit length  $L$  in  $x_3$ -direction is given by

$$\rho_0 \psi / L = \Sigma / L = \frac{1}{2} \int_0^R r \, dr \int_0^{2\pi} t_{z\theta} e_{z\theta} \, d\theta$$

substituting from (10.5) and  $e_{z\theta} = b/2\pi r$ , we obtain

$$(10.8) \quad \Sigma / L = (\mu b^2 / 8\pi) [\ln(R/2\epsilon) + K_0(R/\epsilon)]$$

where  $R$  is the outer radius of the solid. Again we see that for finite  $R$  the strain energy is finite. Eq. (10.8) shows how the energy grows with size.

The same problem can be treated by means of the nonlocal theory of continuous dislocations [30]. For the screw dislocations for a given Burger's vector  $b$ , we have

$$(10.9) \quad \frac{\partial e_{32}}{\partial x_1} - \frac{\partial e_{31}}{\partial x_2} = \frac{b}{2}$$

The equilibrium equations reduce to

$$(10.10) \quad \frac{\partial t_{31}}{\partial x_1} + \frac{\partial t_{32}}{\partial x_2} = 0$$

For the stress tensor  $t_{31}$  and  $t_{32}$ , we have the constitutive equations

$$(10.11) \quad \{t_{31}, t_{32}\} = \int_V \mu(|\tilde{x}' - \tilde{x}|) \{e'_{31}, e'_{32}\} da'$$

where the anti-plane strains are given by

$$(10.12) \quad e_{31} = \frac{\partial w}{\partial x_1}, \quad e_{32} = \frac{\partial w}{\partial x_2}$$

We introduce the stress potential  $\phi$  by

$$(10.13) \quad t_{31} = -\frac{\partial \phi}{\partial x_2}, \quad t_{32} = \frac{\partial \phi}{\partial x_1}$$

by means of which Eq. (10.10) is satisfied. The Fourier transforms of (10.9),

(10.11) to (10.13) may be combined to give

$$(10.14) \quad \bar{\phi} = \bar{\mu} \bar{b}/k^2$$

where  $k = (k_1 k_1)^{1/2}$  is the magnitude of the wave vector.

Following Kunin [8,II], if we employ the Debye Model, then the inverse of (10.14) is found to be

$$(10.15) \quad \phi = \int_A G(|\underline{x}' - \underline{x}|) b(\underline{x}') da(\underline{x}')$$

where the integration is over the area in  $(x_1, x_2)$ -plane and

$$(10.16) \quad G(r) = \frac{\mu_0}{2\pi} \left[ \int_0^\rho \frac{J_1(\tau) - 1}{\tau} d\tau - \ln(\kappa R) \right],$$

$$\rho = \kappa r, \quad \kappa = \pi/a$$

For a single screw at the origin  $r=0$ , this gives

$$(10.17) \quad t_{31} = \frac{\mu_0 b \kappa^2 x_2}{2\pi} \frac{J_0(\rho) - 1}{\rho^2}, \quad t_{32} = - \frac{\mu_0 b \kappa^2 x_1}{2\pi} \frac{J_0(\rho) - 1}{\rho^2}$$

Alternatively,

$$(10.18) \quad \tau_\theta = 2\pi t_{z\theta} / \mu_0 \kappa b = [1 - J_0(\rho)] / \rho, \quad t_{zr} = 0$$

$t_{z\theta}$  vanishes at the origin  $r=0$ . It has slightly oscillatory behavior for  $r>0$  (Fig. 5) and it acquires its first maximum at  $\rho \approx 2.76$  with an amplitude

$$(10.19) \quad \tau_{z\theta \max} \approx 0.423 \mu_0 b \kappa / 2\pi$$

This value is nearly identical to (10.7) where an entirely different (singular) kernel was used. Note however that the location of the maximum differ considerably.

## 11. CRACK TIP PROBLEM

An infinite plate with a line crack of length  $2c$  subjected to loads at infinity is known as the Griffith crack. It is well-known that the classical elasticity solution of this problem gives stress singularity at the crack tip. Because of this, no fracture criterion based on maximum stress hypothesis could be employed. Various alternative criteria (Griffith energy criterion, J-integral, etc.) had to be established to circumvent this difficulty. With the development of nonlocal theory, this problem has been resolved by Eringen and his coworkers [31 - 34]. Here I discuss only the so-called Mode III problem, i.e. line crack subject to anti-plane shear load (Fig. 6).

The classical elasticity solution for a line crack in a plate under anti-plane loading at infinity is well known [35]

$$(11.1) \quad \sigma = \sigma_{23} - i \sigma_{13} = \sigma_0 \bar{z}(\bar{z}^2 - c^2)^{-1/2}$$

where  $\sigma_0$  is the applied shear,  $2c$  is the crack length and  $z = x_1 + i x_2$ ,  $\bar{z} = x_1 - i x_2$ .

Employing (11.1) in (7.25), we determine the nonlocal stress field

$$(11.2) \quad t_{23} - i t_{13} = (\pi\epsilon/2r_1)^{1/2} e^{-r_1/\epsilon} (C_1 e^{i\theta_1/2} + C_2 e^{-i\theta_1/2}) + \sigma$$

where  $(r_1, \theta_1)$  are the polar coordinates with the origin at the right-hand crack tip (Fig. 6). The boundary condition at the crack tip is calculated by considering the tip as a small circular cylinder of radius  $r_1$  so that

in the limit  $t_{rz}$  vanishes as  $r_1 \rightarrow 0$ , i.e.

$$(11.3) \quad \lim_{r_1 \rightarrow 0} t_{rz} = 0$$

This gives  $C_2 = 0$  and  $C_1 = - (c/\pi\epsilon)^{1/2} \sigma_0$  and we have [ 34 ]

$$(11.4) \quad t_{z\theta} - i t_{zr} = (t_{32} - i t_{31}) e^{-i\theta_1} \\ = \sigma_0 (c/2r_1)^{1/2} \{ (2r_1^2/cr_2)^{1/2} \exp[i(-\theta + \frac{\theta_2}{2})] - \exp(-r_1/\epsilon) \} \exp(-i\theta_1/2)$$

$(r_2, \theta_2)$  are the plane polar coordinates attached to the left crack tip and  $(r, \theta)$  have the origin  $x_1 = x_2 = 0$ .

Along the  $x_1$ -axis ( $\theta = \theta_1 = \theta_2 = 0$ ),  $t_{z\theta}$  acquires its maximum near to the crack tip. From (11.4), we have

$$(11.5) \quad T_\theta(\rho) = \gamma^{1/2} t_{z\theta}/\sigma_0 = (\pi\epsilon)^{1/2} t_{z\theta}/K_{III} \\ = (2\rho)^{-1/2} [(1 + \gamma\rho)(1 + \frac{\gamma\rho}{2})^{-1/2} - e^{-\rho}]$$

where

$$(11.6) \quad \rho = r_1/\epsilon, \quad \gamma = \epsilon/c, \quad K_{III} = (\pi\epsilon)^{1/2} \sigma_0$$

It is clear that  $t_{z\theta}$  vanishes at the crack tip  $\rho = 0$  and acquires a maximum at  $\rho = \rho_c = 1.2565$  since  $\gamma \ll 1$  ( $\gamma \leq 10^{-4}$ ).

$$(11.7) \quad t_{z\theta \max} = \sigma_0 (\epsilon/c)^{-1/2} [(2\rho_c)^{1/2} + (2\rho_c)^{-1/2}]^{-1}$$

$T_{\theta}(\rho)$  given by (11.5) is plotted against  $\rho$  in Fig. 7. From this it is clear that

- (a) The stress field vanishes at the crack tip instead of being singular as predicted by classical elasticity.
- (b) Fracture begins when  $t_{z\theta\max} = t_y$ , where  $t_y$  is the cohesive yield stress.

From (11.7), we have

$$(11.8) \quad K_c/t_y = 3.9278 \epsilon^{1/2}$$

where  $K_c = (\pi c)^{1/2} \sigma_{oc}$  is the critical fracture toughness. For  $e_0 = 0.39$ ,  $K_c/t_y$  is shown in Table 1 along with its values based on the classical fracture criterion, namely  $K_c = (4\mu \gamma_s)^{1/2}$  where  $\gamma_s$  is the surface energy. This table also displays some experimental results. The present results are again in good agreement with experimental observations of Ohr and Chang [36], even though further considerations are necessary for the inhomogeneity of the material at the core region.

<u>Material</u>	<u>Classical</u>	<u>Present</u>	<u>Experiment</u>
Al (fcc)	1.11	0.49	0.3
Cu (fcc)	3.86	0.47	0.66
Fe (bcc)	1.04	0.42	0.23

- (c) The maximum stress acts at  $\rho = \rho_c$  not at the tip of the crack  $\rho = 0$ . Although  $\rho_c$  is very small, this implies that fracture initiates ahead of the crack joining the tip. If the inhomogeneity and the presence of dislocations near the crack tip is taken into account, we expect  $\rho_c$  to become larger than atomic dimensions.

Interactions of dislocations with crack was treated by Eringen [34]. For the solution of the crack tip problems for modes I and II, see [32], [33] and for crack curving, see [24]. Point defects and elastic interactions were explored in the works of Gairola [37] and Kumin [8].

#### ACKNOWLEDGEMENT

This work was supported by the Office of Naval Research. The author is indebted to Dr. N. Basdekas for his encouragement. The skillful typing of this manuscript was done by Betty Kaminski.

## REFERENCES

1. Rogula, D., Bull. Acad. Polon. Sci., Ser. Sci. Techn. 13, 7 (1975)
2. Krumhansl, J.A. in: Lattice Dynamics. Edited by R.F. Wallis, Pergamon Press, London, Oxford, p. 627 (1965)
3. Kroner, E. and B.K. Datta, Z. Phys. 196, 203 (1966)
4. Kunin, I.A. Prikl., Mat., Mech. 30, 642, (1966).
5. Eringen, A.C. Int. J. Engng. Sci. 10, 425 (1972)
6. Eringen, A.C. Int. J. Engng. Sci., 4, 179, (1966), see also Developments in Mechanics, V. 3, Part 1, edited by T.C. Huang & M.W. Johnson Jr., 23, 1965.
7. Eringen, A.C. & D.G.B. Edelen in Continuum Physics, v. 4, Acad. Press, Ch. 2 & 3. Edited by A.C. Eringen, 1976.
8. Kunin, I.A. Elastic Media with Microstructures I & II, Springer Verlag 1982/1983.
9. Nonlocal Theory of Material Media. Edited by D. Rogula, Springer Verlag, 1982.
10. Eringen, A.C., Int. J. Engng. Sci. 10, 561 (1972)
11. Speziale C.S. and A.C. Eringen, Comp. & Math with Appls., 7, 27, (1981)
12. Eringen, A.C., J. Math. Phys. 14, 733 (1973)
13. Eringen, A.C., J. Math. Phys. 25, 717 (1984)
14. Eringen, A.C. and D.G.B. Edelen, Int. J. Engng. Sci. 10, 233 (1972)
15. Eringen, A.C. in Topics in Mathematical Physics, edited by Halis Odabasi and O. Akyuz, Int. Symp., Istanbul Turkey, 1975 (Colorado Univ. Press), p.1
16. Eringen, A.C. in Nonlinear Equations in Physics and Mathematics, Edited by A.C. Barut, Reidel Publishing Co., 271, 1977.
17. Eringen, A.C. Crystal Lattice Defects, 7, 109, 1977.
18. Eringen, A.C. Mechanics of Continua, John Wiley, 1967, R.E. Krieger 1980, Ch. 5.



19. Friedman, M. and M. Katz, Arch. Rat. Mech. Anal. 21, 49, 1966.
20. Kotowski, R., Z. Phys. B 33, 321 (1979).
21. Kosilova, V.G., I.A. Kunin and E.G. Sosnina, Fiz. Tverd. Tela, 10, 367, (1968).
22. Vdovin, V.E. and I.A. Kunin, Fiz. Tverd. Tela, 10, 375, 1968.
23. Ari, N. and A.C. Eringen, Crystal Lattice Defects Amorph. Mat. 10 33 1983.
24. Eringen, A.C. in Defects, Fracture and Fatigue, Edited by G.C. Sih and J. W. Provan Martinus Nijhoff 233, 1982.
25. Eringen, A.C., J. Appl. Phys. 59, 4703, (1983)
26. Wallis, R.F. and D.C. Gazis, Lattice Dynamics, edited by R.F. Wallis Pergamon, New York, 537, 1965.
27. Kaliski, S. and C. Rymarz, Bull. WATJ Dubroskiego 20, 17 and 25 (1975).
28. A.C. Eringen, J. Phys. D. 10, 671 (1977).
29. Lawn, B.R. and T.R. Wilshaw, Fracture of Brittle Solids, Cambridge U. Press, London (1975).
30. Eringen, A.C., To appear in J. Appl. Phys.
31. Eringen, A.C. and B.S. Kim, Mech. Reg. Comm. 1, 233, 1974.
32. Eringen, A.C., C.G. Speziale and B.S. Kim. J. Mech. Phys. Solids, 25, 339, 1977.
33. Eringen, A.C., Int. J. of Fracture, 14, 367, (1978).
34. Eringen, A.C., J. Appl. Phys. 54, 6811 (1983)
35. Sneddon, I.N. and G. Lowengrub, Crack Problems in the Classical Elasticity Theory, John Wiley, p. 37. 1969.
36. Ohr, S.M., J.A. Horton and S.-J. Chang, "Direct Observations of Crack Tip Dislocation Behavior During Tensile and Cyclic Deformation," Tech. Report, Oak Ridge National Laboratory.
37. Gairola, B.K.D. in Ref. 9, p. 52.

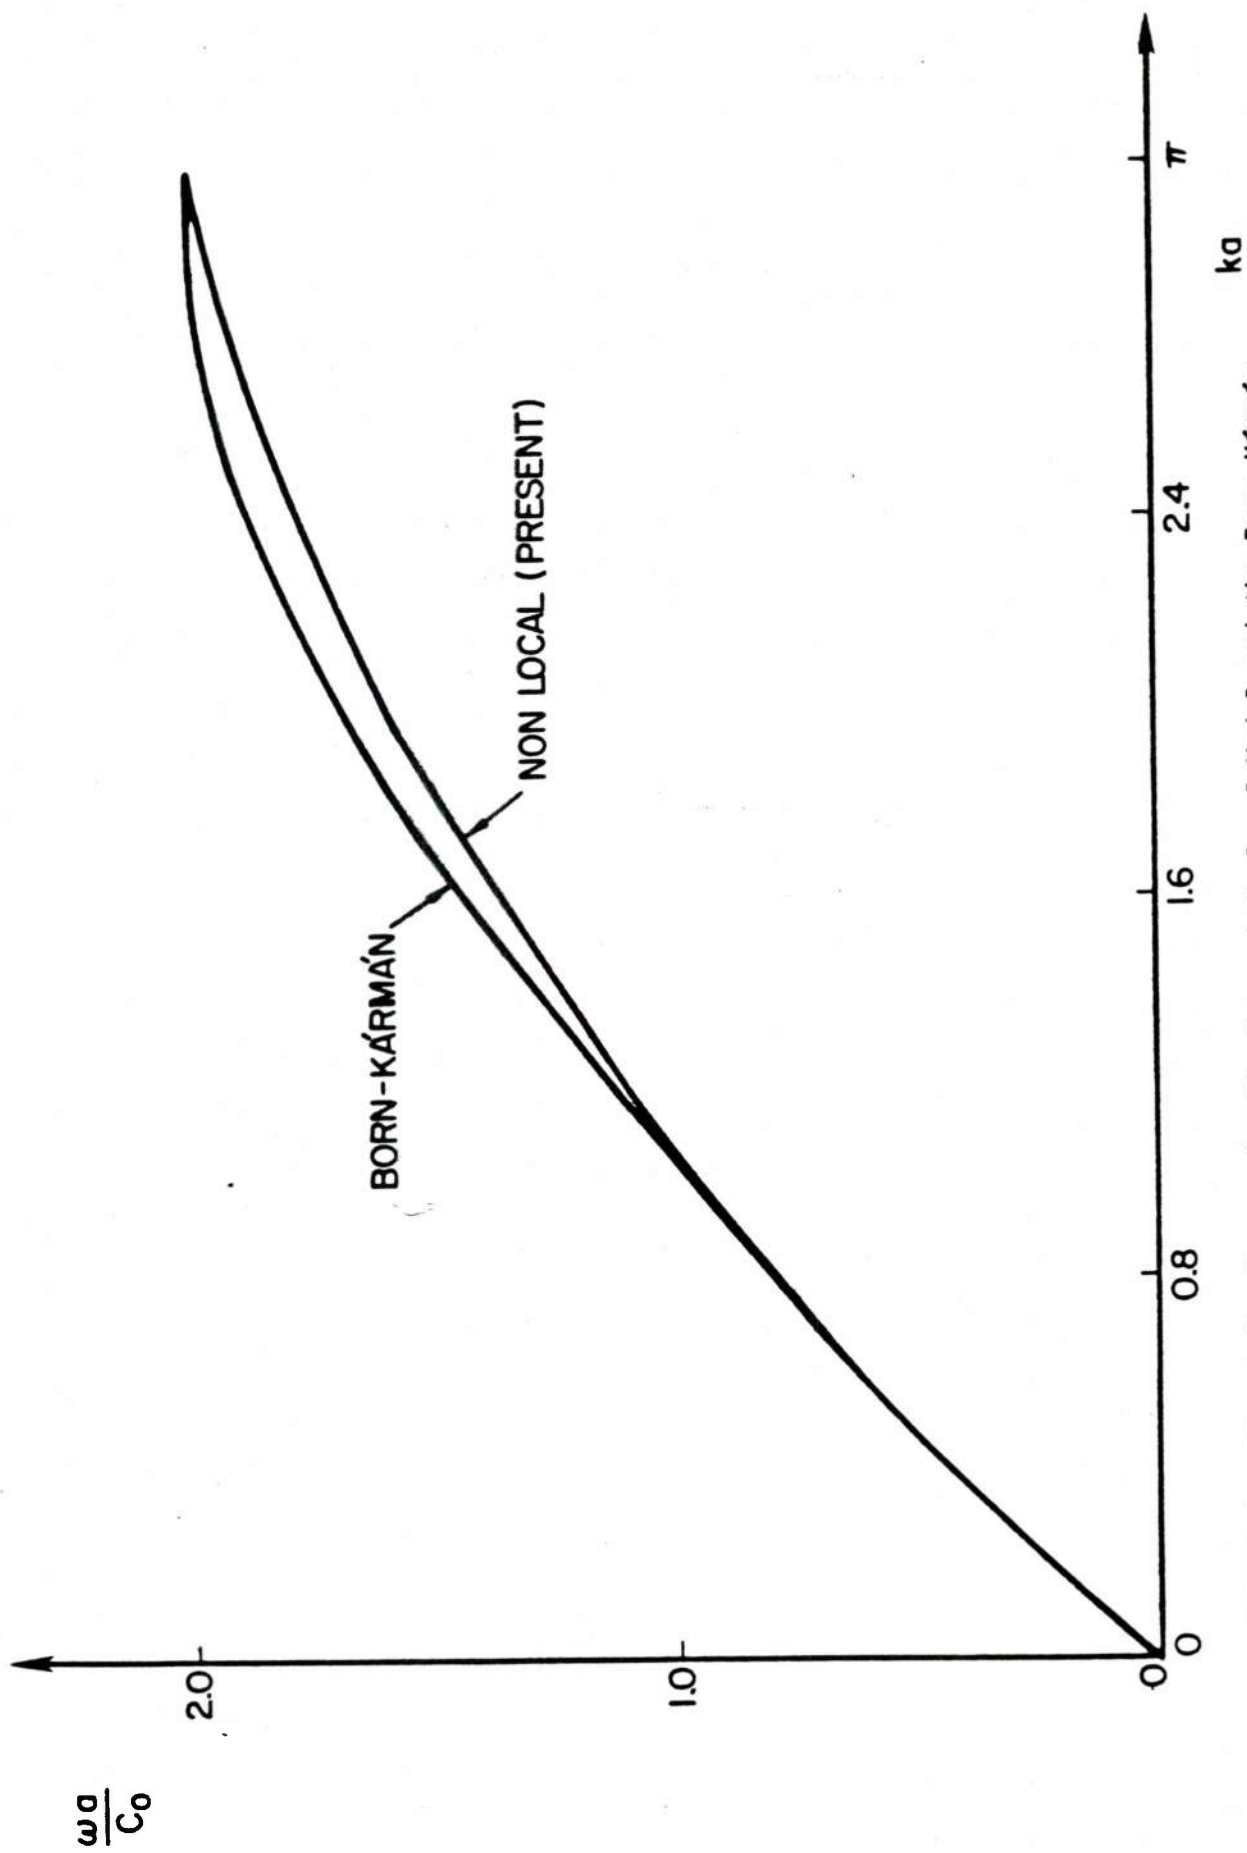


FIGURE 1: Dispersion Curves for the Present Nonlocal Model and the Born-Kármán Model of Lattice Dynamics

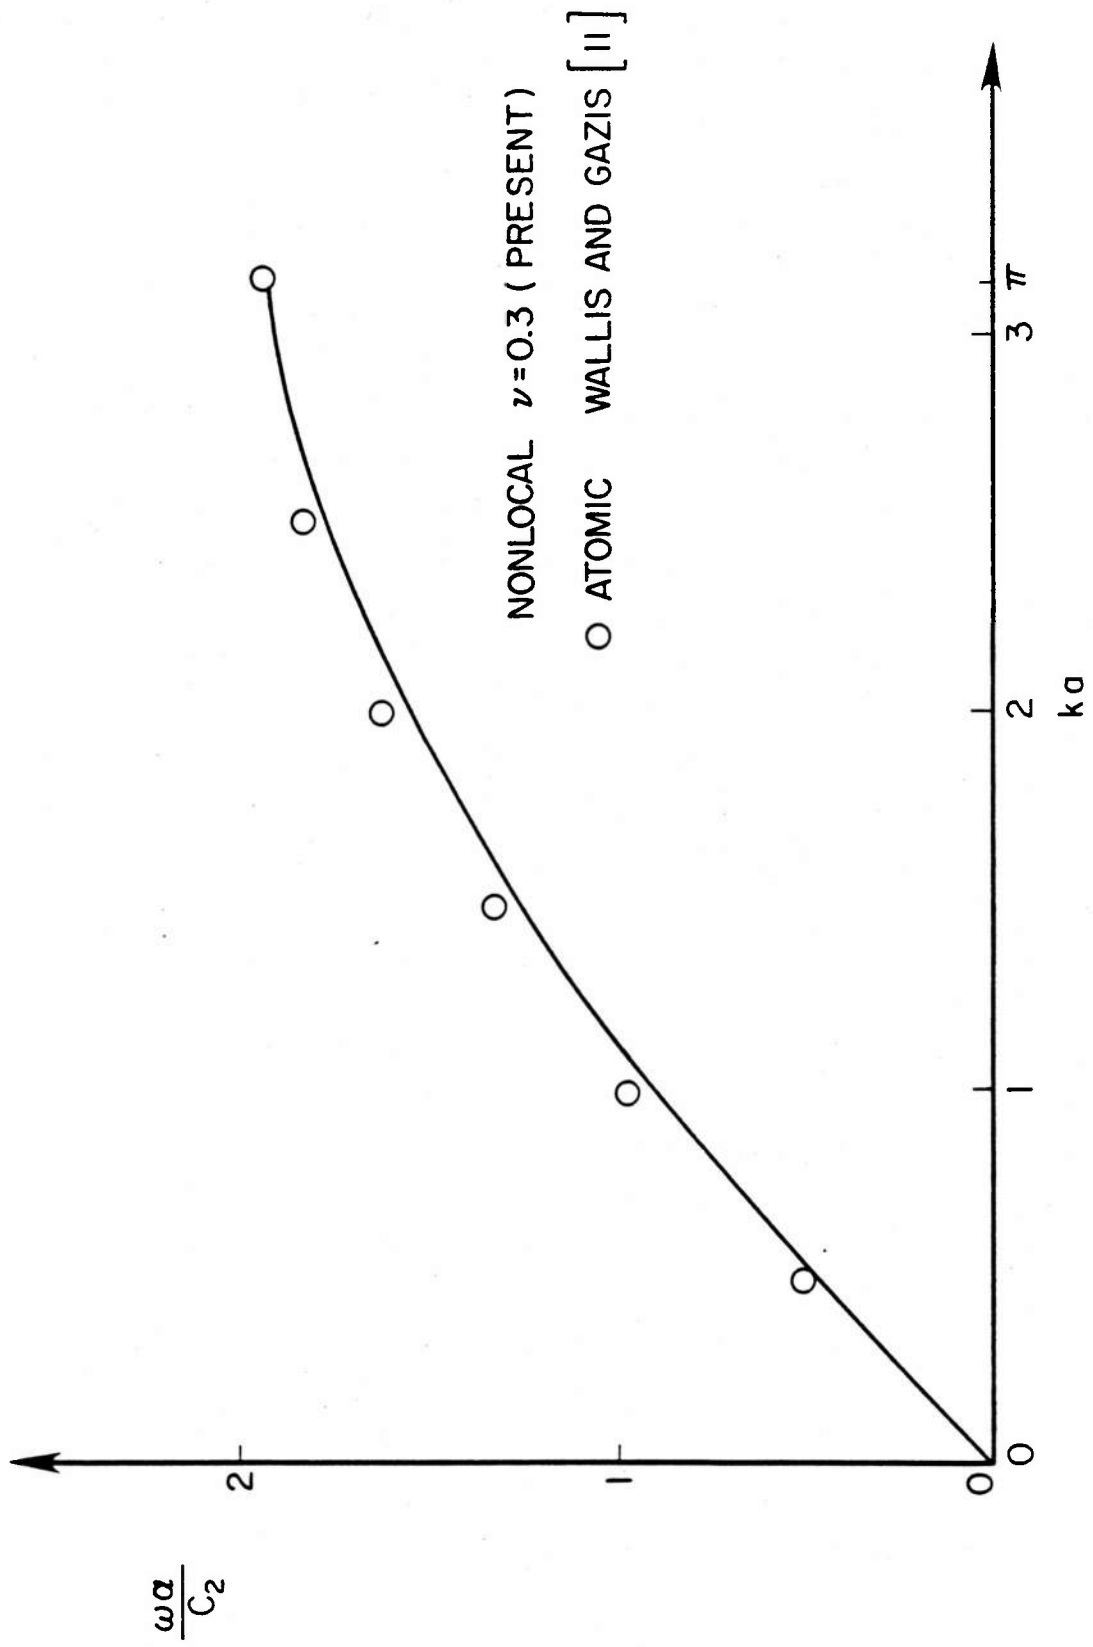


Figure 2: Dispersion Relations for Rayleigh Surface Waves


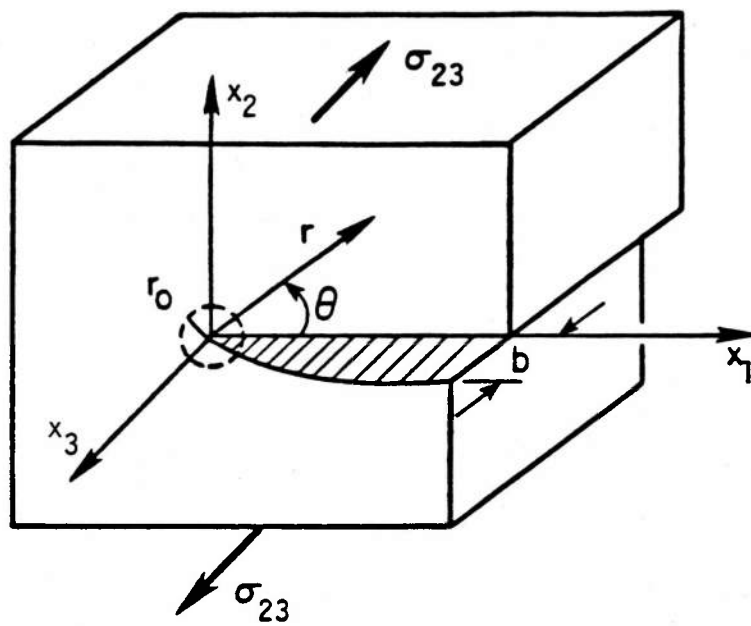


Figure 3: SCREW DISLOCATION

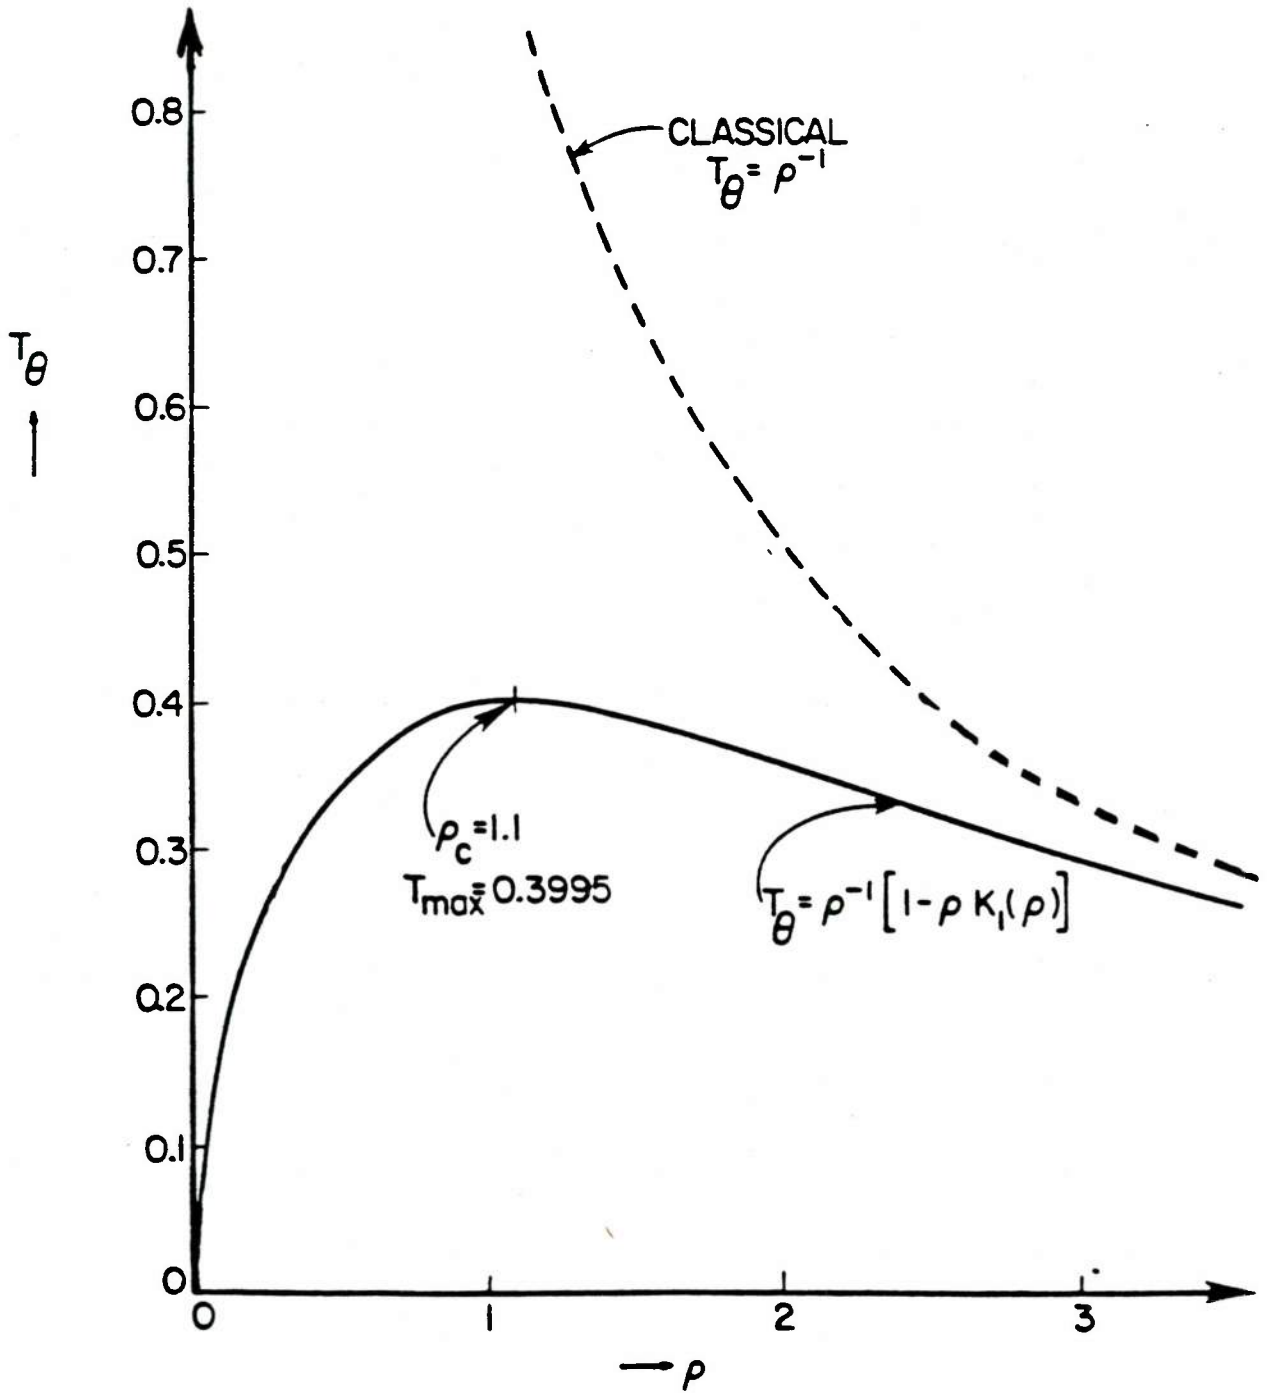

NON-DIMENSIONAL HOOP STRESS (Screw Dislocation)

FIGURE 4


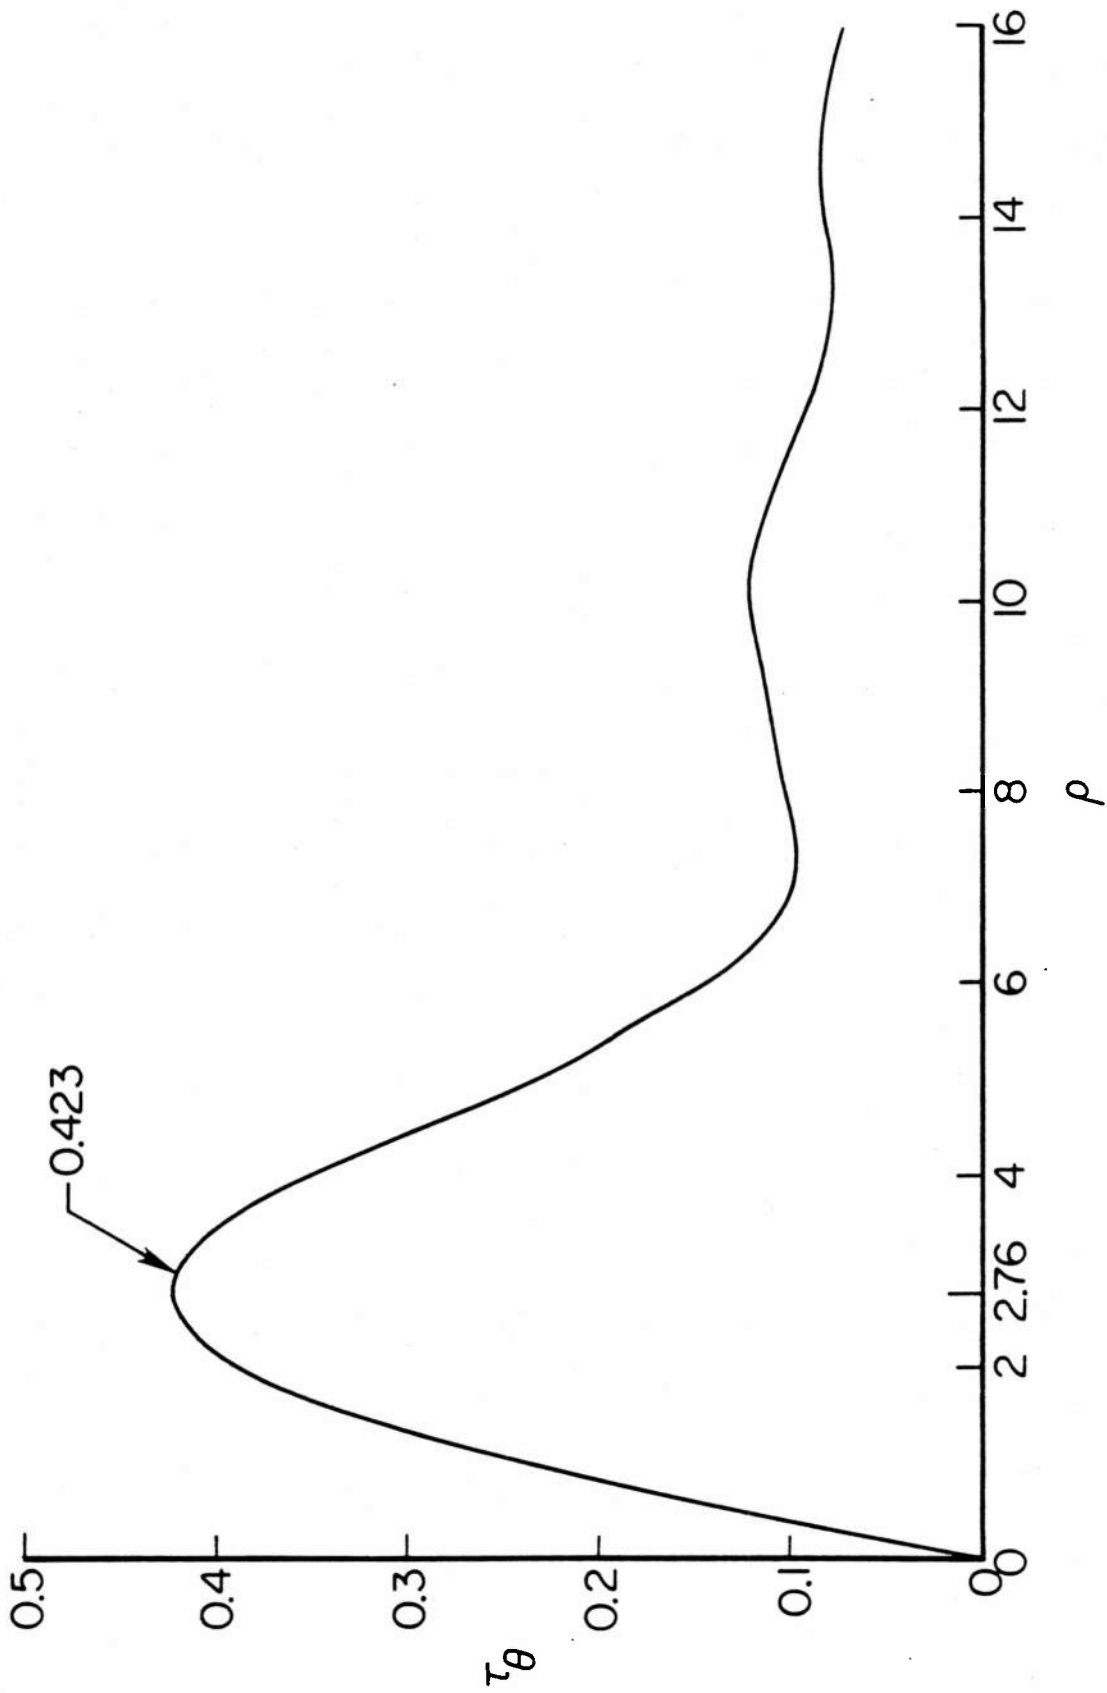


FIGURE 5. SHEAR STRESS IN SCREW DISLOCATION (Eq. 10.18)

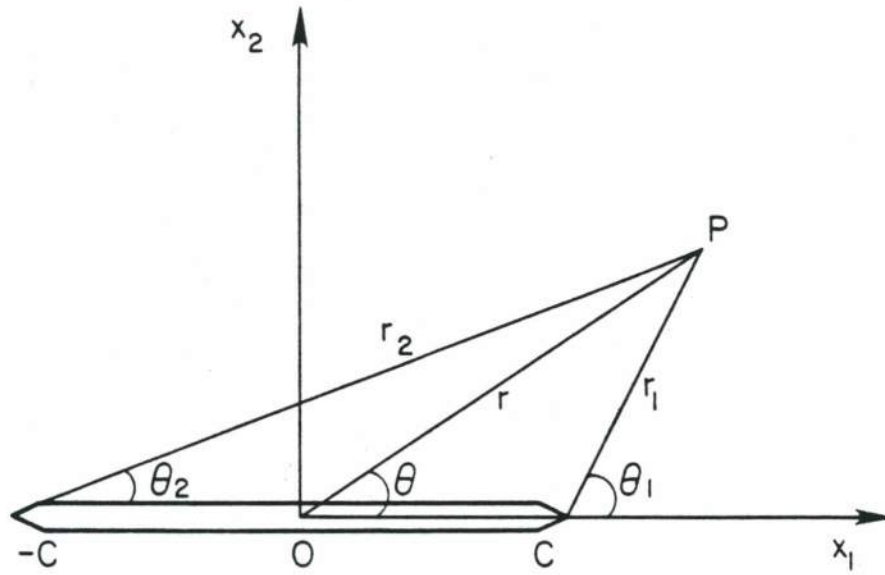

CRACK SUBJECT ANTI-PLANE SHEAR (MODE III)

FIGURE 6

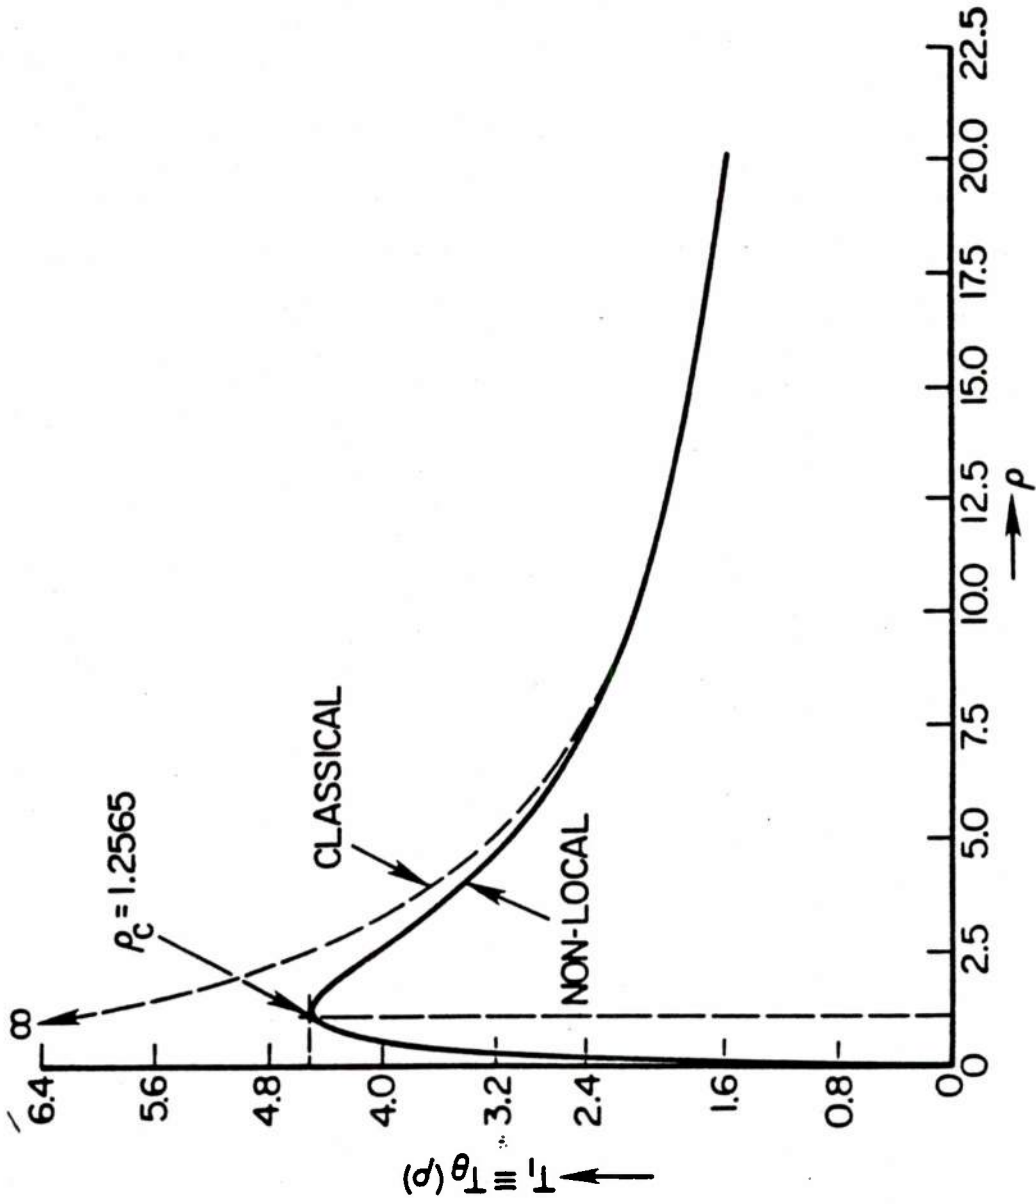


Figure 7: Nondimensional Shear in Mode III



Part 1 - Government  
Administrative and Liaison Activities

Office of Naval Research  
Department of the Navy  
Arlington, Virginia 22217  
Attn: Code 474 (2)  
Code 471  
Code 200

Director  
Office of Naval Research  
Eastern/Central Regional Office  
666 Summer Street  
Boston, Massachusetts 02210

Director  
Office of Naval Research  
Branch Office  
536 South Clark Street  
Chicago, Illinois 60605

Director  
Office of Naval Research  
New York Area Office  
715 Broadway - 5th Floor  
New York, New York 10003

Director  
Office of Naval Research  
Western Regional Office  
1030 East Green Street  
Pasadena, California 91106

Naval Research Laboratory (6)  
Code 2627  
Washington, D.C. 20375

Defense Technical Information Center (12)  
Cameron Station  
Alexandria, Virginia 22314

Navy

Undersea Explosion Research Division  
Naval Ship Research and Development  
Center  
Norfolk Naval Shipyard  
Portsmouth, Virginia 23709  
Attn: Dr. E. Palmer, Code 177

Navy (Con't.)

Naval Research Laboratory  
Washington, D.C. 20375  
Attn: Code 8400  
8410  
8430  
8440  
6300  
6390  
6380

David W. Taylor Naval Ship Research  
and Development Center  
Annapolis, Maryland 21402  
Attn: Code 2740  
28  
281

Naval Weapons Center  
China Lake, California 93555  
Attn: Code 4062  
4520

Commanding Officer  
Naval Civil Engineering Laboratory  
Code L31  
Port Hueneme, California 93041

Naval Surface Weapons Center  
White Oak  
Silver Spring, Maryland 20910  
Attn: Code R-10  
G-402  
K-82

Technical Director  
Naval Ocean Systems Center  
San Diego, California 92152

Supervisor of Shipbuilding  
U.S. Navy  
Newport News, Virginia 23607

Navy Underwater Sound  
Reference Division  
Naval Research Laboratory  
P.O. Box 8337  
Orlando, Florida 32806

Chief of Naval Operations  
Department of the Navy  
Washington, D.C. 20350  
Attn: Code OP-098

474:NP:716:lab  
78u474-619

Navy (Con't.)

Strategic Systems Project Office  
Department of the Navy  
Washington, D.C. 20376  
Attn: NSP-200

Naval Air Systems Command  
Department of the Navy  
Washington, D.C. 20361  
Attn: Code 5302 (Aerospace and Structures)  
604 (Technical Library)  
320B (Structures)

Naval Air Development Center  
Warminster, Pennsylvania 18974  
Attn: Aerospace Mechanics  
Code 606

U.S. Naval Academy  
Engineering Department  
Annapolis, Maryland 21402

Naval Facilities Engineering Command  
200 Stovall Street  
Alexandria, Virginia 22332  
Attn: Code 03 (Research and Development)  
04B  
045  
14114 (Technical Library)

Naval Sea Systems Command  
Department of the Navy  
Washington, D.C. 20362  
Attn: Code 05H  
312  
322  
323  
05R  
32R

Navy (Con't.)

Commander and Director  
David W. Taylor Naval Ship  
Research and Development Center  
Bethesda, Maryland 20084  
Attn: Code 042  
17  
172  
173  
174  
1800  
1844  
012.2  
1900  
1901  
1945  
1960  
1962

Naval Underwater Systems Center  
Newport, Rhode Island 02840  
Attn: Bruce Sandman, Code 3634

Naval Surface Weapons Center  
Dahlgren Laboratory  
Dahlgren, Virginia 22448  
Attn: Code G04  
G20

Technical Director  
Mare Island Naval Shipyard  
Vallejo, California 94592

U.S. Naval Postgraduate School  
Library  
Code 0384  
Monterey, California 93940

Webb Institute of Naval Architecture  
Attn: Librarian  
Crescent Beach Road, Glen Cove  
Long Island, New York 11542

Army

Commanding Officer (2)  
U.S. Army Research Office  
P.O. Box 12211  
Research Triangle Park, NC 27709  
Attn: Mr. J. J. Murray, CRD-AA-IP

Army (Con't.)

Watervliet Arsenal  
MAGGS Research Center  
Watervliet, New York 12189  
Attn: Director of Research

U.S. Army Materials and Mechanics  
Research Center  
Watertown, Massachusetts 02172  
Attn: Dr. R. Shea, DRXMR-T

U.S. Army Missile Research and  
Development Center  
Redstone Scientific Information  
Center  
Chief, Document Section  
Redstone Arsenal, Alabama 35809

Army Research and Development  
Center  
Fort Belvoir, Virginia 22060

NASA

National Aeronautics and Space  
Administration  
Structures Research Division  
Langley Research Center  
Langley Station  
Hampton, Virginia 23365

National Aeronautics and Space  
Administration  
Associate Administrator for Advanced  
Research and Technology  
Washington, D.C. 20546

Air Force

Wright-Patterson Air Force Base  
Dayton, Ohio 45433  
Attn: AFFDL (FB)  
(FBR)  
(FBE)  
(FBS)  
AFML (MBM)

Chief Applied Mechanics Group  
U.S. Air Force Institute of Technology  
Wright-Patterson Air Force Base  
Dayton, Ohio 45433

Air Force (Con't.)

Chief, Civil Engineering Branch  
WLRC, Research Division  
Air Force Weapons Laboratory  
Kirtland Air Force Base  
Albuquerque, New Mexico 87117

Air Force Office of Scientific Research  
Bolling Air Force Base  
Washington, D.C. 20332  
Attn: Mechanics Division

Department of the Air Force  
Air University Library  
Maxwell Air Force Base  
Montgomery, Alabama 36112

Other Government Activities

Commandant  
Chief, Testing and Development Division  
U.S. Coast Guard  
1300 E Street, NW.  
Washington, D.C. 20226

Technical Director  
Marine Corps Development  
and Education Command  
Quantico, Virginia 22134

Director Defense Research  
and Engineering  
Technical Library  
Room 3C128  
The Pentagon  
Washington, D.C. 20301

Dr. M. Gaus  
National Science Foundation  
Environmental Research Division  
Washington, D.C. 20550

Library of Congress  
Science and Technology Division  
Washington, D.C. 20540

Director  
Defense Nuclear Agency  
Washington, D.C. 20305  
Attn: SPSS

Other Government Activities (Con't)

Mr. Jerome Persh  
Staff Specialist for Materials  
and Structures  
OUSDR&E, The Pentagon  
Room 3D1089  
Washington, D.C. 20301

Chief, Airframe and Equipment Branch  
FS-120  
Office of Flight Standards  
Federal Aviation Agency  
Washington, D.C. 20553

National Academy of Sciences  
National Research Council  
Ship Hull Research Committee  
2101 Constitution Avenue  
Washington, D.C. 20418  
Attn: Mr. A. R. Lytle

National Science Foundation  
Engineering Mechanics Section  
Division of Engineering  
Washington, D.C. 20550

Picatinny Arsenal  
Plastics Technical Evaluation Center  
Attn: Technical Information Section  
Dover, New Jersey 07801

Maritime Administration  
Office of Maritime Technology  
14th and Constitution Avenue, NW.  
Washington, D.C. 20230

PART 2 - Contractors and Other Technical  
Collaborators

Universities

Dr. J. Tinsley Oden  
University of Texas at Austin  
345 Engineering Science Building  
Austin, Texas 78712

Professor Julius Miklowitz  
California Institute of Technology  
Division of Engineering  
and Applied Sciences  
Pasadena, California 91109

Universities (Con't)

Dr. Harold Liebowitz, Dean  
School of Engineering and  
Applied Science  
George Washington University  
Washington, D.C. 20052

Professor Eli Sternberg  
California Institute of Technology  
Division of Engineering and  
Applied Sciences  
Pasadena, California 91109

Professor Paul M. Naghdi  
University of California  
Department of Mechanical Engineering  
Berkeley, California 94720

Professor A. J. Durelli  
Oakland University  
School of Engineering  
Rochester, Missouri 48063

Professor F. L. DiMaggio  
Columbia University  
Department of Civil Engineering  
New York, New York 10027

Professor Norman Jones  
The University of Liverpool  
Department of Mechanical Engineering  
P. O. Box 147  
Brownlow Hill  
Liverpool L69 3BX  
England

Professor E. J. Skudrzyk  
Pennsylvania State University  
Applied Research Laboratory  
Department of Physics  
State College, Pennsylvania 16801

Professor J. Klosner  
Polytechnic Institute of New York  
Department of Mechanical and  
Aerospace Engineering  
333 Jay Street  
Brooklyn, New York 11201

Professor R. A. Schapery  
Texas A&M University  
Department of Civil Engineering  
College Station, Texas 77843

Universities (Con't.)

Professor Walter D. Pilkey  
University of Virginia  
Research Laboratories for the  
Engineering Sciences and  
Applied Sciences  
Charlottesville, Virginia 22901

Professor K. D. Willmert  
Clarkson College of Technology  
Department of Mechanical Engineering  
Potsdam, New York 13676

Dr. Walter E. Haisler  
Texas A&M University  
Aerospace Engineering Department  
College Station, Texas 77843

Dr. Hussein A. Kamel  
University of Arizona  
Department of Aerospace and  
Mechanical Engineering  
Tucson, Arizona 85721

Dr. S. J. Fenves  
Carnegie-Mellon University  
Department of Civil Engineering  
Schenley Park  
Pittsburgh, Pennsylvania 15213

Dr. Ronald L. Huston  
Department of Engineering Analysis  
University of Cincinnati  
Cincinnati, Ohio 45221

Professor G. C. M. Sih  
Lehigh University  
Institute of Fracture and  
Solid Mechanics  
Bethlehem, Pennsylvania 18015

Professor Albert S. Kobayashi  
University of Washington  
Department of Mechanical Engineering  
Seattle, Washington 98105

Professor Daniel Frederick  
Virginia Polytechnic Institute and  
State University  
Department of Engineering Mechanics  
Blacksburg, Virginia 24061

Universities (Con't)

Professor A. C. Eringen  
Princeton University  
Department of Aerospace and  
Mechanical Sciences  
Princeton, New Jersey 08540

Professor E. H. Lee  
Stanford University  
Division of Engineering Mechanics  
Stanford, California 94305

Professor Albert I. King  
Wayne State University  
Biomechanics Research Center  
Detroit, Michigan 48202

Dr. V. R. Hodgson  
Wayne State University  
School of Medicine  
Detroit, Michigan 48202

Dean B. A. Boley  
Northwestern University  
Department of Civil Engineering  
Evanston, Illinois 60201

Professor P. G. Hodge, Jr.  
University of Minnesota  
Department of Aerospace Engineering  
and Mechanics  
Minneapolis, Minnesota 55455

Dr. D. C. Drucker  
University of Illinois  
Dean of Engineering  
Urbana, Illinois 61801

Professor N. M. Newmark  
University of Illinois  
Department of Civil Engineering  
Urbana, Illinois 61803

Professor E. Reissner  
University of California, San Diego  
Department of Applied Mechanics  
La Jolla, California 92037

Professor William A. Nash  
University of Massachusetts  
Department of Mechanics and  
Aerospace Engineering  
Amherst, Massachusetts 01002



Universities (Con't)

Professor G. Herrmann  
Stanford University  
Department of Applied Mechanics  
Stanford, California 94305

Professor J. D. Achenbach  
Northwest University  
Department of Civil Engineering  
Evanston, Illinois 60201

Professor S. B. Dong  
University of California  
Department of Mechanics  
Los Angeles, California 90024

Professor Burt Paul  
University of Pennsylvania  
Towne School of Civil and  
Mechanical Engineering  
Philadelphia, Pennsylvania 19104

Professor H. W. Liu  
Syracuse University  
Department of Chemical Engineering  
and Metallurgy  
Syracuse, New York 13210

Professor S. Bodner  
Technion R&D Foundation  
Haifa, Israel

Professor Werner Goldsmith  
University of California  
Department of Mechanical Engineering  
Berkeley, California 94720

Professor R. S. Rivlin  
Lehigh University  
Center for the Application  
of Mathematics  
Bethlehem, Pennsylvania 18015

Professor F. A. Cozzarelli  
State University of New York at  
Buffalo  
Division of Interdisciplinary Studies  
Karr Parker Engineering Building  
Chemistry Road  
Buffalo, New York 14214

Universities (Con't)

Professor Joseph L. Rose  
Drexel University  
Department of Mechanical Engineering  
and Mechanics  
Philadelphia, Pennsylvania 19104

Professor B. K. Donaldson  
University of Maryland  
Aerospace Engineering Department  
College Park, Maryland 20742

Professor Joseph A. Clark  
Catholic University of America  
Department of Mechanical Engineering  
Washington, D.C. 20064

Dr. Samuel B. Batdorf  
University of California  
School of Engineering  
and Applied Science  
Los Angeles, California 90024

Professor Isaac Fried  
Boston University  
Department of Mathematics  
Boston, Massachusetts 02215

Professor E. Krempl  
Rensselaer Polytechnic Institute  
Division of Engineering  
Engineering Mechanics  
Troy, New York 12181

Dr. Jack R. Vinson  
University of Delaware  
Department of Mechanical and Aerospace  
Engineering and the Center for  
Composite Materials  
Newark, Delaware 19711

Dr. J. Duffy  
Brown University  
Division of Engineering  
Providence, Rhode Island 02912

Dr. J. L. Swedlow  
Carnegie-Mellon University  
Department of Mechanical Engineering  
Pittsburgh, Pennsylvania 15213

Universities (Con't)

Dr. V. K. Varadan  
Ohio State University Research Foundation  
Department of Engineering Mechanics  
Columbus, Ohio 43210

Dr. Z. Hashin  
University of Pennsylvania  
Department of Metallurgy and  
Materials Science  
College of Engineering and  
Applied Science  
Philadelphia, Pennsylvania 19104

Dr. Jackson C. S. Yang  
University of Maryland  
Department of Mechanical Engineering  
College Park, Maryland 20742

Professor T. Y. Chang  
University of Akron  
Department of Civil Engineering  
Akron, Ohio 44325

Professor Charles W. Bert  
University of Oklahoma  
School of Aerospace, Mechanical,  
and Nuclear Engineering  
Norman, Oklahoma 73019

Professor Satya N. Atluri  
Georgia Institute of Technology  
School of Engineering and  
Mechanics  
Atlanta, Georgia 30332

Professor Graham F. Carey  
University of Texas at Austin  
Department of Aerospace Engineering  
and Engineering Mechanics  
Austin, Texas 78712

Dr. S. S. Wang  
University of Illinois  
Department of Theoretical and  
Applied Mechanics  
Urbana, Illinois 61801

Professor J. F. Abel  
Cornell University  
Department of Theoretical  
and Applied Mechanics  
Ithaca, New York 14853

Universities (Con't)

Professor V. H. Neubert  
Pennsylvania State University  
Department of Engineering Science  
and Mechanics  
University Park, Pennsylvania 16802

Professor A. W. Leissa  
Ohio State University  
Department of Engineering Mechanics  
Columbus, Ohio 43212

Professor C. A. Brebbia  
University of California, Irvine  
Department of Civil Engineering  
School of Engineering  
Irvine, California 92717

Dr. George T. Rahn  
Vanderbilt University  
Mechanical Engineering and  
Materials Science  
Nashville, Tennessee 37235

Dean Richard H. Gallagher  
University of Arizona  
College of Engineering  
Tucson, Arizona 85721

Professor E. F. Rybicki  
The University of Tulsa  
Department of Mechanical Engineering  
Tulsa, Oklahoma 74104

Dr. R. Haftka  
Illinois Institute of Technology  
Department of Mechanics and Mechanical  
and Aerospace Engineering  
Chicago, Illinois 60616

Professor J. G. de Oliveira  
Massachusetts Institute of Technology  
Department of Ocean Engineering  
77 Massachusetts Avenue  
Cambridge, Massachusetts 02139

Dr. Bernard W. Shaffer  
Polytechnic Institute of New York  
Route 110  
Farmingdale, New York 11735

Industry and Research Institutes

Dr. Norman Hobbs  
Kaman Avidyne  
Division of Kaman  
Sciences Corporation  
Burlington, Massachusetts 01803

Argonne National Laboratory  
Library Services Department  
9700 South Cass Avenue  
Argonne, Illinois 60440

Dr. M. C. Junger  
Cambridge Acoustical Associates  
54 Rindge Avenue Extension  
Cambridge, Massachusetts 02140

Mr. J. H. Torrance  
General Dynamics Corporation  
Electric Boat Division  
Groton, Connecticut 06340

Dr. J. E. Greenspon  
J. G. Engineering Research Associates  
3831 Menlo Drive  
Baltimore, Maryland 21215

Newport News Shipbuilding and  
Dry Dock Company  
Library  
Newport News, Virginia 23607

Dr. W. F. Bozich  
McDonnell Douglas Corporation  
5301 Bolsa Avenue  
Huntington Beach, California 92647

Dr. H. N. Abramson  
Southwest Research Institute  
8500 Culebra Road  
San Antonio, Texas 78284

Dr. R. C. DeHart  
Southwest Research Institute  
8500 Culebra Road  
San Antonio, Texas 78284

Dr. M. L. Baron  
Weidlinger Associates  
110 East 59th Street  
New York, New York 10022

Industry and Research Institutes (Con't)

Dr. T. L. Geers  
Lockheed Missiles and Space Company  
3251 Hanover Street  
Palo Alto, California 94304

Mr. William Caywood  
Applied Physics Laboratory  
Johns Hopkins Road  
Laurel, Maryland 20810

Dr. Robert E. Dunham  
Pacifica Technology  
P.O. Box 148  
Del Mar, California 92014

Dr. M. F. Kanninen  
Battelle Columbus Laboratories  
505 King Avenue  
Columbus, Ohio 43201

Dr. A. A. Hochrein  
Daedalean Associates, Inc.  
Springlake Research Road  
15110 Frederick Road  
Woodbine, Maryland 21797

Dr. James W. Jones  
Swanson Service Corporation  
P.O. Box 5415  
Huntington Beach, California 92646

Dr. Robert E. Nickell  
Applied Science and Technology  
3344 North Torrey Pines Court  
Suite 220  
La Jolla, California 92037

Dr. Kevin Thomas  
Westinghouse Electric Corp.  
Advanced Reactors Division  
P. O. Box 158  
Madison, Pennsylvania 15663

Dr. H. D. Hibbitt  
Hibbitt & Karlsson, Inc.  
132 George M. Cohan Boulevard  
Providence, Rhode Island 02903

Dr. R. D. Mindlin  
89 Deer Hill Drive  
Ridgefield, Connecticut 06877



Industry and Research Institutes (Con't)

Dr. Richard E. Dame  
Mega Engineering  
11961 Tech Road  
Silver Spring, Maryland 20904

Mr. G. M. Stanley  
Lockheed Palo Alto Research  
Laboratory  
3251 Hanover Street  
Palo Alto, California 94304

Mr. R. L. Cloud  
Robert L. Cloud Associates, Inc.  
2972 Adeline Street  
Berkeley, California 94703